

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

6,900

Open access books available

185,000

International authors and editors

200M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.
For more information visit www.intechopen.com



Design, Manufacturing and Testing of Polymer Composite Multi-Leaf Spring for Light Passenger Automobiles - A Review

Senthilkumar Mouleeswaran
*Assistant Professor (Senior Grade),
 Department of Mechanical Engineering
 PSG College of Technology
 Coimbatore
 India*

1. Introduction

Weight reduction has been the main/primary focus of automobile manufactures. Suspension leaf spring, a potential item for weight reduction in automobiles, accounts for 10-25 percent of unsprung weight, (which is considered to be the mass not supported by leaf spring). Application of composite materials reduces the weight of leaf spring without any reduction on the load carrying capacity and stiffness in automobile suspension system (Daugherty, 1981; Breadmore, 1986; Morris, 1986). A double tapered beam for automotive suspension leaf spring has been designed and optimized (Yu & Kim, 1988). Composite mono leaf spring (Rajendran & Vijayarangan, 2001) has also been analyzed and optimized.

Leaf spring should absorb vertical vibrations due to road irregularities by means of variations in the spring deflection so that potential energy is stored in the spring as strain energy and then released slowly. So, increasing energy storage capability of a leaf spring ensures a more compliant suspension system. A material with maximum strength and minimum modulus of elasticity in longitudinal direction is the most suitable material (Corvi, 1990) for a leaf spring. Important characteristics of composites (Springer & Kollar, 2003) that make them excellent for leaf spring instead of steel are higher strength-to-weight ratio, superior fatigue strength, excellent corrosion resistance, smoother ride, higher natural frequency, etc. Fatigue failure is the predominant mode of in-service failure of many automobile components, especially the springs used in automobile suspension systems. Fatigue behaviour of Glass Fiber Reinforced Plastic epoxy (GFRP) composite materials has been studied (Hawang & Han, 1986). A composite mono-leaf spring has been designed and their end joints are analysed and tested for a light weight vehicle (Shivasankar & Vijayarangan, 2006). Experimental and numerical analysis are carried out on a single leaf constant cross section composite leaf spring (Jadhao & Dalu, 2011). Theoretical equation for predicting fatigue life, formulated using fatigue modulus and its degrading rate, is simplified by strain failure criterion for practical application. A prediction method for

fatigue strength of composite structures at an arbitrary combination of frequency, stress ratio and temperature has been presented (Yasushi,1997).

In the present work, a 7-leaf steel spring used in a passenger car is replaced with a composite multi leaf spring made of glass/epoxy composites. Dimensions and number of leaves of steel leaf spring (SLS) and composite leaf spring (CLS) are considered to be same. Primary objective is to compare their load carrying capacity, stiffness and weight savings of CLS. Ride comfort of both SLS and CLS is found and compared. Also, fatigue life of SLS and CLS is also predicted. This chapter of the book explores the work done on design optimisation, finite element analysis, analytical & experimental studies and life data analysis of steel and composite leaf springs (Senthilkumar & Vijayarangan,2007).

2. Steel Leaf Spring (SLS)

2.1 Design and finite element analysis

Design parameters of 7-leaf steel spring that exists in a light passenger car (available in India) are given in Table 1. The spring is assumed to be a double cantilever beam, even though the leaf spring is simply supported at the ends. Also, this spring is geometrically and materially symmetrical so that only one half is considered with cantilever beam boundary conditions for the analysis to save the calculation time. Axle seat is assumed to be fixed and loading is applied at free eye end.

| Parameters | Values |
|-------------------------------------|--------|
| Total length (eye-to-eye), mm | 1150 |
| Arc height at axle seat(Camber), mm | 175 |
| Spring rate, N/mm | 20 |
| Number of full length leaves | 2 |
| Number of graduated leaves | 5 |
| Width of the leaves, mm | 34 |
| Thickness of the leaves, mm | 5.5 |
| Full bump loading, N | 3250 |
| Spring weight, kg | 13.5 |

Table 1. Parameters of steel leaf spring.

A stress analysis was performed using two-dimensional, plane strain finite element model (FEM). A plane strain solution is considered because of the high ratio of width to thickness of a leaf. Model is restrained to the right half part only because the spring is symmetric. The contact between leaves is emulated by interface elements and all the calculations are done using ANSYS (version 7.1) (Eliahu Zahavi,1992). Nodes are created based on the values of co-ordinates calculated and each pair of coincident nodes is joined by the interface elements that simulate action between neighboring leaves. Element selected for this analysis is SOLID42(Eliahu Zahavi,1992) which behaves as the spring having plasticity, creep, swelling, stress stiffening, large deflection, and large strain capabilities. Element is defined by four nodes having two degrees of freedom at each node: translations in the nodal x and y directions. Interface elements CONTA174 that is defined by eight nodes and TARGE170 are used to represent contact and sliding between adjacent surfaces of leaves. The contact

elements themselves overlay the solid elements describing the boundary of a deformable body and are potentially in contact with the target surface, defined by TARGE170. This target surface is discretized by a set of target segment elements (TARGE170) and is paired with its associated contact surface via a shared real constant set. An average coefficient of friction 0.03 is taken between surfaces(SAE manual). Also, analytical solution is carried out using spring design SAE manual.

2.2 Static testing

The static testing on existing steel leaf spring was carried out using an electro-hydraulic test rig which is depicted in Fig.1. The rig has the ability to apply a maximum static load of 10 kN. It has a display unit to show both load and corresponding deflection. The loading was gradually from no load to full bump load of 3250 N. The strain gauges were employed to measure strain and to calculate stress. The experimental data corresponding to steel leaf spring is given in Table 2. Maximum normal stress, σ_{11} from FEM is compared to the experimental solution under full bump loading (error, 8.63%). There is a good correlation for stiffness in experimental, analytical and FEM methods (Table 2).

| Parameters | Experiment | Analytical | FEM |
|-------------------------|------------|------------|--------|
| Load, N | 3250 | 3250 | 3250 |
| Maximum stress, MPa | 680.05 | 982.05 | 744.32 |
| Maximum deflection, mm | 155 | 133.03 | 134.67 |
| Maximum stiffness, N/mm | 20.96 | 24.43 | 24.13 |

Table 2. Stress analysis of steel leaf spring using experimental, analytical and FEM.

3. Composite Leaf Spring (CLS) (Senthilkumar & Vijayarangan,2007)

Applicability of CLS in automobiles is evaluated by considering the types of vehicles and different loading on them. Theoretical details of composite mono-leaf spring are reported (Ryan,1985; Richrad et al., 1990). In some designs, width is fixed and in each section the thickness is varied hyperbolically so that thickness is minimum at two edges and is maximum in the middle (Nickel,1986). Another design, in which width and thickness are fixed from eyes to middle of spring and towards the axle seat width decreases hyperbolically and thickness increases linearly, has been presented (Yu & Kim, 1988). In this design, curvature of spring and fiber misalignment in the width and thickness direction are neglected. A double tapered CLS has been designed and tested with optimizing its size for minimum weight(Rajendran & Vijayarangan,2002). A composite mono-leaf spring has also been designed and optimized with joint design(Mahmood & Davood,2003). The mono-leaf spring is not easily replaceable on its catastrophic failure. Hence, in this work, a composite multi leaf spring is designed and tested for its load carrying capacity, stiffness and fatigue life prediction using a more realistic situation.

3.1 Material selection

Material selected should be capable of storing more strain energy in leaf spring. Specific elastic strain energy can be written as:

$$S = \frac{1}{2} \frac{\sigma_t^2}{\rho E}$$

(1)

where σ_t is allowable stress, E is modulus of elasticity and ρ is density. Based on specific strain energy of steel spring and some composite materials(Yu&Kim,1988), E-glass/epoxy is selected as spring material having the mechanical properties given in Table 3. This material is assumed to be linearly elastic and orthotropic.

| Parameters | Values |
|----------------------------|-----------------------|
| Modulus of elasticity, GPa | E_{11} , 38.6 |
| Modulus of elasticity, GPa | E_{22} , 8.27 |
| Modulus of shear, GPa | G_{12} , 4.14 |
| Poisson ratio, | ν_{xy} , 0.26 |
| Tensile strength, MPa | σ_{t11} , 1062 |
| Tensile strength, MPa | σ_{t22} , 31 |
| Compressive strength, MPa | σ_{c11} , 610 |
| Compressive strength, MPa | σ_{c22} , 118 |
| Shear strength, MPa | τ_{12} , 71 |

Table 3. Mechanical properties of E-glass/epoxy(Springer & Kollar,2003).

3.2 Layup selection

Stored elastic strain energy in a leaf spring varies directly with the square of maximum allowable stress and inversely with the modulus of elasticity both in the longitudinal and transverse directions according to Eq. (1). Composite materials like E-glass/epoxy in the direction of fibers have good characteristics for storing strain energy. So, lay up is selected to be unidirectional along the longitudinal direction of spring. This also helped in fabricating process using filament-winding machine.

3.3 Design and finite element analysis of composite leaf spring

With the extensive use of laminated composite materials in almost all engineering fields, the optimal design of laminated composites has been an extensive subject of research in recent years. The dimensions of the composite leaf spring are taken as that of the conventional steel leaf spring. Each leaf of the composite leaf spring consists of 20 plies of thickness 0.275 mm each. The number of leaves is also the same for composite leaf spring. The design parameters selected are listed in Table 4.

A 3-D model of the leaf spring is used for the analysis in ANSYS 7.1, since the properties of the composite leaf spring vary with the directions of the fiber. The loading conditions are assumed to be static.The element chosen is SOLID46, which is a layered version of the 8-node structural solid element to model layered thick shells or solids. The element allows up to 250 different material layers. To establish contact between the leaves, the interface elements CONTACT174 and TARGET170 are chosen.

Individual leaves are fabricated using a filament-winding machine. A fiber volume fraction of 0.6 is used. All individual leaves are assembled together using a center bolt and four side

clamps. Also metal spring eyes are fixed at both the ends. CLS is tested with an electro-hydraulic leaf spring test rig (Fig. 1). Four CLSs were manufactured and tested. The spring, which provided the lowest stiffness and highest stress values, has been considered for comparative purpose because it satisfies the fail-safe condition. The reason for the stiffness and stress variations may be due to variation in volume fraction obtained in the fabrication process or due to lack of complete curing. A reasonably good weight reduction (68.15%) is achieved by using CLS (4.3 kg) in place of SLS (13.5 kg).

| Parameters | Values |
|-------------------------------|--------|
| Thickness of each leaf, mm | 5.5 |
| Width of the each leaf ,mm | 34 |
| Thickness of the fiber, mm | 0.2 |
| Width of the fiber, mm | 34 |
| Thickness of the resin, mm | 0.075 |
| Width of the resin, mm | 34 |
| Thickness of single layer, mm | 0.275 |
| Number of layers | 20 |

Table 4. Design parameters of composite leaf spring.

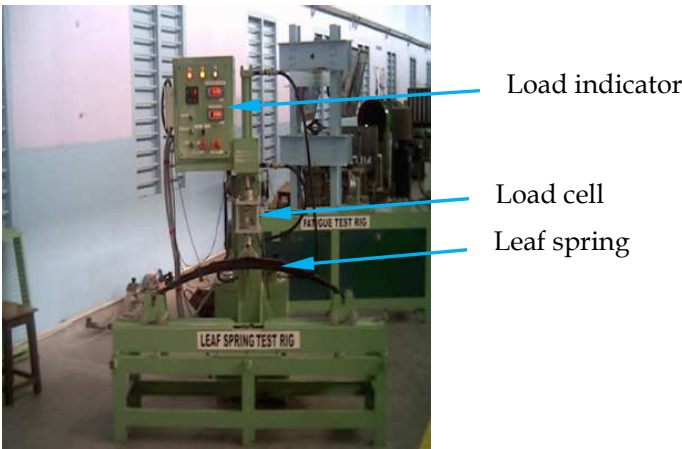


Fig. 1. Electro-hydraulic leaf spring test rig.

For a light passenger vehicle with a camber height of 175 mm, static load to flatten the leaf spring is theoretically estimated to be 3250 N. Therefore, a static vertical force of 3250 N is applied to determine the load-deflection curves (Fig. 2).The load is gradually increased to obtain the deflection of steel spring first untill it becomes completely flat. Then, for similar deflection in composite leaf spring, the loads are measured for composite leaf spring. From Fig.2, it is understood that the deflection increases linearly as load increases in both steel and composite leaf springs. For a full bump load of 3250 N, composite leaf spring deflects to 94 mm only while steel leaf spring deflects 175 mm. The FEM results of longitudinal stress and deflection of CLS are shown in Figs.3&4. During full bump load test, experimental stress measurement (Fig. 5) is carried out to verify the results of FEM analysis (Figs 3 & 4). Fig.3 shows the variation of stress in CLS along the length of the spring. Fig.4 shows the deflection of CLS at various points along the length. It is found that CLS develops the maximum stress of about 215 MPa and it deflectes about 60 mm. E-glass/epoxy composite

leaf spring has spring constants 34.57-53.59 N/mm. Thus, all the data of spring constants for CLSs are greater than the design value, 20 N/mm. The reason for increased stiffness is lower density of E-glass/epoxy composite combination.

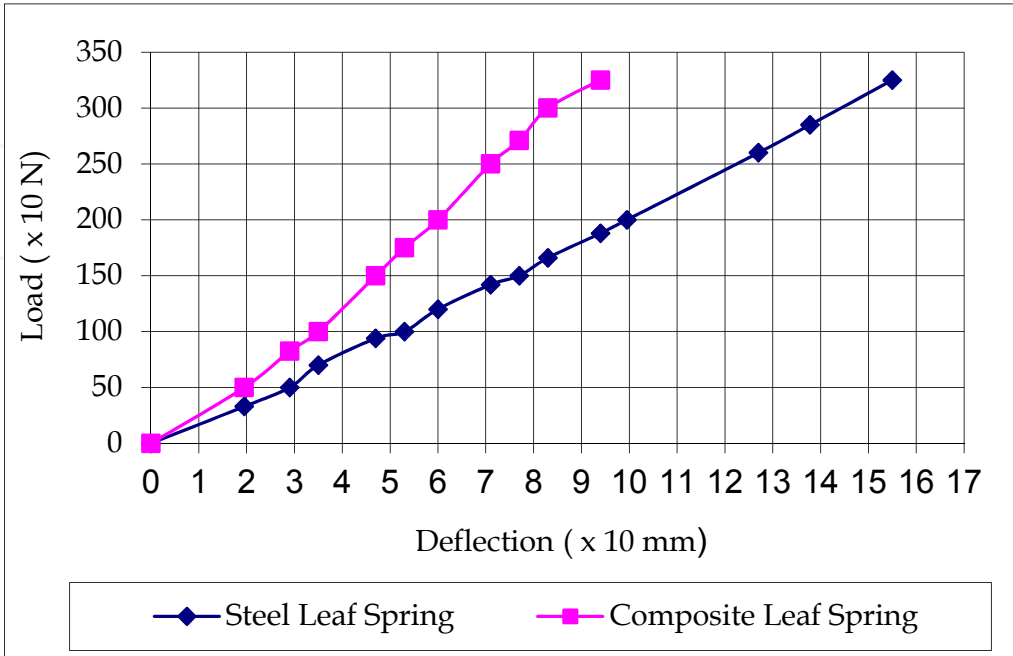


Fig. 2. Load - deflection curves for steel and composite leaf springs.

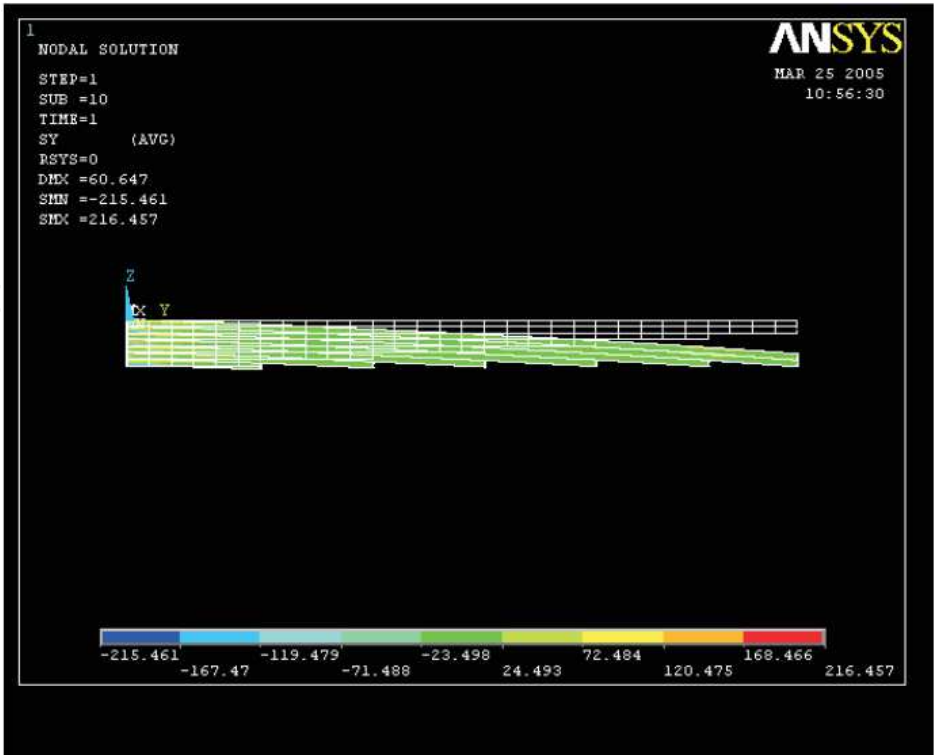


Fig. 3. FEM results of longitudinal stress of composite spring.

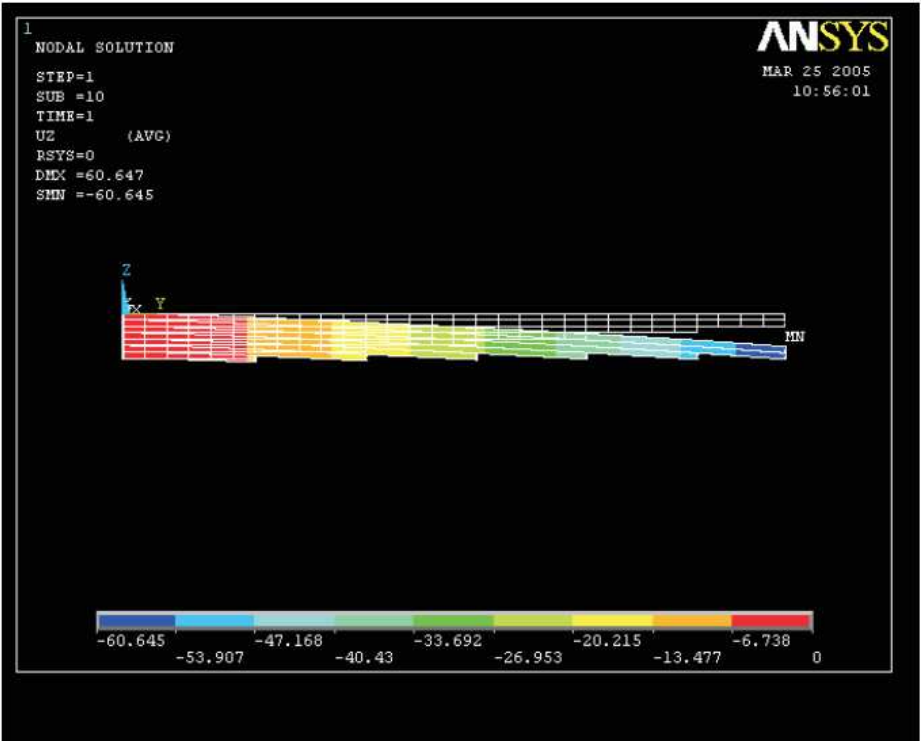


Fig. 4. FEM results of deflection of composite spring.

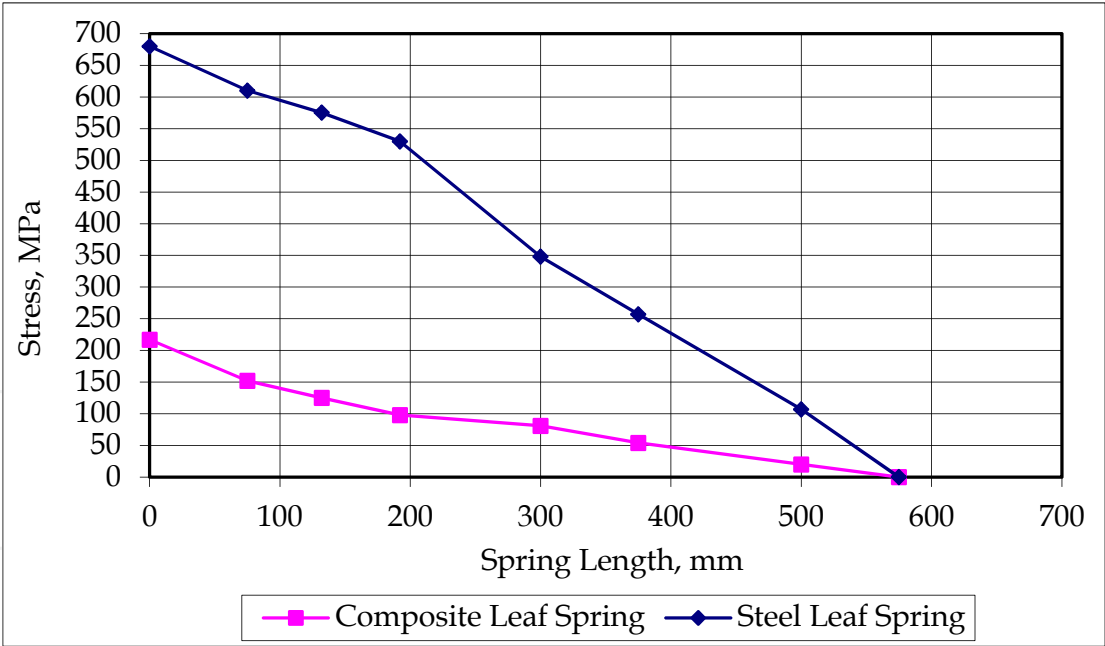


Fig. 5. Variation of experimental stress of steel and composite springs.

Leaf spring is analyzed under transverse loading condition. The longitudinal compressive strength of composite used in this analysis is less than its longitudinal tensile strength. So failure criterion stress is longitudinal compressive stress. Maximum longitudinal compressive stress (Fig. 5) is 222 MPa for CLS. At a same loading, maximum stress developed in SLS is 680 MPa (Table 2, Fig. 5). When compared with stress developed in SLS, less stress (67.35%) is developed in CLS. Compressive strength of fiber glass/epoxy is 610

MPa and yielding stress of steel is 1175 MPa. So, factor of safety obtained in SLS is 1.73, while in CLS it is 2.75. Experimental deflection of CLS under full bump loading is 94 mm (Fig. 2), which is less than the maximum value (175 mm). It shows that CLS is stiffer (64.95 %) than SLS. Table 5 gives the results of analysis of CLS using experimental, analytical and finite element methods. The variation of longitudinal stress of SLS and CLS is also presented in Figs.6&7. Fig. 6 shows the variation of longitudinal stress of steel leaf spring in FEM and experimental analysis. There is about 8% higher stress value obtained in the FEM than experiments. This is due to the fact that the constraints given at the ends of leaf spring are stiffer than the actual stiffness due the cantilever configuration in FEM. There could also be deviation from the material properties used in FEM analysis.

| Parameters | Experiment | Analytical | FEM |
|-------------------------|------------|------------|--------|
| Load, N | 3250 | 3250 | 3250 |
| Maximum stress, MPa | 222 | 310.82 | 215.46 |
| Maximum deflection, mm | 94 | 59.20 | 60.65 |
| Maximum stiffness, N/mm | 34.57 | 54.89 | 53.59 |

Table 5. Stress analysis of composite leaf spring using experimental, analytical and FEM.

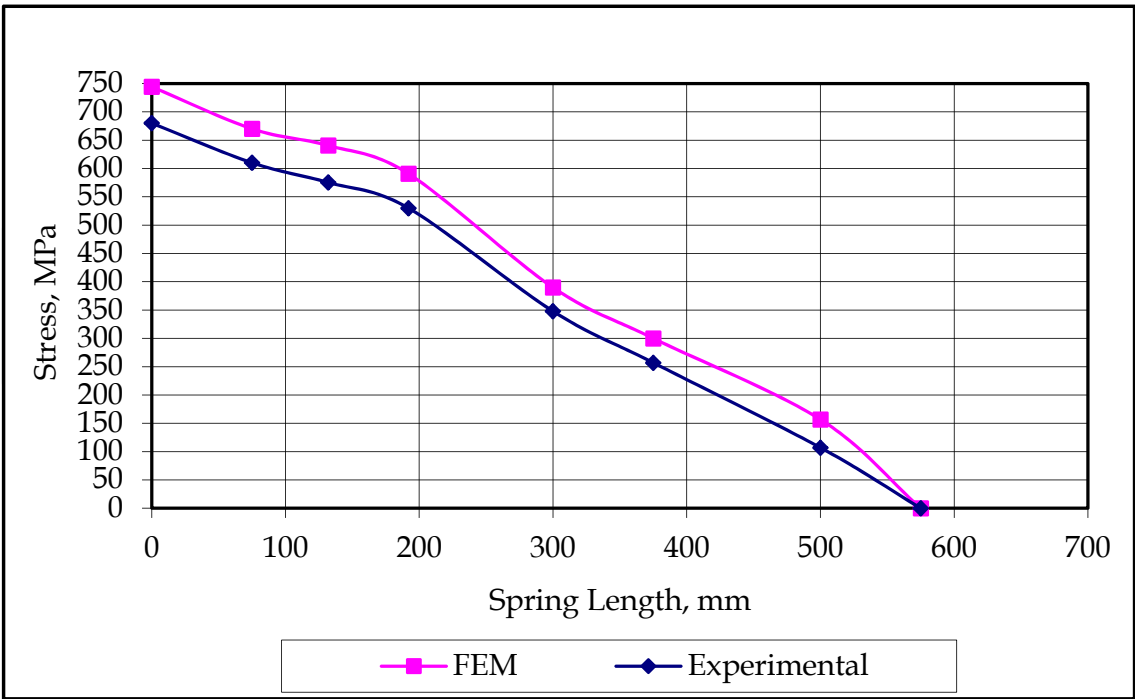


Fig. 6. Variation of longitudinal stress of steel leaf spring.

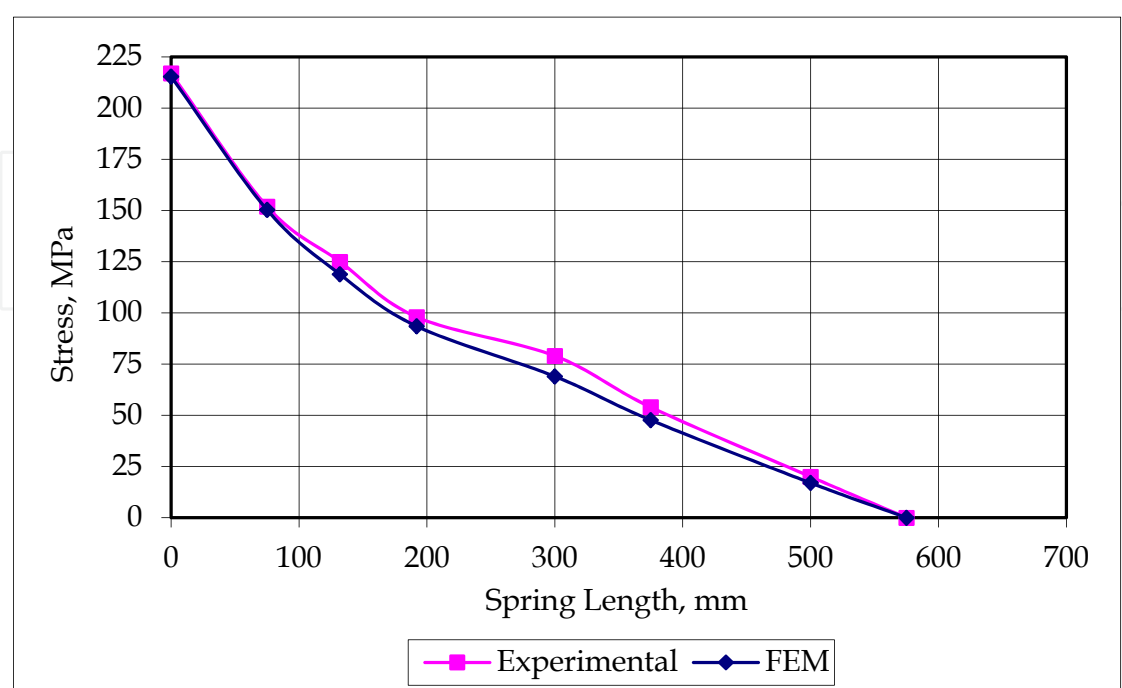


Fig. 7. Variation of longitudinal stress of composite leaf spring.

4. Fatigue analysis (Senthilkumar & Vijayarangan, 2007)

Main factors that contribute to fatigue failures include number of load cycles experienced, range of stress and mean stress experienced in each load cycle and presence of local stress concentrations. Testing of leaf springs using the regular procedure consumes a lot of time. Hence (SAE manual,1990) suggests a procedure for accelerated tests, which give quick results, particularly for SLSs. As per the outlined procedure(SAE manual,1990 & Yasushi,1997), fatigue tests are conducted on SLSs and CLSs. Fatigue life(Yasushi,1997) is expressed as the number of deflection cycles a spring will withstand without failure (Fig. 8).

4.1 Fatigue life of Steel Leaf Spring (SLS)

Fatigue life calculation of SLS is given as follows: stroke available in fatigue testing machine, 0-200 mm; initial deflection of SLS, 100 mm; initial stress (measured by experiment), 420 MPa; final deflection of SLS (camber), 175 mm; maximum stress in the final position (measured by experiment), 805 MPa. Fatigue life cycles predicted for SLS is less than 10,00,000 cycles (Fig. 8) by the procedure outlined in (SAE manual,1990).

4.2 Fatigue life of Composite Leaf Spring (CLS)

A load is applied further from the static load to maximum load with the help of the electro-hydraulic test rig, up to 3250 N, which is already obtained in static analysis. Test rig is set to operate for a deflection of 75 mm. This is the amplitude of loading cycle, which is very high. Frequency of load cycle is fixed at 33 mHz, as only 20 strokes/min is available in the test rig. This leads to high amplitude low frequency fatigue test.

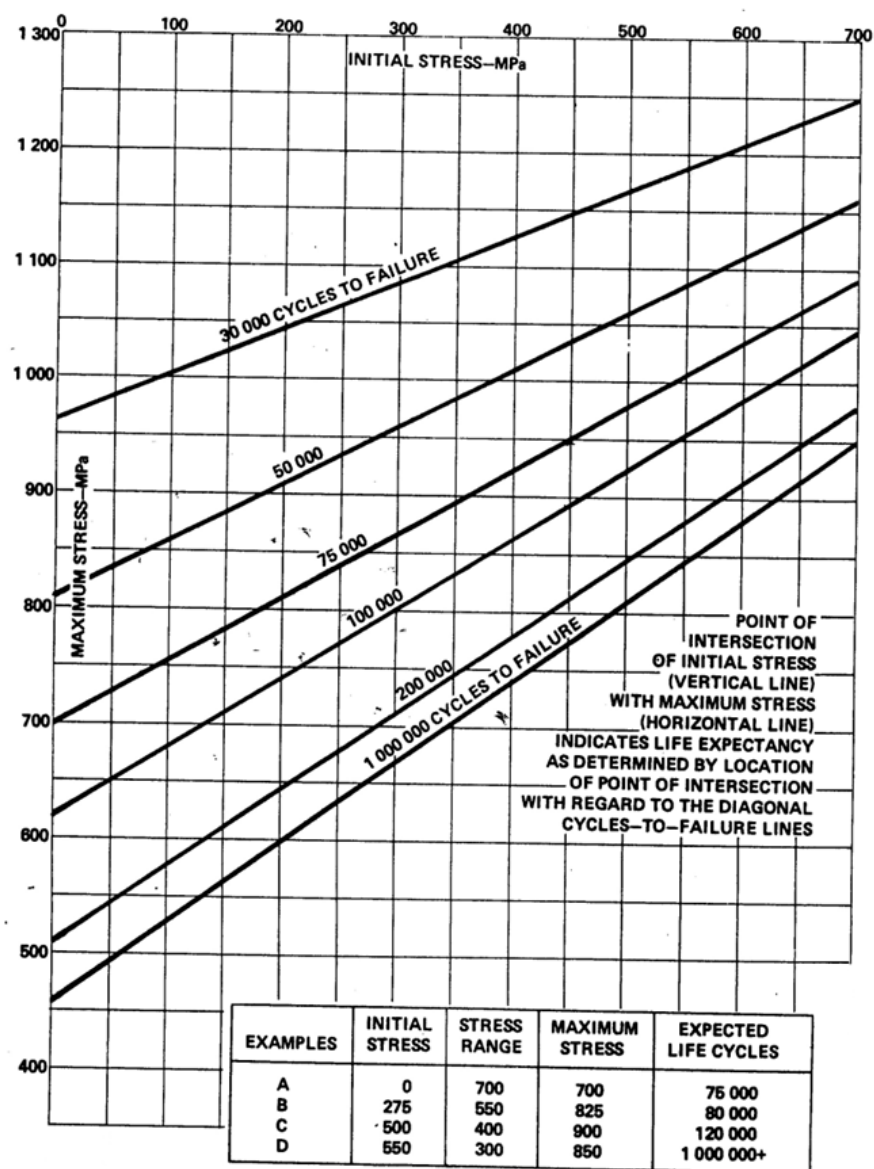


Fig. 8. Estimation of fatigue life cycles of steel leaf springs (SAE manual,1990).

Maximum and minimum stress values obtained at the first cycle of the CLS are 222 MPa and 133 MPa respectively. As the cycles go on increasing, stress convergence is happening only after 25000 cycles. These maximum and minimum operating stress values are 240 MPa and 140 MPa respectively. Because of very low stress level, fatigue life of CLS is very high under simulated conditions.

4.2.1 Life data analysis

Life data analysis (Weibull,1961) which is a statistical approach is used to find the reliability of predictions about the life of composite leaf springs by fitting a statistical distribution to life data from representative sample units. For the GFRP leaf spring, the life data is measured in terms of the number of cycles to fail for the four leaf springs and are presented in Table 6.

| Leaf spring No. | Cycles to fail | Stress level |
|-----------------|----------------|--------------|
| 1 | 10,800 | 0.65 |
| 2 | 6,950 | 0.65 |
| 3 | 19,240 | 0.65 |
| 4 | 14,350 | 0.65 |

Table 6. Number of cycles to failure for composite leaf spring.

4.2.2 Life time distribution

Weibull life distribution model is selected which has previously been used successfully for the same or a similar failure mechanism. The Weibull distribution is used to find the reliability of the life data and it helps in selecting the particular data that is to be used in life prediction model. The Weibull distribution uses two parameters, namely, ‘b’ and ‘Θ’ to estimate the reliability of the life data. ‘b’ is referred to as shape parameter and ‘Θ’ is referred to as scale parameter.

The reliability of Weibull distribution is given by,

$$R(t) = 1 - \exp[-x / \theta]^b$$

(2)

where, X is the life; b is the Weibull slope or ‘shape’ parameter and Θ is the characteristic life or ‘scale’ parameter.

The parameters of the Weibull distribution are calculated using probability plotting (Weibull, 1961). The life cycles of leaf spring are arranged in increasing order and the median rank is calculated using the Equation (3) and are shown in Table 7.

$$Medianrank = 100 * (j - 0.3) / (N + 0.4)$$

(3)

where, j is the order number and N is the total quantity of sample.

| Order No. | Cycles to fail | Median rank |
|-----------|----------------|-------------|
| 1 | 6,950 | 15.9 |
| 2 | 10,800 | 38.5 |
| 3 | 14,350 | 61.4 |
| 4 | 19,240 | 84.1 |

Table 7. Median rank of composite leaf springs.

The value of Θ is found to be 14,600 cycles. The reliability of the life data is calculated and shown in Table 8. It is found that the reliability of 3rd GFRP spring is higher than that of other leaf springs and the fatigue life data of 3rd GFRP spring has been considered for fatigue life prediction.

The fatigue test is conducted up to 20000 cycles and it is examined that no crack initiation is visible. The details of test results at 0 and 20000 cycles are as follows: maximum load cycle range, 1850-3250 N; amplitude, 75 mm; frequency, 33 mHz; spring rate, 27.66 N/mm; maximum operating stress, 240 MPa; minimum operating stress, 140MPa and time taken 17 h. The experimental results are available only up to 20000 cycles. With no crack initiation,

| Leaf spring no. | Life (cycles) | Median rank | Reliability (%) |
|-----------------|---------------|-------------|-----------------|
| 1. | 10,800 | 38.5 | 43 |
| 2. | 6,950 | 15.9 | 39 |
| 3. | 19,240 | 84.1 | 73 |
| 4. | 14,350 | 61.4 | 62.7 |

Table 8. Reliability of fatigue life data.

there is a necessity to go for analytical model for finding number of cycles to failure from analytical results. An analytical fatigue model to predict the number of fatigue cycles to failure for the components made up of composite material has been developed (Hwang and Han,1986). They have proposed two constants in their relation on the basis of experimental results. It is proved that the analytical formula predicts the fatigue life of component with E-Glass/epoxy composite material.

Hwang and Han relation: $N=\{B(1-r)\}^{1/C}$

(4)

where, N is the number of cycles to failure; B= 10.33; C= 0.14012; $r = \sigma_{\max}/\sigma_U$; σ_{\max} is the maximum stress; σ_U is the ultimate tensile strength and r is the applied stress level. Equation (4) is applied for different stress levels and fatigue life is calculated for the composite leaf spring. The results are obtained based on the analytical results (Table 9) and the resulting S-N graph is shown in Fig.9. From Fig.9, it is observed that the composite leaf spring, which is made up of E-glass/epoxy is withstanding more than 10 Lakh cycles under the stress level of 0.24.

The test was conducted for nearly 17 hours to complete 20000 cycles. The variations in stress level were reduced to very low level after 20000 cycles. There was no crack initiation up to 20000 cycles. The stress level of 0.24 is obtained from experimental analysis. This is very much helpful for the determination of remaining number of cycles to failure using fatigue model (Hwang and Han,1986). According to this fatigue model, the failure of the composite leaf spring takes place only after 10 Lakh cycles. Since the composite leaf spring is expected to crack only after 10 Lakh cycles, it is required to conduct the leaf spring fatigue test up to 10 Lakh cycles for finding type and place of crack initiation and propagation. For completing full fatigue test up to crack initiation with the same frequency, nearly 830 hours of fatigue test is required.

From the design and experimental fatigue analysis of composite multi leaf spring using glass fibre reinforced polymer are carried out using life data analysis, it is found that the composite leaf spring is found to have 67.35% lesser stress, 64.95% higher stiffness and 126.98% higher natural frequency than that of existing steel leaf spring. The conventional multi leaf spring weighs about 13.5 kg whereas the E-glass/Epoxy multi leaf spring weighs only 4.3 kg. Thus the weight reduction of 68.15% is achieved. Besides the reduction of weight, the fatigue life of composite leaf spring is predicted to be higher than that of steel leaf spring. Life data analysis is found to be a tool to predict the fatigue life of composite multi leaf spring. It is found that the life of composite leaf spring is much higher than that of steel leaf spring.

| Maximum stress MPa | Applied stress level | Number of cycles to failure |
|--------------------|----------------------|-----------------------------|
| 100 | 0.1 | 8143500 |
| 200 | 0.2 | 3515500 |
| 300 | 0.3 | 1354800 |
| 400 | 0.4 | 450900 |
| 500 | 0.5 | 122700 |
| 600 | 0.6 | 25000 |
| 700 | 0.7 | 3200 |
| 800 | 0.8 | 200 |
| 900 | 0.9 | - |
| 1000 | 1.0 | - |

Table 9. Fatigue life at different stress levels of composite leaf spring.

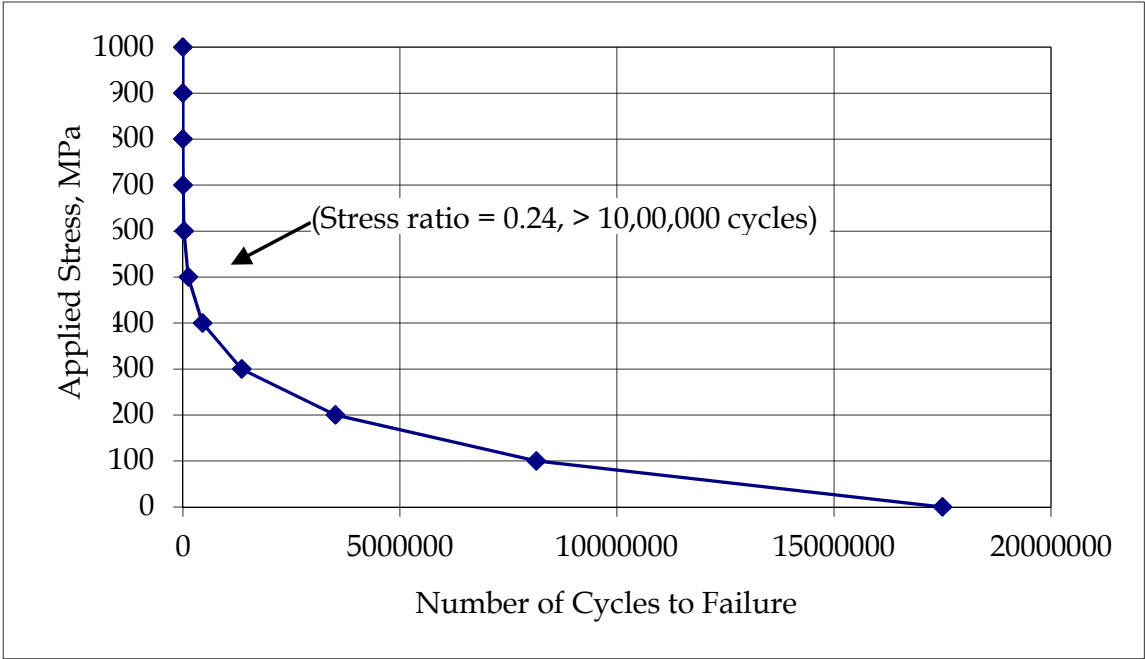


Fig. 9. S-N curve for composite leaf spring.

5. Optimisation

Optimisation of weight reduction in CLS has been carried out(Senthilkumar & Vijayarangan,2007). The finite element analysis of composite multi leaf spring with 7 leaves shows that maximum deflection of the leaf spring and the bending stress induced are well within the allowable limit (factor of safety 2.8). So, it is decided to optimize the number of leaves with minimum of 2 leaves and maximum of 7 leaves using ANSYS 7.1 itself, for the

minimum weight. The number of leaves is reduced one by one, without changing any of the dimensions, and found out results for same full bump load. The results are shown in Table 10. From the FEM results in Table 10, it is understood that the leaf spring with 3 leaves violates the constraints of deflection and stress. Therefore, further optimization is terminated at this point. It is evident that only 4 leaves (2 full length leaves and 2 graduated leaves) are sufficient to withstand the applied load. The composite leaf spring with 4 leaves weighs about 3.18 kg only. It gives a weight reduction of 76.4%.

| No.of Leaves | Maximum Deflection (mm) | | Maximum direct stress along the length of leaf spring (MPa) | |
|--------------|-------------------------|-----------|---|-----------|
| | ANSYS | Allowable | ANSYS | Allowable |
| 7 | 61 | 175 | 217 | 610 |
| 6 | 97 | | 324 | |
| 5 | 104 | | 409 | |
| 4 | 150 | | 607 | |
| 3 | 308 | | 1079 | |

Table 10. Results of optimization of number of leaves.

6. Ride comfort

To provide ride comfort to passenger, leaf spring has to be designed in such a way that its natural frequency is maintained to avoid resonant condition with respect to road frequency. The road irregularities usually have the maximum frequency of 12 Hz(Yu&Kim,1988). Therefore, leaf spring should be designed to have a natural frequency, which is away from 12 Hz to avoid the resonance. Stiffness is more and weight is lower of CLS than that of SLS. Therefore, first natural frequency of CLS (14.3 Hz) will be higher (126.98%) than that of SLS (6.3 Hz). First natural frequency of CLS is nearly 1.2 times the maximum road frequency and therefore resonance will not occur, and it provides improved ride comfort. After optimization, CLS has a fundamental natural frequency of 41.5 Hz, which is 3.46 times the maximum road frequency, which ensures that resonance will not occur.

7. Conclusion

Design and experimental analysis of composite multi leaf spring using glass fibre reinforced polymer are carried out. Compared to steel spring, the composite leaf spring is found to have 67.35% lesser stress, 64.95% higher stiffness and 126.98% higher natural frequency than that of existing steel leaf spring. The conventional multi leaf spring weighs about 13.5 kg whereas the E-glass/Epoxy multi leaf spring weighs only 4.3 kg. Thus the weight reduction of 68.15% is achieved. Besides the reduction of weight, the performance of the leaf spring is also increased. Compared to the steel leaf spring (13.5 kg), the optimised composite leaf spring weighs nearly 76.4% less than the steel spring. Ride comfort and life of CLS are also more when compared to SLS. Therefore, it is concluded that composite multi leaf spring is an effective replacement for the existing steel leaf spring in light passenger vehicles.

8. Acknowledgement

This work is carried out as part of research project supported by Defense Research and Development Organisation (DRDO), India. Author is grateful for the financial support provided by DRDO.

9. References

- ANSYS 7.1. Manual, (1997). Ansys Inc, New York
- Breadmore, P. & Johnson, C. F. (1986). The potential for composites in structural automotive Applications, *Composites science and Technology*, Vol. 26, No.4, pp. (251- 281), ISSN 0266-3538
- Corvi, A. (1990). A preliminary approach to composite beam design using FEM analysis, *Composite structures*, Vol. 16, No.(1-3), pp. (259 – 275), ISSN 0263-8223
- Daugherty, R.L. (1981). Composite leaf springs in heavy truck applications, *Proceedings of International conference of composites material*, ISBN 493113601X, Tokyo
- Eliahu Zahavi. (1992). *The finite element method in machine design*, Prentice Hall, ISBN 0133182398, New York.
- Hawang, W. & Han, K.S. (1986). Fatigue of composites – fatigue modulus concept and life prediction, *Journal of composite material*, Vol. 20, pp. (154 - 165), ISSN 0021-9983
- Jadhao, K.K. & Dalu, R.S. (2011). Experimental investigation & numerical analysis of composite leaf spring, *International journal of engineering science and technology*, Vol.3, No.6,pp.(4759-4764), ISSN 0975-5462.
- Morris, C. J. (1986). Composites structures for automobiles, *Composite structures*, Vol. 5, No.3, pp. (163 – 176), ISSN 0263-8223
- Mahmood, M.S. & Davood, R. (2003). Analysis and optimization of a composite leaf spring, *Composite structures*, Vol.60, pp.(317-325), ISSN 0263-8223
- Nickel, H.W. (January 1986). Bushing construction for a fiber reinforced plastic leaf spring, *US pat 4,565,356*
- Ryan, W.E. (December 1985). Method of making a molded fiber reinforced plastic leaf spring, *US pat 4, 560, 525*
- Richrad, D.S.; Mutzner, J.E. & Eiler, J.F. (January, 1990). Method of forming a composite leaf spring with fabric wear pad, *US pat 4,894,108*
- Rajendran, I. & Vijayarangan, S. (2001). Optimal design of a composites leaf spring using genetic algorithm, *Computers and structures*, Vol. 79, No.11, pp. (1121 – 1129), ISSN 0045-7949
- Senthilkumar, M. & Vijayarangan, S. (2007). Design optimization and experimental analysis of composite leaf spring for light passenger vehicles, *Advances in vibration engineering*, Vol.6, No.3, pp.(175-183), ISSN 0972-5768
- Senthilkumar, M. & Vijayarangan, S. (2007). Static analysis and fatigue life prediction of steel and composite leaf spring for light passenger vehicles, *Journal of scientific & industrial research*, Vol.66, No.2,pp.(128-134), ISSN: 0022-4456
- Senthilkumar, M. & Vijayarangan, S. (2007). Analytical and experimental studies on fatigue life prediction of steel and composite multi-leaf spring for light passenger vehicles using life data analysis, *Materials science (Medžiagotyra)*, Vol.13, No.2, pp.(141-146), ISSN 1392-1320

- Shiva Shankar, G.S. & Vijayarangan, S. (2006). Mono composite leaf spring for light weight vehicle – design, end joint analysis and testing, *Materials science*, Vol.12, No.3, pp. (220-225), ISSN 1392-1320
- Springer, G.S. & Kollar, L.P. (2003). *Mechanics of composite structure*, Cambridge university press, ISBN 0-521-80165-6, New York
- Weibull, W. (1961). Fatigue testing and analysis of test results, *Pergamon press*, Paris
- Yu, W.J. & Kim, H.C. (1988). Double tapered FRP beam for automotive suspension leaf spring. *Composite structures*, Vol. 9, No.4, pp. (279- 300), ISSN 0263-8223
- Yasushi, M. (1997). Prediction of flexural fatigue strength of CFRP composites under arbitrary frequency, stress ratio and temperature, *Journal of composite material*, Vol. 31, pp. (619 - 638), ISSN 0021-9983
- (1980). *Manual on Design and Application of Leaf Springs*, HS - 788 (edition: 1), SAE International, ISBN 978-0-89883-383-6, New York

IntechOpen



Materials Science and Technology

Edited by Prof. Sabar Hutagalung

ISBN 978-953-51-0193-2

Hard cover, 324 pages

Publisher InTech

Published online 07, March, 2012

Published in print edition March, 2012

Materials are important to mankind because of the benefits that can be derived from the manipulation of their properties, for example electrical conductivity, dielectric constant, magnetization, optical transmittance, strength and toughness. Materials science is a broad field and can be considered to be an interdisciplinary area. Included within it are the studies of the structure and properties of any material, the creation of new types of materials, and the manipulation of a material's properties to suit the needs of a specific application. The contributors of the chapters in this book have various areas of expertise. therefore this book is interdisciplinary and is written for readers with backgrounds in physical science. The book consists of fourteen chapters that have been divided into four sections. Section one includes five chapters on advanced materials and processing. Section two includes two chapters on bio-materials which deal with the preparation and modification of new types of bio-materials. Section three consists of three chapters on nanomaterials, specifically the study of carbon nanotubes, nano-machining, and nanoparticles. Section four includes four chapters on optical materials.

How to reference

In order to correctly reference this scholarly work, feel free to copy and paste the following:

Senthilkumar Mouleeswaran (2012). Design, Manufacturing and Testing of Polymer Composite Multi-Leaf Spring for Light Passenger Automobiles - A Review, Materials Science and Technology, Prof. Sabar Hutagalung (Ed.), ISBN: 978-953-51-0193-2, InTech, Available from:
<http://www.intechopen.com/books/materials-science-and-technology/design-manufacturing-and-testing-of-polymer-composite-multi-leaf-spring-for-light-passenger-automobi>

INTech
open science | open minds

InTech Europe

University Campus STeP Ri
Slavka Krautzeka 83/A
51000 Rijeka, Croatia
Phone: +385 (51) 770 447
Fax: +385 (51) 686 166
www.intechopen.com

InTech China

Unit 405, Office Block, Hotel Equatorial Shanghai
No.65, Yan An Road (West), Shanghai, 200040, China
中国上海市延安西路65号上海国际贵都大饭店办公楼405单元
Phone: +86-21-62489820
Fax: +86-21-62489821

© 2012 The Author(s). Licensee IntechOpen. This is an open access article distributed under the terms of the [Creative Commons Attribution 3.0 License](https://creativecommons.org/licenses/by/3.0/), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

IntechOpen

IntechOpen