

# We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

6,900

Open access books available

185,000

International authors and editors

200M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index  
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?  
Contact [book.department@intechopen.com](mailto:book.department@intechopen.com)

Numbers displayed above are based on latest data collected.  
For more information visit [www.intechopen.com](http://www.intechopen.com)



---

# Kolsuz-Ulukisla-Nigde Clays, Central Anatolian Region – Turkey and Petroleum Exploration

---

Burhan Davarcioglu

Additional information is available at the end of the chapter

<http://dx.doi.org/10.5772/48286>

---

## 1. Introduction

Clays are naturally occurring, fine-grained minerals under surface conditions mostly as alteration products with distinct crystal structures. They may show plastic behavior when mixed with sufficient water and become stiff when dried or cooked. They, having different physical properties, occur in three modes: (I) surface clays that may be old or very young sedimentary formations, as suggested by the name, they occur near surface, (II) shales that have been subjected to pressures to become rigid and layered due to various reasons (e.g., tectonic or subsidence-related), and (III) fire clays that are mined out from deeper sites comparing to the other two and they behave refractory and include less impurities thus they are physically and chemically more uniform.

Some clay minerals having large surface area, high ion exchange capacity and molecular grid properties have been pioneered for the development of many new products (Falaras et al., 2000). Clay-organic complex structures have been a research subject particularly since 1930's. Results of these researches made beneficial contribution to the process of expanding their use in diverse areas (Smith, 1934). Besides, progresses in analytical techniques that made possible to determine mineralogical and chemical compositions of the clays appreciably expedited this process.


Clay minerals are formed as a result of changes in temperature, pressure, geochemical, and physical conditions (Murray, 1999). Although clay minerals could be resulted from weathering, sedimentation, burial, diagenesis and hydrothermal alteration processes in general, occurrence of monomineralic clay deposits is scant. Even in an ordinary clay sample, several clay species could occur together. Clay minerals can be categorized in 4 subgroups in natural environments: (I) kaolinite group, (II) smectite group, (III) illite group, and (IV) chlorite group (Murray, 1991).

The relationship between heat and pressure with the formation of clay minerals and its consequence on the formation of petroleum has been an imperative subject for research past 40 years (Perry and Hower, 1970; Dypvik, 1983). In the recent years one of the methods in the petroleum explorations is organic maturation and the other is clay mineral diagenesis. In both the clay mineral diagenesis and the organic maturation, clay minerals show structural changes with the changing temperature, which reveals the degree of metamorphism. The principal factors including pressure, temperature, depth and burial that are efficient during the conversion of the clay minerals and hydrocarbon formation and primary migration can be explained through clay mineral diagenesis and organic maturation (Dunoyer de Segonzag, 1970; Dypvik, 1983).

Clay mineral characterization could be carried out employing spectroscopic methods for various purposes in the geological sciences (Heroux et al., 1979). In the literature, there is a voluminous research on determination of clay mineral chemistry using diverse techniques. Today, one of the most preferred methods is the FTIR (Fourier Transform Infrared) Spectroscopy. There is a significant increase in number of studies using this method dealing with the clay characterization in Turkey (Akyuz and Akyuz, 2003; Davarcioglu et al., 2005; Davarcioglu and Kayali, 2007; Davarcioglu et al., 2007; Davarcioglu and Ciftci, 2009). One of such studies is on the quantitative and qualitative characterization of Central Anatolian clay deposits and diatomites by employing the spectroscopic methods (Kayali et al., 2005; Davarcioglu et al., 2008; Davarcioglu, 2009). The Central Anatolia is one of the richest in occurrence of clay deposits in the world. Therefore, investigation of these deposits, their quantitative and qualitative characterization is highly important.

In the XRD measurements, characteristic peak of glycol-saturated montmorillonite is  $17\text{ Å}^\circ$  peak (Cradwick and Wilson, 1972). As it disappears, mineralogical conversion of montmorillonite to illite becomes evident. As a consequence of chemical reactions depending on increasing depth and temperature, increase of Al and decrease of Si in montmorillonite's tetrahedral sheet results in changes in structure and by taking-up K ions available in the environment due to feldspar alteration, montmorillonite converts to illite (Weaver, 1960; Suchy et al., 2007). Expelled water as result of this change results in an increase in salinity of connate water already present in shale. Mg, Si and Ca ions, products of such conversion, could form minerals like calcite and dolomite facilitated by increasing temperature and these new minerals deposit within shale. This in turn results in a decrease in porosity and permeability and an increase in density (Bishop et al., 2002; Dunoyer de Segonzag, 1970).

Montmorillonite, being very sensitive clay mineral to temperature and depth, play an important role in both oil formation and its migration. As a result of reactions occurring in association with increasing temperature and depth, montmorillonite converts to illite losing its structural water (smectite converts to illite in alkaline environment). This conversion occurs at about 2500-4500 m burial depth and at  $100\text{ }^\circ\text{C}$ . In this process, K contents of pore waters show increase. Organic matter requires H ions to become hydrocarbon. H ions facilitate structural break-down (so-called cracking) of hydrocarbons with large organic molecules to smaller ones. During the loss of water from montmorillonite, H ion concentration

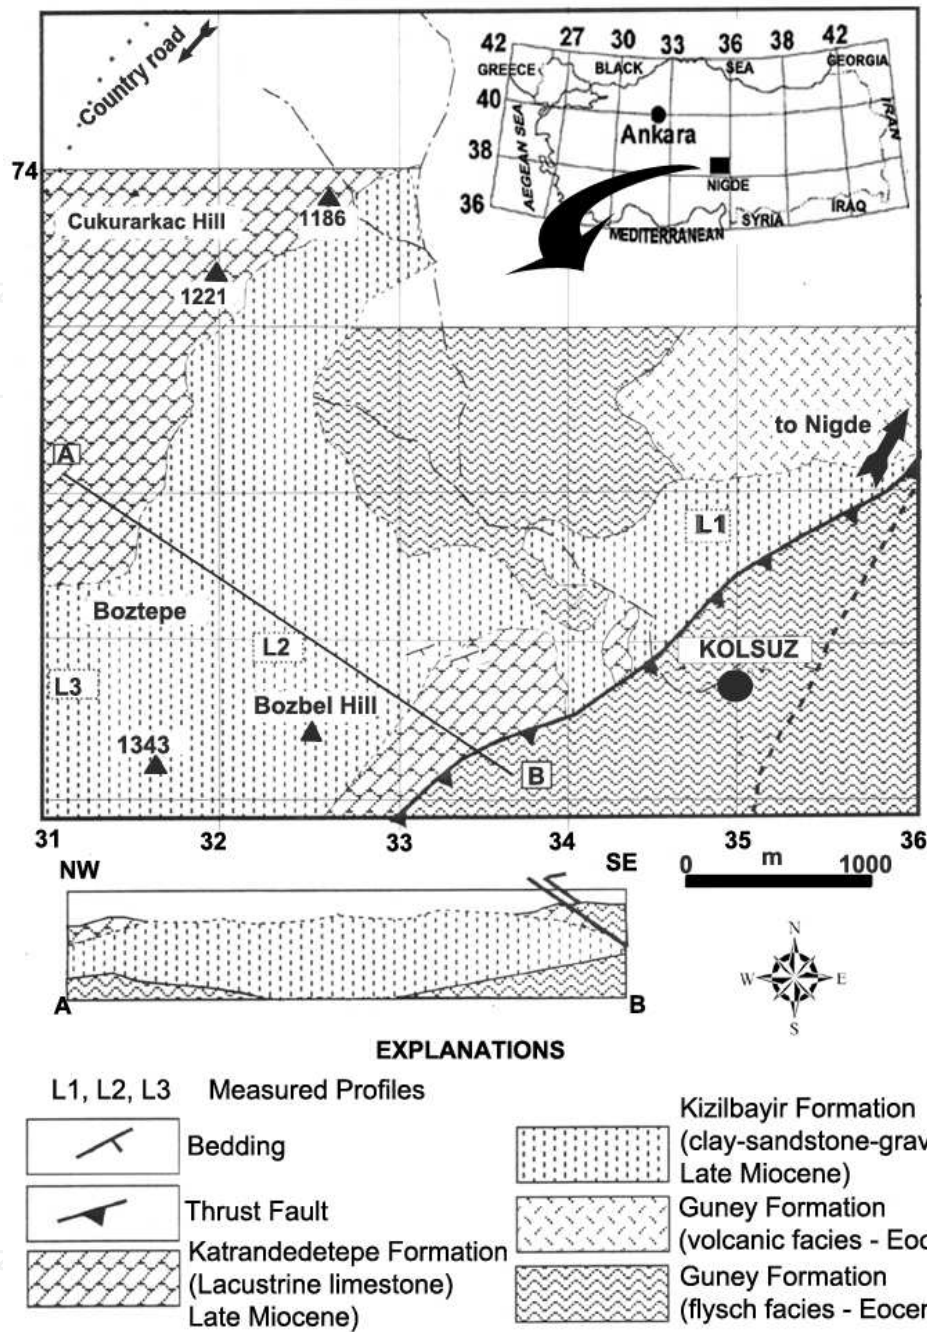

**Figure 1.** Generalized geological map of the Kolsuz-Ulukisla region and its around (adapted from Kayali et al., 2005).

of the environment raises. Water expulsion takes place at fairly steady and regular temperature. Some of the layers start losing water at 50-60 °C through 300 °C. About 70-80% of the water is expelled between 120-160 °C that corresponds to the formation of petroleum. This study suggests that results acquired from the organic maturation can be obtained through spectral analysis of structural changes occurring in clay minerals.

One of the geological studies in the Kolsuz area (Ulukisla-Nigde, Central Anatolian) deals with the clay profiles. In this study, using columnar sections and local observations,

distribution of clay horizons and their lithostratigraphic relations were investigated (Oktay, 1982). On the other hand, sedimentological, mineralogical and chemical properties of the clays of the same area were studied in depth later by Gurel (1999). The Kizilbayir Formation outcropping in the north of Ulukisla basin is the key formation due to its association with the clay occurrences. The formation starts with gravel-bearing red-green clays at the base, progressing upward, large-scale cross-bedded conglomerate, sandstone with clay intercalations occur and conglomerate with mudstone interbeds dominate towards the top (Demirtasli et al., 1986). Thickness of the formation in the area ranged from 10 to 250 m.

However, no comprehensive study on the qualitative and the quantitative characteristics of the clays occurring in this area was available to date. Thus, this study aims to investigate clays of the area using the spectroscopic method and observed structural changes in the clay structures were interpreted in terms of petroleum formation and their possible use in petroleum exploration in the area.

## **2. Experimental**

### **2.1. Preparation of samples**


A combined profile representing the constructed profiles chosen for this and nearby area was shown in Figure 1. The clay samples were taken from three different levels shown in the lithostratigraphic columnar section of a selected locality in the Kolsuz-Ulukisla region (Figure 2). The samples taken from lower level, middle level and upper level labeled as (Kk1), (Kk2), and (Kk3), respectively. Initially about 1 kg of samples were collected, and 20-40 g splits were prepared for further analyses. Samples were heated at 110 °C for 24 hours and crushed to powder and screened using an 80 mesh sieve. Clay fractions were prepared following the procedure including removal of carbonates, sulfates and organic matter by dissolving, through washing to acquire stable suspension, and siphoning (to acquire the clay fraction - <2 micron) (Brown, 1961; Gundogdu, 1982).

In general, the clay minerals contain significant amount of water. Conversely, they contain less alkaline and alkaline earth elements. Absorption bands due to the water molecules occupy large spectral fields, the ones critical for identification of clay minerals. Thus in order to minimize this undesired overlap, samples for the FTIR measurements were prepared through clay concentration without employing a centrifuge. However for the chemical analyses, samples were analyzed as bulk sample without concentrating for clay fraction. Organic matter was removed through boiling in H<sub>2</sub>O<sub>2</sub> solution and then samples were dried in an oven at 110 °C for 24 hours.

### **2.2. FTIR measurements**

Samples collected from the study area were prepared applying the disc technique (mixing ~1 mg clay sample with ~200 mg KBr) and put in molds. These intimate mixtures were then pressed at very high pressure (10 tons per cm<sup>2</sup>) to obtain the transparent discs, which were then placed in the sample compartment. Bruker Equinox 55 Fourier transform FTIR



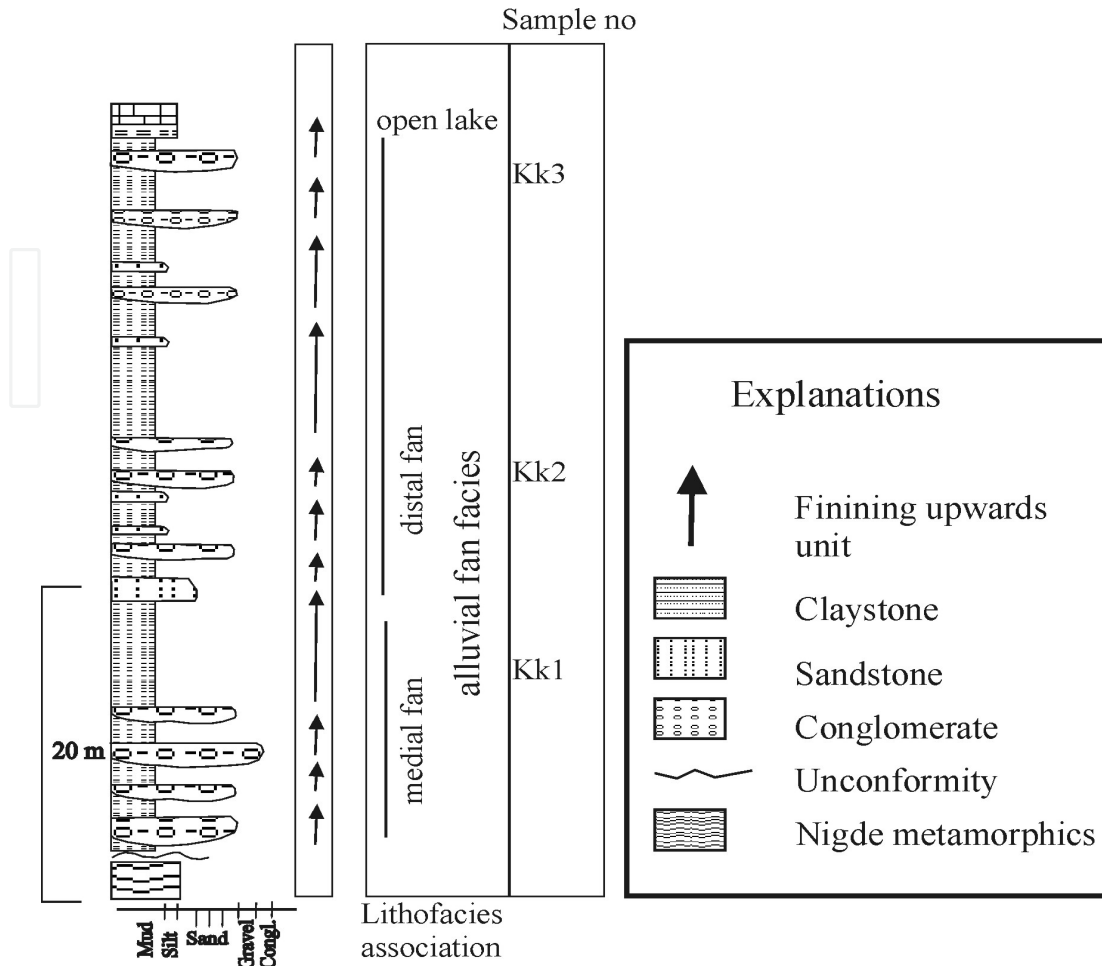

**Figure 2.** Generalized lithostratigraphic columnar section of the Kolsuz-Ulukisla region (adapted from Kayali et al., 2005).

spectrophotometer (Department of Physics, METU, Ankara-Turkey) was used for the IR spectral measurements of these samples with standard natural clay and the spectra were recorded over the range of  $5000\text{--}370\text{ cm}^{-1}$  (% transmission versus  $\text{cm}^{-1}$ ). Before taking the spectra measurements of the samples, spectrophotometer was calibrated with polystyrenes and silicate oxide of thickness 0.05 nm.

The infrared spectra of the illite (IMt-1; Silver Hill, Montana, USA), illite-smectite mixed layer (ISMt-1; Mancos Shale, Ord.), montmorillonite (SCa-3; Otay, San Diego Country California, USA), Ca-montmorillonite (STx; Gonzales Country, Texas, USA), Na-montmorillonite (SWy-1; Crook Country, Wyoming, USA), kaolinite (KGa-1; Washington Country, Georgia, USA), chlorite (ripidolite, CCa-1; Flagstaff Hill, El Dorato Country, California, USA), and palygorskite (PFI; Gadsden Country, Florida, USA) known as standard natural clay minerals ("The World Source Clay Minerals") were taken (Table 1), and then the spectra of anhydrite, gypsum, and mixtures of the illite+quartz+feldspar, quartz+feldspar have been taken for the analyses of subject samples.

Along with XRD (X-ray powder diffraction) analysis, the functional groups in the clay minerals structures could only be determined through the FTIR spectra. Therefore,

qualitative and quantitative analysis of the minerals by employing the FTIR spectroscopy is very important and promising.

Assignment	I	ISmML	Na-mont	C	P
Wavenumber (cm <sup>-1</sup> )					
v(OH) stretching	-	3685 (shoulder)	-	-	-
Inner-layer OH, (Al-O...H) stretching	-	-	3680	-	-
v(OH) stretching	-	-	-	3662	-
v(OH) stretching	-	-	3627 (shoulder)	-	3627
v(OH) stretching	3622	3622	3622	-	-
v(OH) stretching	-	-	-	3565	3546
v(OH) stretching	-	-	-	3434	-
δ(water-OH) stretching	-	-	-	-	3408, 3266
δ(water-OH) scissoring	-	-	-	-	1731
δ(water-OH) scissoring	-	-	-	-	1673, 1640
v(Si-O) stretching	-	-	-	-	1163, 1114
v(Si-O) normal to the plane stretching	1090	1090	-	-	-
v(Si-O) planar stretching	1031	1031	-	-	-
v(Si-O) stretching	-	-	-	-	1020
v(Si-O) stretching	-	-	-	988	-
(Al-Al-OH) deformation	916	916	920	-	-
OH deformation	-	-	-	-	905
(Al-Fe-OH) deformation	-	-	890	-	-
(Al-Mg-OH) deformation	832	810	875	-	-
M-OH stretching	-	-	805	819	-
Si-O deformation	-	-	-	766	-
(Al-O-Si) inner surface vibration	756	-	-	-	-
(Al-O-Si) inner layer vibration	-	750	-	-	-
OH deformation	688, 622	622	620	667	-
(Si-O-Al) deformation	-	-	-	543	-
(O-Si-O) bending	525	525	520	-	528
(O-Si-O) bending	468	468	468	-	469
(Si-O-Mg) deformation	-	-	-	441	-
(O-Si-O) bending	-	-	-	-	426

**Table 1.** Fundamental vibration frequencies of standard natural clays (I=illite, ISmML=illite-smectite mixed layer, Na-mont=Na-montmorillonite, C=chlorite, P=palygorskite).

A second treatment was employed only to the clay sample taken from the lower level (Kk1) to see whether there is a change in the structure of the samples or not due to FTIR spectrum measurements. For this procedure, HCl, bicarbonate (Na<sub>2</sub>CO<sub>3</sub>), and sodiumdithonit (Na<sub>2</sub>S<sub>2</sub>O<sub>4</sub>), and sodiumstrate (Na<sub>3</sub>C<sub>6</sub>H<sub>5</sub>O<sub>7</sub>) liquids were added to the sample to remove carbonates (mainly calcite and dolomite), amorphous materials and manganese oxides, which were expected to be present. This mixture was treated in an oven at 120 °C for 24 hours and washed using ethyl alcohol until complete removal of those unwanted components was achieved. The FTIR spectrum of the precipitate was then taken.

### 3. Chemical and minerological analyses


The chemical analyses of the Kolsuz-Ulukisla clay samples (dried in an oven at 110 °C for 24 hours) were carried out at the ACME-Canada laboratories by means of XRF-ICP (X-ray fluorescence spectrometry-Inductively Coupled Plasma) technique. Major oxide composition of the samples representing the lower, middle and upper parts of the profile was given in Table 2. These data suggest that the clays of the region are essentially rich in

SiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub>, and CaO. Main cause of these enrichments was due to ascending briny and carbonated waters through capillary actions and precipitation due to transpiration in arid and semi-arid regions. On the other hand, aluminum enrichment could be due to presence of either other aluminum silicates (such as K-feldspars) or Al<sup>3+</sup> being in the clay structures.

	Lower part (Kk1)	Middle part (Kk2)	Upper part (Kk3)
SiO <sub>2</sub>	46.50	48.57	49.12
TiO <sub>2</sub>	0.66	0.76	0.47
Al <sub>2</sub> O <sub>3</sub>	12.74	13.97	9.46
Fe <sub>2</sub> O <sub>3</sub>	7.28	8.10	4.24
MnO	0.14	0.14	0.15
MgO	4.68	5.09	2.90
CaO	9.37	6.94	15.04
Na <sub>2</sub> O	0.96	1.10	1.72
K <sub>2</sub> O	2.31	2.64	1.65
Cr <sub>2</sub> O <sub>3</sub>	0.028	0.027	0.029
P <sub>2</sub> O <sub>5</sub>	0.06	0.15	0.10


**Table 2.** Major oxide composition of the studied profile (in %).

XRD measurements were employed to determine the mineral phases included in the same samples (Siemens D-5000 Diffract AT V 3.1 diffractometer, CuK $\alpha$  radiation  $\lambda=1.54056$  Å and 0.03 steps; General Directorate of Mineral Research and Exploration laboratories-MTA, Ankara-Turkey). According to the XRD measurements (Figures 3 and 4), subject clays are found to be composed of abundant chlorite (45%), illite (32%), quartz (20%), smectite (3%), feldspar, calcite, and trace quantities of palygorskite and Fe-oxide minerals. In the Kk1 lower part of the clay profile (Figure 2), amount of quartz tend to decrease while smectite, illite and chlorite show significant increase. Whereas at the top of the Kk1, just opposite of this abundance trend was observed and palygorskite was totally absent.

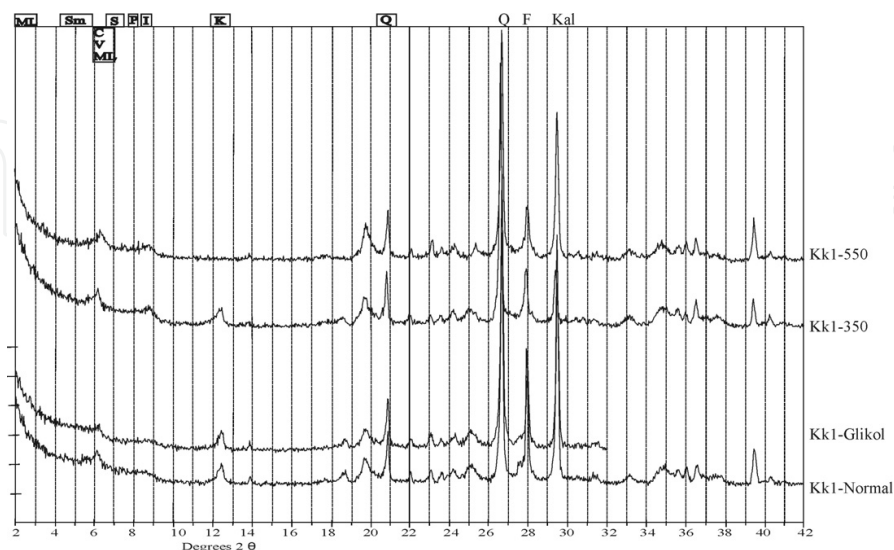


**Figure 3.** XRD pattern of the clay samples belonging to the lower level (Kk1) of Kolsuz-Ulukisla clays (Q=quartz, F=feldspar, I=illite, ML=mixed layer clay, C=chlorite, S=smectite).



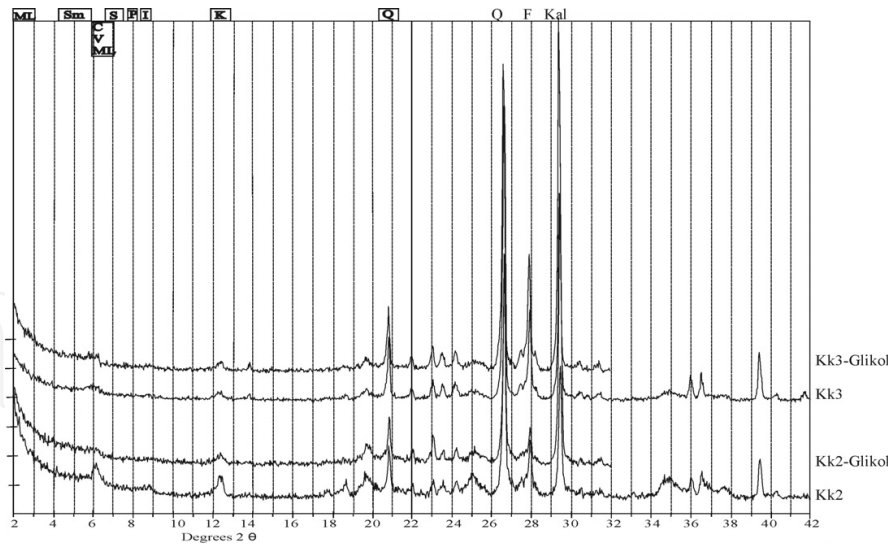

**Figure 4.** XRD patterns of the clay samples from the lower level (Kk2) and the upper level (Kk3) of Kolsuz-Ulukisla clays (Q=quartz, F=feldspar, I=illite, ML=mixed layer clay, C=chlorite, S=smectite).

DTA (Differential Thermal Analysis) and TGA (Thermogravimetric Analysis) measurements have been carried out for the determinations of the thermal behaviour of the clay samples (Figure 5). Measurements were carried out in the MTA Labs (Ankara-Turkey) using a Rigaku Thermal Analyzer Ver. 2.22EZ (SN#39421). Here smectite peak falls in the same field with the one of chlorite. Minute endothermic peak of smectite occurs in between  $\sim 100$ - $250$   $^{\circ}\text{C}$ , and second endothermic peak appears at  $\sim 700$   $^{\circ}\text{C}$  and shallow endothermic/exothermic peak is observed at  $\sim 800$ - $900$   $^{\circ}\text{C}$ . Best observed endothermic peak of chlorite in the DTA-grams is the one observed between  $500$ - $600$   $^{\circ}\text{C}$ . This peak may shift toward  $\sim 700$   $^{\circ}\text{C}$  due to the iron content. Subsequently this peak may fall in the same interval with smectite's peak at  $\sim 700$   $^{\circ}\text{C}$ . Chlorite's exothermic peak occurs at  $750$   $^{\circ}\text{C}$  (Kok, 2006; Kok and Smykatz-Kloss, 2009; Yener et al., 2007).

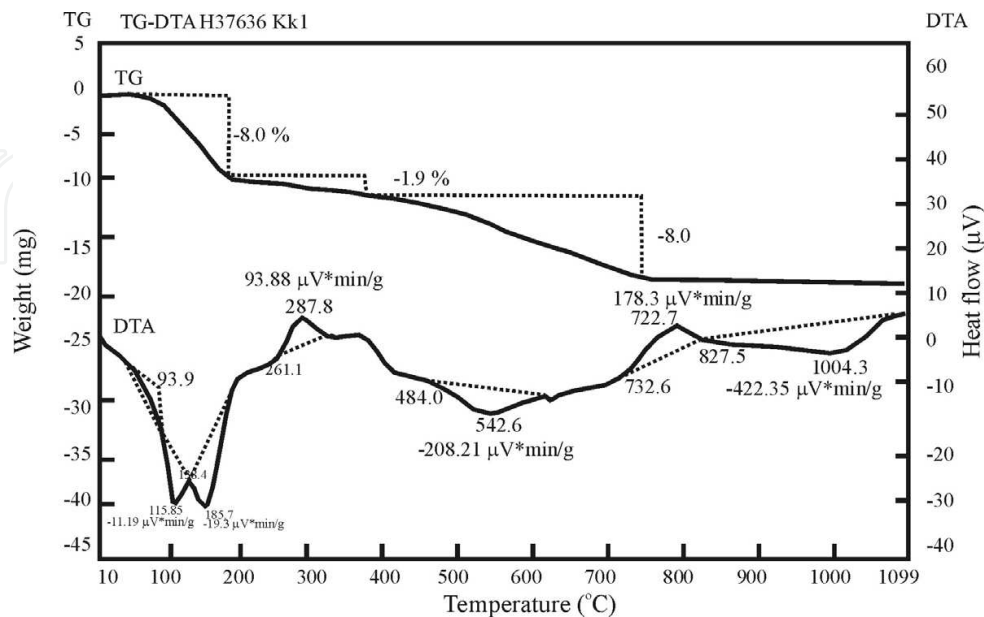

**Figure 5.** DTA-TGA measurements of the Kolsuz-Ulukisla clays.


#### 4. Petroleum formation

In the recent years, one of the methods used in petroleum explorations is organic maturation and the other diagenesis of clay minerals. Results acquired through the first approach could be attained using the second method. Fundamental nature of the second approach can be explained as follow: clays that immature or recently deposited may contain smectite (montmorillonite), illite and kaolinite depending on the source area. With subsidence, these minerals lose their water content and are subjected to mineralogical transformations. Smectite converts to illite within the range of oil formation temperature (60-150 °C) (Weaver, 1960; Dunoyer de Segonzag, 1970). When the upper limit of this range was approached, kaolinite and illite convert to mica, if ferromagnesian minerals are available in the environment; these minerals transform to chlorite instead (Figure 6). Consequently, clays can give an idea about the degree of maturation of a sample of interest. For the fields where oil explorations are carried out, clays can be used to answer following questions: (I) which layers has source rock potential, their regional coverage and relationship with the paleogeography, (II) source rocks occurring what part and depth of the basin and which time interval have enough maturation, (III) when and how the oil migration occurred, (IV) the relationship with oil formation and oil migration (Hunt, 1995). However, time and duration plays an important role in this process accompanying the mineralogical transformations.

Mineralogical changes of the clay minerals are closely related to the temperature and water chemistry of the environment. Thus, they reflect better and more precise transformation temperature (paleotemperature) of the clay minerals. Reflectance degree of vitrinite, a major organic component of coals, shows increase with increasing degree of metamorphism (Teichmuller, 1987). In diagenesis stage, reflectance degree of vitrinite is 5%. In this stage, organic matter is not mature enough to produce oil and the second stage is catagenesis (boundary is 2%). While oil formation takes place between 0.7% and 1.3%, wet gas occurs between 1.3% and 2%. Lower boundary of metagenesis is 4%, under which metamorphism starts (Bozkaya and Yalcin, 1996).

During diagenesis and metamorphism, mineralogical changes occurring in the clay structures give extent of such events of the sedimentary rocks. Structural characteristics and parameters of the clay minerals are not unique for all depositional environments. However, depositional environments are characteristic to formation of certain clay minerals. Major parameters of sedimentary environment including pressure, temperature, subsidence, time, proton-electron concentration and metal-ion concentration greatly affect the clay mineral structures (Bozkaya and Yalcin, 1996). Most of the petroleum source rocks contain various clay minerals. Source rock properties like porosity and permeability vary depending on variety, abundance and distribution of the clay minerals (Bayar et al., 1987).

In the study area, the Kolsuz clays are loosely cemented with calcite, silica and Fe-oxides. Gravels are of various origins including sandstone, greywacke, claystone, limestone, marl, volcanics, granodiorite, gabbro, quartzite, chert, and serpentinite (Kayali et al., 2005). Petrographic investigations on thin-sections of 12 samples from the Kizilbayir Formation

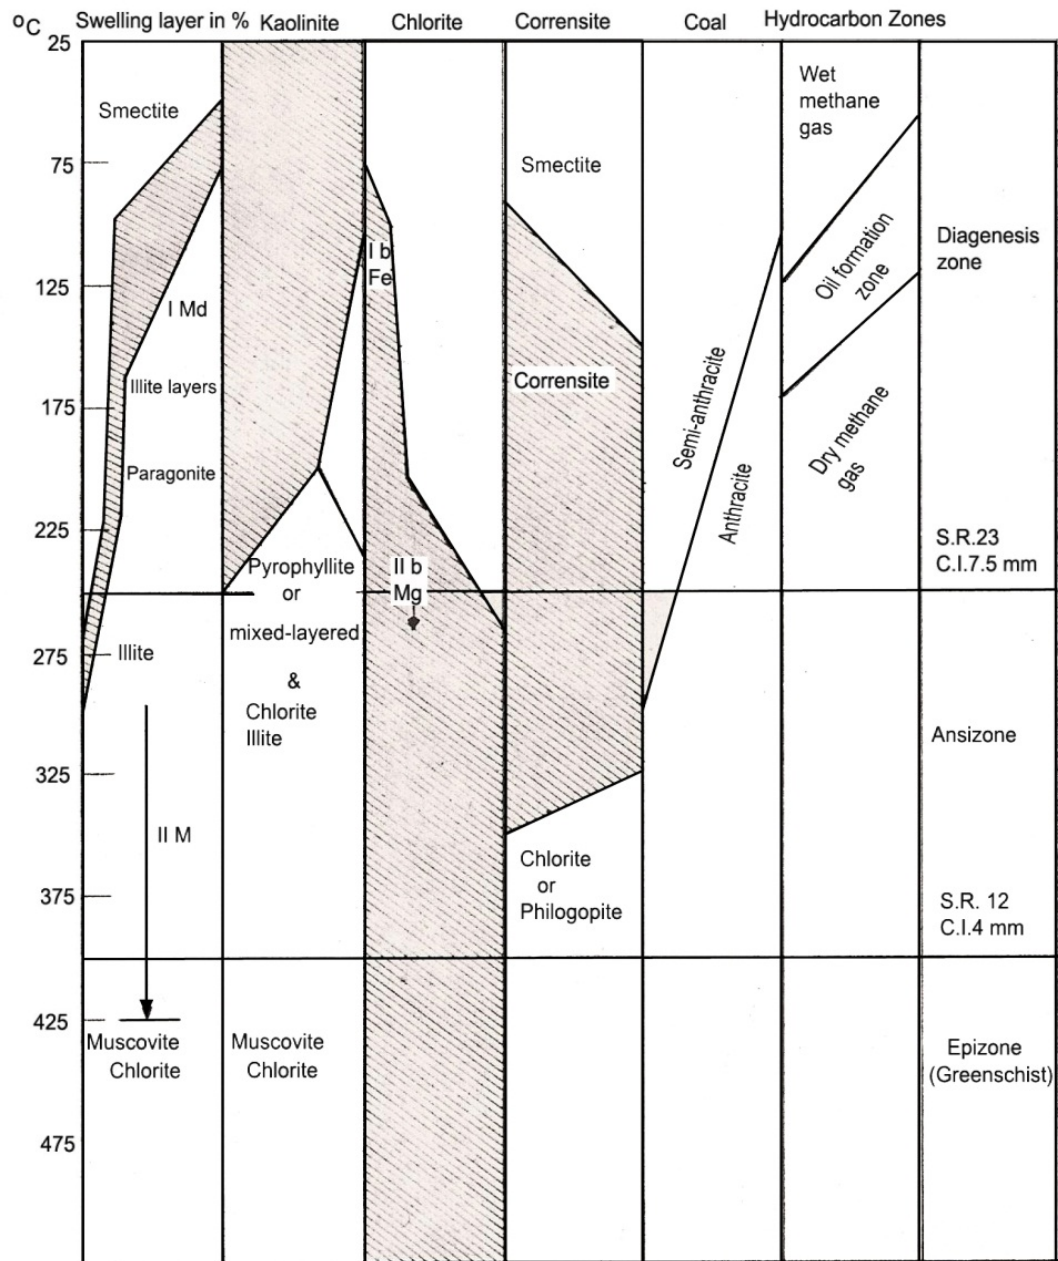


**Figure 6.** Diagenesis of clay minerals and oil formation zones in terms of temperature (adapted Weaver, 1960; Suchy et al., 2007).

indicated prevalent presence of feldspars, quartz, calcite, lithic fragments of volcanic, magmatic and metamorphic rocks, of carbonates (e.g., limestone and marl) and clastic sedimentary rocks (e.g., sandstone, claystone and greywacke) cemented chiefly by calcium carbonate (Gurel 1999; Kayali et al., 2005).


## 5. Results and discussions

The clay samples were taken from three different levels shown in the lithostratigraphic columnar section of a selected locality in the Kolsuz-Ulukisla region (Figure 2). The FTIR

spectra of the samples taken from lower level (Kk1), middle level (Kk2), and upper level (Kk3) of Kolsuz-Ulukisla (Turkey) clay profile are given in Figures 7 through 9, respectively. Interpretation of the observed vibrational bands in these samples were carried out by comparing with those found in the world clay standards with known fundamental vibration frequencies for illite, illite-smectite mixed layer, Na-montmorillonite, chlorite (ripidolite), palygorskite (Table 1) and the other clay standards. Results are listed in Table 3.

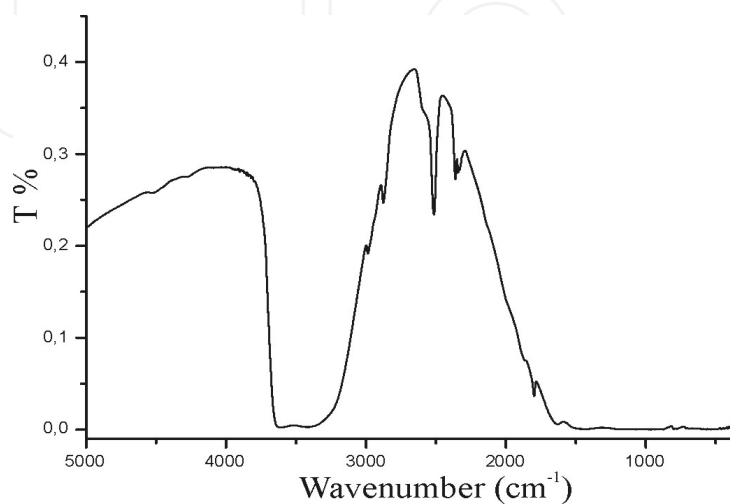


**Figure 7.** FTIR spectrum of the clay sample taken from the lower level (Kk1) of Kolsuz-Ulukisla.

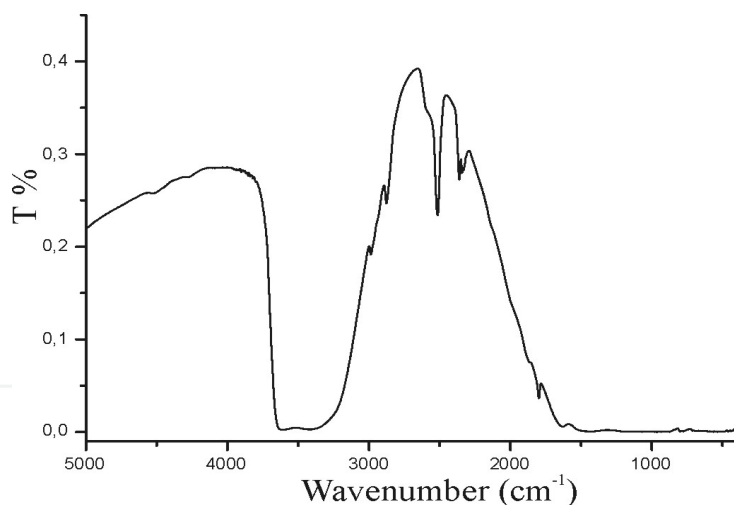

**Figure 8.** FTIR spectrum of the clay sample taken from the middle level (Kk2) of Kolsuz-Ulukisla.

As seen from Table 3, all of the samples belonging to the lower, middle, and upper levels of Kolsuz-Ulukisla (Turkey) clay profiles Kk1, Kk2, and Kk3, respectively, include illite, illite-smectite mixed layer, Na-montmorillonite, chlorite, palygorskite, calcite, feldspar and quartz minerals.

The FTIR spectrum of the sample representing (as summarized in FTIR measurements) lower level (Kk1) of Kolsuz-Ulukisla profile has been taken to see effects of the heat treatments on the structure of the subject samples (Figure 10). The assignments of the vibration frequencies of this spectrum were carried out following the same procedure

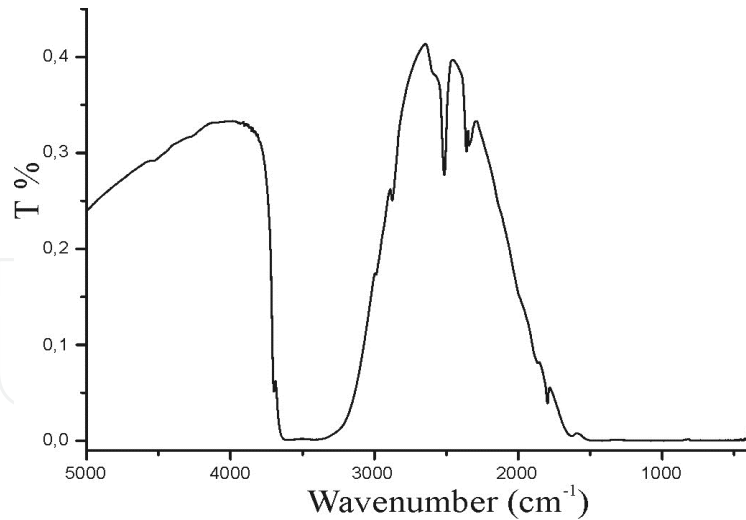


**Figure 9.** FTIR spectrum of the clay sample taken from the upper level (Kk3) of Kolsuz-Ulukisla.

Assignment	Kk1	Kk2	Kk3	Mineral
	Wavenumber (cm <sup>-1</sup> )			
v(OH) stretching "shoulder"	-	-	3680	Illite
Inner-layer OH, (Al-O...H) stretching	-	-	3680	Na-Montmorillonite
v(OH) stretching	-	-	3660	Chlorite
v(OH) stretching	3622	3622	3622	Illite/Na-Montmorillonite
v(OH) stretching	2515	2515	2515	Calcite
δ(water-OH) scissoring	1731	1731	1731	Palygorskite
δ(water-OH) scissoring	1673	1673	1673	Palygorskite
v(Si-O) normal to the plane stretching	1090	1090	1090	Illite-smectite mixed layer
v(Si-O) planar stretching	1031	1031	1031	Illite-smectite mixed layer
v(Si-O) stretching	988	988	988	Chlorite
(Al-Al-OH) deformation	920	920	917	Na-Montmorillonite
OH deformation	905	905	905	Palygorskite
M-OH stretching	819	819	817	Chlorite
M-OH leaning	805	805	805	Na-Montmorillonite
v(OH) stretching	798	798	798	Quartz/Amorphous Silica/Feldspar
v(OH) stretching	788	788	788	Quartz
v(OH) stretching	697	697	697	Quartz
OH deformation	620	620	620	Na-Montmorillonite
(Si-O-Al) deformation	543	543	543	Chlorite
(O-Si-O) bending	520	520	520	Na-Montmorillonite
(O-Si-O) bending	468	468	468	Na-Montmorillonite/Palygorskite/Illite
(Si-O-Mg) deformation	441	441	441	Chlorite

**Table 3.** FTIR spectrum analysis results of Kolsuz-Ulukisla clay samples Kk1, Kk2, and Kk3 belonging to lower, middle, and upper levels, respectively.

applied to the spectra of the other samples and the results are given in Table 4. When results listed in Table 4 interpreted with the one in Table 3, it can be seen that the sample, Kk1, is composed of illite, calcite, chlorite, feldspar and quartz. Band assigned as vibrational frequencies for Na-montmorillonite and palygorskite were not observed after the thermal treatment. However, for illite at 916 and 833 cm<sup>-1</sup> (Al-Mg-OH) deformation and at 525 and 470 cm<sup>-1</sup> (O-Si-O) bending frequency bands were observed after the thermal treatment. This bands are resulted due to re-arrangement of Al and Mg atoms within the crystal structure during the thermal treatment (Bishop et al., 2002).



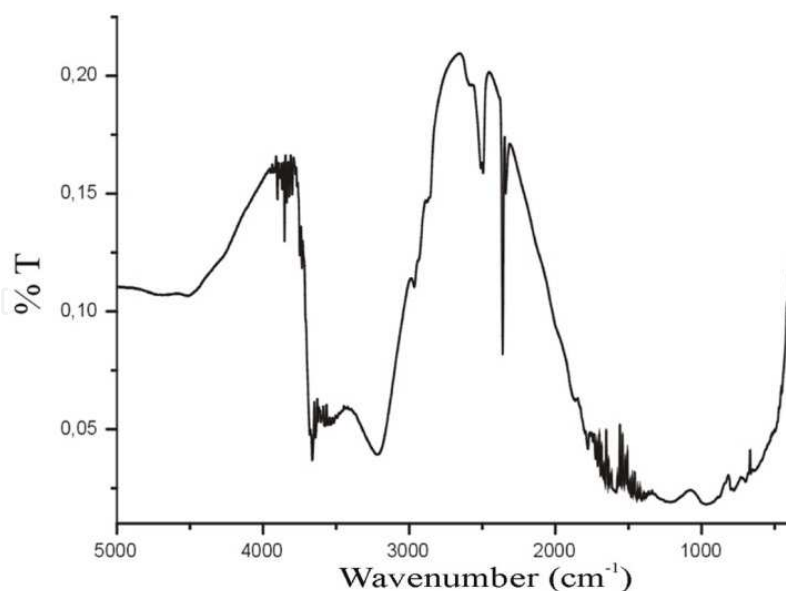

**Figure 10.** FTIR spectrum of the clay sample Kk1 after thermal treatment.

Assignment	Kk1	
	Wavenumber (cm <sup>-1</sup> )	Mineral
v(OH) stretching "shoulder"	3680	Illite
v(OH) stretching	3662	Chlorite
v(OH) stretching	3622	Illite
v(OH) stretching	3566	Chlorite
v(OH) stretching	3435	Chlorite
v(OH) stretching	2515	Calcite
v(Si-O) normal to the plane stretching	1090	Illite
v(Si-O) planar stretching	1031	Illite
(Al-Al-OH) deformation	916	Illite
(Al-Mg-OH) deformation	833	Illite
M-OH stretching	817	Chlorite
v(OH) stretching	798	Quartz//Feldspar
v(OH) stretching	788	Quartz
v(OH) stretching	697	Quartz
(Si-O-Al) deformation	543	Chlorite
(O-Si-O) bending	525	Illite
(O-Si-O) bending	470	Illite
(Si-O-Mg) deformation	443	Chlorite

**Table 4.** Results of the FTIR spectrum analyses of the clay sample (Kk1) from Kolsuz-Ulukisla (Turkey) after thermal treatment.

Only v(Si-O) stretching at 988 cm<sup>-1</sup> among the vibrational frequencies of chlorite at 3660, 988, 819, 543, and 441 cm<sup>-1</sup> was not observed after the thermal treatment. This is because that the organic molecules are forced into silicate layers during the thermal treatment. XRD data acquired from preheated sample (Kk1) between 350-550 °C, indicated that chlorite and illite peaks were not shifted but smectite peak was shifted towards 10 Å. In the same sample, kaolinite should also be present, because the 7 Å peak disappears at 550 °C. Based on FTIR and XRD (even at slow scan) measurements, kaolinite was never observed. Thus we conclude that Kk1 does not include any kaolinite. The v(OH) stretching vibrations of quartz at 798, 788 and 697 cm<sup>-1</sup> and v(OH) stretching vibration of calcite at 2515 cm<sup>-1</sup> remain the same after the heat treatment. As a result from FTIR analysis, we can say that the framework

of silicate (T-O-T) structures of Kolsuz-Ulukisla-Nigde (Turkey) clay minerals samples has not been destroyed.

Before the thermal treatment, in Kk1 and Kk3 samples, palygorskite's only bands including  $\delta(\text{water-OH})$  scissoring vibrational bands at 1731 and 1673  $\text{cm}^{-1}$  (Frost et al., 2001), OH deformation bands at 905  $\text{cm}^{-1}$  and (O-Si-O) bending vibration band at 468  $\text{cm}^{-1}$  were observed. While illite's  $\nu(\text{OH})$  stretching vibrational band appears as shoulder at 3680  $\text{cm}^{-1}$  in Kk3 clay samples, despite (O-Si-O) bending vibration band at 468  $\text{cm}^{-1}$  observed in Kk1 and Kk3 samples was assigned as belonged to palygorskite, it could belong to Na-montmorillonite's (O-Si-O) bending vibration band. Similarly, vibration band observed at 3680  $\text{cm}^{-1}$  in Kk3 sample was assigned as  $\nu(\text{OH})$  stretching vibration band, it belongs to inner-layer OH, (Al-O...H) stretching band (Farmer and Russell, 1964). In samples Kk1 and Kk3, when bands assigned at 3622, 920, 805, 620, and 468  $\text{cm}^{-1}$  were evaluated altogether; they appear well-matched with fundamental vibration bands of Na-montmorillonite standard. But vibration band at 920  $\text{cm}^{-1}$  of the Na-montmorillonite standard clay was observed at 917  $\text{cm}^{-1}$  in Kk3 sample.

## 6. Conclusions

1. Clay minerals of selected profiles in Nigde-Ulukisla area were determined both by the XRD and the FTIR.
2. Structural evaluation of these clay varieties was carried using the FTIR spectra.
3. Structural changes could be determined efficiently by the FTIR.
4. Findings are evaluated with the known data for depth-temperature-clay mineral transformations during burial processes in sedimentary basins.
5. Study area has potential to produce hydrocarbons as indicated by the presence of certain clay species.

## Author details

Burhan Davarcioglu

*Department of Physics, Faculty of Arts and Sciences, Aksaray University, Aksaray, Turkey*

## Acknowledgement

We would like to thank Turkish Scientific and Technological Research Council (TUBITAK-Turkey) for the financial support (project code: CAYDAG 2005-101Y067). Professor Dr. Cigdem Ercelebi (Department of Physics, Middle East Technical University, Turkey) is also gratefully appreciated for the FTIR.

## 7. References

- Akyuz S, Akyuz T (2003). FT-IR spectroscopic investigation of adsorption of pyrimidine on sepiolite and montmorillonite from Anatolia. *Journal of Inclusion Phenomena and Macrocylic Chemistry*. 46(1): 51-55.

- Bayar M, Turkay E, Gumrah, F (1987). Formation of clay with water injection in increasing oil production to investigate the effects of experimental. Proceedings of 3rd National Clay Symposium. Turkmenoglu and Akiman (ed.), September 21-27, 287-299, Ankara, Turkey.
- Bishop J, Madejova P, Komadel P, Froschl H (2002). The influence of structural Fe, Al and Mg on the infrared OH bands in spectra of dioctahedral smectites. *Clay Minerals*. 37(4): 607-616.
- Bozkaya O, Yalcin H (1996). Diagenesis-Metamorphic transition the methods used to determine. *Journal of Engineering Geology-Turkey*. 49: 1-22.
- Brown G (1961). The X-ray Identification and Crystal Structures of Clay Minerals. Mineralogical Society (Clay Minerals Group), London, pp. 543.
- Cradwick PD, Wilson, MJ (1972). Calculated X-ray diffraction profiles for interstratified kaolinite-montmorillonite. *Clay Minerals*. 9(5):395-405.
- Davarcioğlu B, Gurel A, Kayali, R (2005). Investigation of Central Anatolia region Nigde-Dikilitas (Turkey) clays by FT-IR spectroscopy. Proceedings of 12th National Clay Symposium. Yakupoglu, Aclan and Kose (ed.), September 5-9, 63-72, Van, Turkey.
- Davarcioğlu B, Kayali R (2007). Investigation of Central Anatolia Aksaray-Guzelyurt region kaolinitic clays by FT-IR spectroscopy. *Journal of Faculty Engineering-Architecture Selcuk University*. 22(1-2): 49-58.
- Davarcioğlu B, Gurel A, Kayali R (2007). Investigation of Eastern Black Sea Rize-Findikli-Camlihemsin region clays by FTIR spectroscopy. 6th International Industrial Minerals Symposium. Kemal, Batar, Kaya and Seyrenkaya (ed.), February 1-3, 87-95, Izmir, Turkey.
- Davarcioğlu B, Kayali R, Gurel A (2008). FT-IR spectroscopic study of Arapli-Yesilhisar-Kayseri clays from Central Anatolia region. *Journal of Clay Science and Technology*. 1(3): 163-173.
- Davarcioğlu B, Ciftci E (2009). Investigation of Central Anatolian clays by FTIR spectroscopy (Arapli-Yesilhisar-Kayseri, Turkey). *International Journal of Natural and Engineering Sciences*. 3(3): 154-161.
- Davarcioğlu B (2009). Investigation of eastern black sea region clays by FTIR spectroscopy (Rize-Findikli-Camlihemsin, Turkey). *Colloquium Spectroscopium Internationale XXXVI*. August 30-September 3, Book of Abstract, 74, Budapest, Hungary.
- Demirtasli E, Bilgin AZ, Erenler F, Isiklar S, Sanli DY, Selim M (1986). The general geology of the basin with the Eregli-Ulukisla Bolcardaglari. Report of MTA-Turkey. No: 8097, pp. 54.
- Dunoyer de Segonzac G (1970). The transformation of clay minerals during diagenesis and low-grade metamorphism: a review. *Sedimentology*. 15(1-2): 281-346.
- Dypvik H (1983). Clay mineral transformations in Tertiary and Mesozoic sediments from North Sea. *American Association of Petroleum Geologists Bulletin*. 67(1): 160-165.
- Falaras P, Lezou F, Seiragakis G, Petrakis D (2000). Bleaching properties of alumina-pillared acid-activated montmorillonite. *Clays and Clay Minerals*. 48(5): 549-556.
- Farmer VC, Russell JD (1964). The infrared spectra of layer silicates. *Spectrochimica Acta*. 20(7): 1149-1173.

- Frost RL, Locos OB, Ruan H, Klopogge JT (2001). Near-infrared and mid-infrared spectroscopic study of sepiolites and palygorskites. *Vibrational Spectroscopy*. 27(1-2): 1-13.
- Gundogdu MN (1982). Investigation of Geological, Mineralogical and Geochemical of Bigadic Cretaceous Sedimentary Neogene. PhD Thesis, Hacettepe University (Turkey), pp. 386.
- Gurel A (1999). Determination of sedimentological, mineralogical and chemical properties of Ulukisla-Kolsuz area (Nigde-Turkey). *Proceedings of 9th National Clay Symposium*. Yenyol, Ongen and Ustaomer (ed.), September 15-18, Istanbul, Turkey.
- Heroux Y, Chagnon A, Bertrand R (1979). Compilation and correlation of major thermal maturation indicators. *American Association of Petroleum Geologists Bulletin*. 63(12): 2128-2144.
- Hunt JM (1995). *Petroleum geochemistry and geology*. W.H. Freeman and Company, New York, pp. 745.
- Kayali R, Gurel A, Davarcioglu B, Ciftci E (2005). Determination of qualitative and quantitative properties of industrial raw materials clays and diatomites in Central Anatolia by spectroscopic methods. TUBITAK-Turkey (project code: YDABCAG-1001Y067), pp. 137.
- Kok MV (2006). Effect of clay on crude oil combustion by thermal analysis techniques. *Journal of Thermal Analysis and Calorimetry*. 84(2): 361-366.
- Kok MV, Smykatz-Kloss W (2008). Characterization, correlation and kinetics of dolomite samples as outlined by thermal methods. *Journal of Thermal Analysis and Calorimetry*. 91(2): 565-568.
- Murray HH (1991) Overview-clay mineral applications. *Applied Clay Science*. 5(5-6): 379-395.
- Murray HH (1999). Applied clay mineralogy today and tomorrow. *Clay Minerals*. 34(1): 39-49.
- Oktay FY (1982). Stratigraphy and geological evolution of Ulukisla and its surroundings. *Geological Bulletin of Turkey*. 25(1): 15-24.
- Perry G, Hower J (1970). Burial diagenesis in Gulf Coast pelitic sediments. *Clays and Clay Minerals*. 18(3): 165-177.
- Smith CR (1934). Base exchange reactions of bentonite and salts of organic bases. *Journal of the American Chemical Society*. 56: 1561-1563.
- Suchy V, Sykorova I, Melka K, Filip J, Machovic V (2007). Illite 'crystallinity', maturation of organic matter and microstructural development associated with lowest-grade metamorphism of Neoproterozoic sediments in the Tepla-Barrandian unit, Czech Republic. *Clay Minerals*. 42(4): 503-526.
- Teichmuller M (1987). Organic material and very low-grade metamorphism. In *Low Temperature Metamorphism*. Frey M (ed.), Blackie, Glasgow and London, pp. 161.
- Weaver CE (1960). Possible uses of clay minerals in search for oil. *Bulletin of American Association of Petroleum Geologists*. 44(9): 1505-1518.
- Wilson MJ (1987). *A Handbook of Determinative Methods in Clay Mineralogy*. Blackie-Son Ltd., London, pp. 308.
- Yener N, Onal M, Ustunisik G, Sarikaya Y (2007). Thermal behavior of a mineral mixture of sepiolite and dolomite. *Journal of Thermal Analysis and Calorimetry*. 88(3): 813-817.