

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

6,900

Open access books available

185,000

International authors and editors

200M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.
For more information visit www.intechopen.com



Elimination of Phenols on a Porous Material

Bachir Meghzili^{1,2}, Medjram Mohamed Salah¹,
Boussaa Zehou El-Fala Mohamed¹ and Michel Soulard³

¹Laboratoire LARMACS, Université de Skikda Algérie,

²Université de Biskra,

³Equipe Matériaux à Porosité Contrôlée, IS2M, LRC CNRS 7228, UHA, ENSCMu, France

1. Introduction

The surface water which feeds the majority of the stations of treatment of drinking water is charged by organic composed, including one great part makes up of humic substances. It is thus important to eliminate them to avoid the formation of generally toxic organohalogen compounds (Dore, 1989; Meier, 1988; Boudhar, 1999). The coagulation and the flocculation followed by a clarification remain the most frequent treatment to withdraw colloids present in water, which they are of organic or mineral origin (Bersillon, 1983; Lefebvre and Legube, 1990).

Conventional treatment of the clarification which could indeed eliminate these macromolecules from the humic type is not always sufficient; it often requires optimal conditions not very compatible with the practical conditions of operation and of the treatment as with the criteria of potability. Processes based on adsorption often constitute a technique of choice, complementary to treatment basic. The adsorption is one of the processes of the separation which finds its application in several fields, such as extraction, purification and depollution.

Among the most recent progress in the water treatment, the advanced processes of oxidation (advanced oxidation process AOP) considered to be effective, allow mineralization in aqueous medium of the toxic organic molecules with respect to the man and of the environment. The advanced processes of oxidation are based on the generation and the use of a very strong oxidant which is the radical hydroxyl. This last can be produced by various processes chemical, photochemical biological, electrochemical (Andreozzi and Al, 1999; Chiron and Al, 2000; Galze and Al, 1992; Safarzadeh-Amiri and Al, 1996; Dussert, 1997). These methods rest on the formation of very reactive chemical entities which will biologically break up the most recalcitrant molecules into molecules degradable or in mineral compounds (Golic and Bahnemann, 1997). The reactions generally studied on this level can be classified in three categories (Hoang, 2009):

- Reactions with the reagents électrophiles (O_3 , HOCl, ClO_2 and NH_2Cl),
- Reactions with the radicalizing species and initiating reactions of production of radicals (HO and inorganic radicals: $CO_3^{\cdot-}$, $SO_4^{\cdot-}$, $Cl_2^{\cdot-}$, catalyse homogeneous by Fe^{II} and Fe^{III} , radiolysis of water, photocatalysis, catalytic ozonization etc...)
- Reactions of phototransformation (UV and solar) with or without catalyst.

In Algeria, organic material can represent, with it only, a big part of the organic load of surface waters, in particular in the case of water of stopping. The presence of natural organic matter in a surface water east at the origin of many problems encountered during the various stages of treatment of potabilisation. Initially, the natural organic matter is undesirable because it reacts with chlorine during disinfection to form volatile organic compounds (trihalométhanes [THM], acid dichloroacetic [DCAA], etc), produced potentially carcinogenic (Lefebvre and Legube 1990; Hooper and Al, 1996; Stevens and Al, 1976; Najm and Al, 1993).

The natural organic matter is also known for its role in the transport and the trapping of organic and/or inorganic pollutants (Bartschat and Al, 1992; Tippinge, 1993). It represents also a potential substrate for the biological growth in the distribution network of drinking water. The weak dehydration of muds resulting from the treatment of drinking water and the filling of the membranes of filtration are also related to the presence of the natural organic matter in water (Dulin and Knocke 1989; Wiesner and Al, 1989; Bersillon and Al, 1999). Among the organic compounds, the phenols are regarded as harmful pollutants even with weak concentrations because of the potential dangers on health and environment (Dutta and Al, 1992, 1998).

The choice of a adsorbent material depends inter alia its type of porosity, its specific surface and nature of the element to be trapped. Our choice was made on a bentonite of M'zila (Mostaganem), rich in montmorillonite, because of its properties particular to fix many substances, of its availability in Algeria and its low costs (Essington, 1994; Amar and Gaid, 1987; Boufatit and Al, 2007). Indeed, some phyllosilicates have the property to easily adsorb water molecules or organics in interfoliar space. This phenomenon called swelling depends on the load of the layer, the localization of this one and the nature of the cations of compensation (Cailliere and Al, 1982). The bentonite is a material which contains approximately montmorillonite 75% and whose size of the particles is lower than 2 μm (Bergaya and Al, 2006). The argillaceous mineral term or phyllosilicate corresponds to hydrated aluminium silicates, of lamellate structures. These clays generally constitute a considerable fraction of grounds (Auerbach and Al, 2004). The layers of the phyllosilicates are consisted a stacking of octahedral layers (O) and tetrahedral (T). The tetrahedral layer generally consists of atoms of silicon surrounded by four oxygen atoms and bound between them by covalent bonds Si-O. The octahedral layer is formed by hexagonal units, composed of atoms of coordinate magnesium or aluminium with six oxygen atoms or with functions hydroxyls. The layers T and O are bound by covalent bonds and imply apical oxygens. The space located between the two layers is called interfoliar space. A layer and an interfoliar space form a structural unit. The phyllosilicates have the possibility of easily adsorbing water molecules in this interfoliar space.

During a isomorphic substitution of an element by another of lower oxidation step, in tetrahedral or octahedral layer, the deficit of load “+” of the layer is made up by interfoliar cations known as of compensation, exchangeable by mineral or organic cations (Cailliere and Al, 1982; Decarreau, 1990; Bouras, 2003). The most frequent substitution for a montmorillonite is that of Al^{3+} by Mg^{2+} in the octahedral layer. For this clay, the distance between the negative sites located at the level of the octahedral layer and the exchangeable cation located at the surface of the layer are such as the forces d' attraction are weak (Cailliere and Al, 1982). Substitutions of So by Al in the tetrahedral layer are also possible.

The interfoliar cations are in general exchangeable by organic and mineral cations being in solutions put in contact with the phyllosilicate. One then characterizes each phyllosilicate by his Capacity of Cation Exchange (CEC). In the case of montmorillonites, the values of CEC lie between 75 and 160 milliéquivalents for 100 grams d' clay (Viallis-Terrisse, 2000). In tables 1 and 2 we show the characteristics physicochemical of bentonite of M' Zila, Algeria (ENOF 1997).

Surface Spécifique (m ² /g)	Masse spécifique (g/cm ³)	pH	Capacité d'échange (meq/100g)	Cations échangeables (meq/100g)			Na/Ca
				Ca ²⁺	Na ²⁺	Mg ²⁺	
65,00	2,71	9,00	75,8	43,6	25,2	4,8	0,58

Table 1. Physico-chemical characteristics of bentonite

Montmorillonite	Quartz	Carbonates	Feldspaths	Biotites
45 à 60%	15 à 20%	8 à 10%	3 à 5%	8 à 10%

Table 2. Mineralogical characteristics of bentonite

2. Material and method

2.1 Procedure

For these tests, distilled water used has a pH ranging between 6 and 6,3. The initial solution of phenol equal to 100 mg/L is prepared starting from the dissolution of phenol crystallized in distilled water. The solutions are prepared by dilution in the water distilled according to the desired concentrations. For the tests of adsorption, we maintained the concentration of the constant aqueous solution (5mg/L) and varies the mass of the adsorbent m= 5,10,15,20,30,40 and 50 mg. After agitation during 5 hours with room temperature with magnetic stirrers, these solutions are centrifuged with 2000 revolutions per minute during 45 minutes for the analysis of phenol by spectrophotometer UV with a wavelength of 270nm by means of a spectrophotometer of the type SHIMADZU UV-1605.

For the kinetics of adsorption one proceeds in the same way, in beakers of 500mL containing distilled water, one adds the optimal bentonite amount (30 mg/L) as a optimal given by the jar-test. Sampling carried out during time make it possible to follow the evolution of the concentrations of phenol remaining in solution. Balance is reached after one 5 hours duration. For the analysis of the solids after adsorption of phenol sampling of bentonite (1 gram) are put in contact with phenol solutions (V=1L, C= 5 and 100 mg/L). After agitation throughout 6 hour to room temperature, the solids are separated from the liquids by filtration. After drying in a drying oven with 80°C the solids are collected for analysis by diffraction of x-rays, thermogravimetry and infra-red spectroscopy.

2.2.1 Diffraction of x-rays (DRX)

This technique allows inter alia, obtaining information on the interfoliar distance from material before and after adsorption of phenol. The apparatus X' PERT Pro of PANALYTICAL uses an assembly in reflexion θ - θ equipped with a tube with copper anode and with a detector RTMS (Real Time Multiple Strip) of type X' celerator. The recording is done uninterrupted during 90 minutes between 3° and 70° into 2θ with the wavelength $\text{CuK}\alpha$ under a tension of 50 Kv and an intensity of 40 my.

2.2.2 Thermogravimetric analyses

The thermogravimetric analyses (TG) give indications on the variation of mass of a sample subjected to a linear rise in temperature. In this present study, we used an thermo-analyzer TG-DSC Sensys evo of SETARAM working between 25 and 750°C , under reconstituted air (mixture O_2/N_2) and with a speed of rise of $5^\circ\text{C}/\text{minute}$. The analyses related to samples of clays saturated and unsaturated with phenol ($\text{C}=100\text{mg}/\text{L}$ and 5mg) and of mass $m=40\text{mg}$. These thermogravimetric analyses under oxidizing atmosphere make it possible, indeed, to differentiate the organic part of the inorganic part, in particular water.

2.2.3 Analyzes by infra-red spectrophotometer

The Infra-red Spectroscopy with Transform of Fourier (IRTF) is based on l' absorption an infra-red radiation by analyzed material. It allows via the detection of the vibrations characteristic of the chemical bonds, to carry out l'analyzes chemical functions present in material. The bentonite samples, initially out of powder, are mixed in a small proportion with KBr (2.3 mg in 100 mg of KBr), then transformed in the form of a pastille. For the analyses, we used an apparatus BRUKER Equinox 55 in the area $400\text{--}4000\text{ cm}^{-1}$, with the following conditions of recording: detector MCT, number of scans 8, resolution 4 cm^{-1} .

3. Results and discussion

3.1 Analyses of the solids

Diffractionogram X of bentonite in a rough state (figure 1), indicates a basal distance (d_{001}) from $12,50\text{ \AA}$. Moreover, it highlights the presence of several crystalline phases (quartz, feldspar). After contact with the phenol solution, the diffractionogram shows that the basal distance increased, because (d_{001}) is of $14,94\text{ \AA}$. Since d_{001} represents the thickness of the layer plus the interfoliar spacing, the spacing of the layers of initial bentonite would be equal to: $12,50\text{ \AA} - 9,60\text{ \AA} = 2,90\text{ \AA}$

The spacing of the layers of bentonite with exchange out of phenol would become equal to: $14,94\text{ \AA} - 9,60\text{ \AA} = 5,34\text{ \AA}$. A difference of $2,44\text{ \AA}$ is thus measured between the spacing of the layers of initial bentonite and those of modified bentonite. It is thus possible that phenol molecules can be easily adsorbed in this interfoliar space.

The results obtained by thermal analysis are illustrated on figure 2 where three curves are presented: that of mass (TG), its derivative ($d\text{TG}$) and heat flow (HF). Curve TG presents several losses of mass according to the temperature. For temperatures going of 25 with 200°C , one observes a first loss from approximately 7%, which corresponds at the water

beginning. It is followed of a weak loss ($\sim 0,9\%$) between 200 and 450°C, allotted to the oxidation of the organic matter imprisoned between the layers of clay and a third loss of mass beginning towards 450°C corresponding to the deshydroxylation from material. Dehydration as well as the deshydroxylation is accompanied by endothermic effects on the curve HF, while the oxidation of phenol results in two weak exothermic peaks. For a stronger phenol concentration (curve not represented), the organic matter loss is of approximately 1,8%. She thus increases with the concentration of phenol of departure.

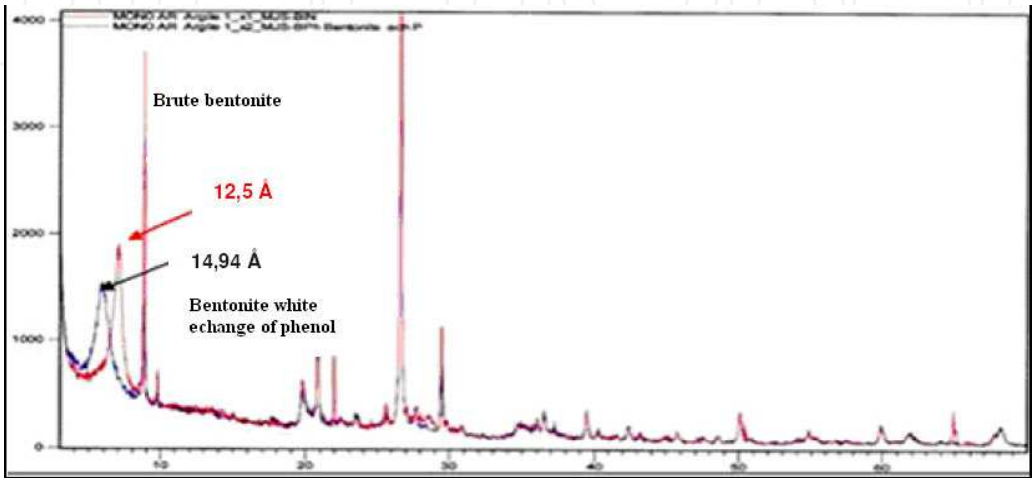


Fig. 1. Powder X-ray Diffractograms of initial bentonite and after phenol exchange

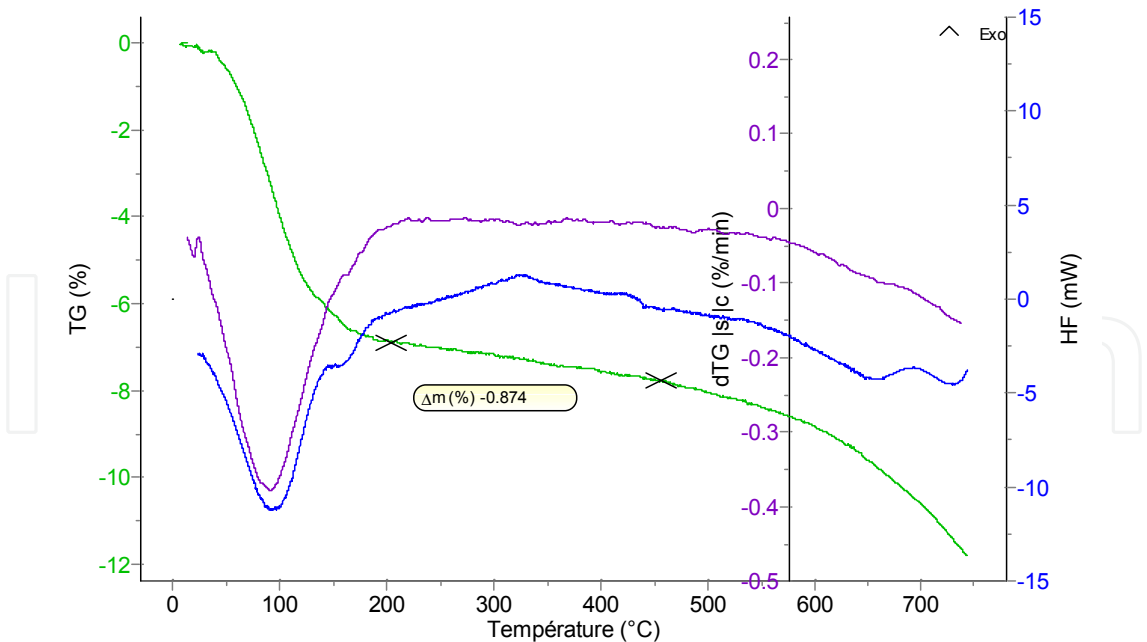


Fig. 2. TG Bentonite containing phenol (concentration at 5 mg/L)

On figure 3 are presented spectra FTIR of the various studied samples: bentonite brut, phenol and bentonite having adsorbed phenol. The presence of phenol should be evaluated by the presence of the characteristic bands, such as the connection OH (δ O-H towards

1360cm⁻¹) and δGo around 1223 cm⁻¹). The absence of these bands on the spectra could be explained by a too weak phenol concentration adsorbed in clay, the technique not being sufficiently sensitive in this case.

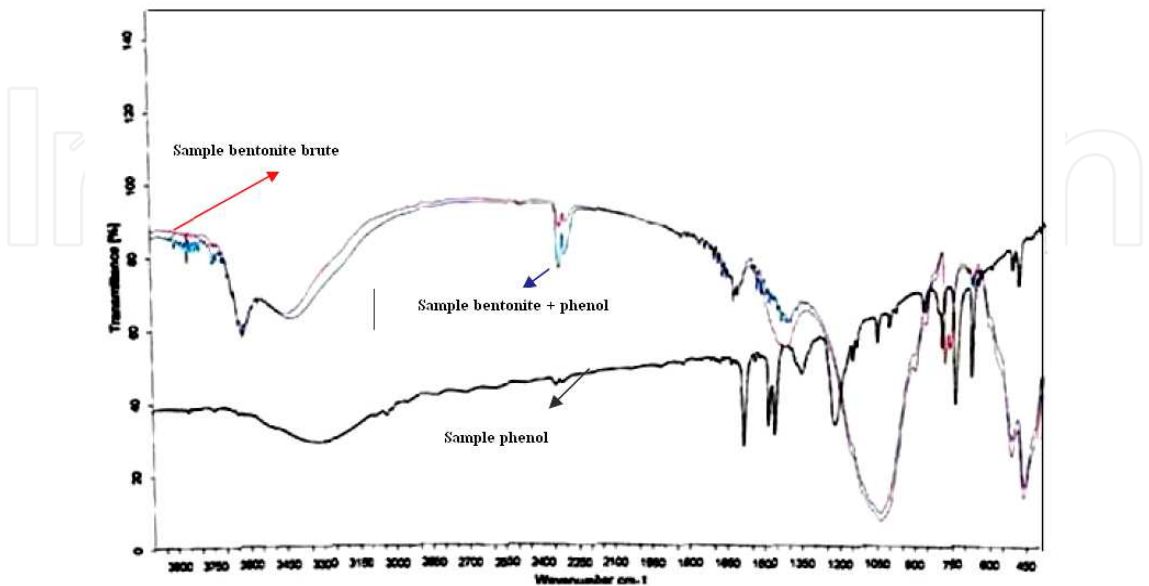


Fig. 3. Spectra FTIR of the studied samples

3.2 Analyzes phenol solutions

The residual concentrations are obtained starting from the absorbance in UV for a wavelength λ max=270nm. Figure 4 shows the whole of spectrum UV for an initial solution of phenol 20mg/L. The results relating to the study of the solutions are gathered in tables 3,4 and are illustrated by figures 4,5 and 6. Figure 5 shows the retention of phenol according to the mass of bentonite and the optimum is for a mass of 30 mg.

Co (mg/L)	Masse bentonite (mg)	Concentration d'équilibre Ce (mg/L)	Rendement % 100 (Co-Ce)/Co
5	0	5.00	0
5	5	3,98	20.4
5	10	3,40	32
5	15	2,78	44,4
5	20	2,28	54.4
5	30	1,80	64
5	40	1,80	64

Table 3. Determination of the concentrations of balance for the bentonite

Co (mg/L)	Masse bentonite (mg)	Ce (mg/L)	X=C ₀ -Ce(mg/L)	x/m (mg/g)	Log(Ce)	Log(x/m)	m/x (g/mg)	1/Ce (L/mg)
5	5	3,98	1,02	204	0,5998	2,309	0,00490	0,251
5	10	3,40	1,60	160	0,5314	2,204	0,00625	0,294
5	15	2,78	2,22	148	0,444	2,170	0,00675	0,359
5	20	2,28	2,72	136	0,3579	2,135	0,00735	0,438
5	30	1,80	3,2	106	0,2552	2,025	0,00943	0,555
5	40	1,80	3,2	80	0,2552	1,903	0,0125	0,555
5	50	1,80	3,2	64	0,2552	1,806	0,0156	0,555

Co: concentration initiale
Ce: concentration d'équilibre

Table 4. Determination of the isotherms of Freundlich and Langmuir

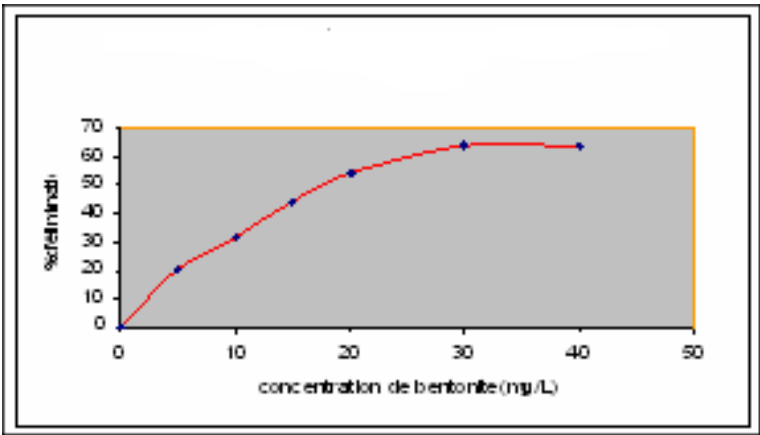


Fig. 4. Yield of elimination of phenol according to the bentonite concentration

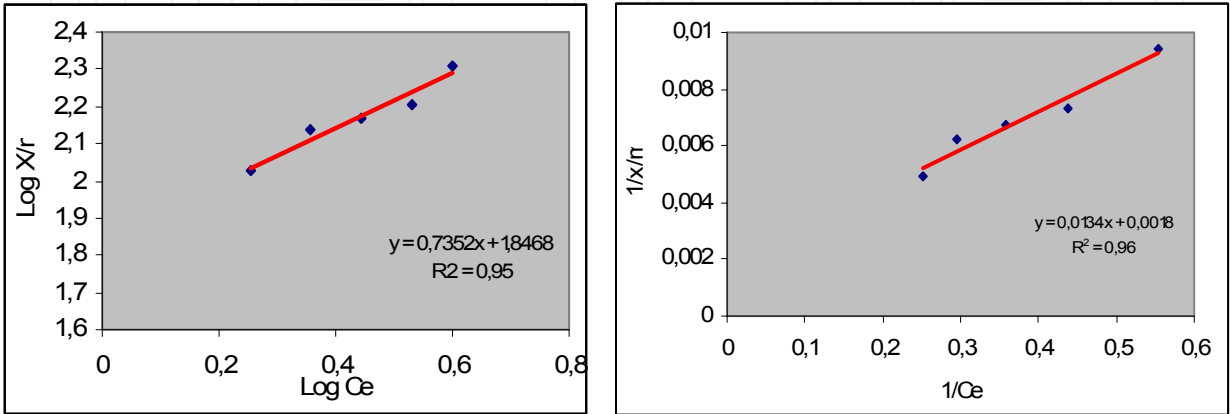


Fig. 5. Freundlich isotherm Figure 6. Langmuir isotherm

3.3 Isotherms of adsorption of phenol

Several models were quoted in the literature to describe the isotherms adsorption. The models of Langmuir and Freundlich are most often used. Balance is described by curves with the room temperature, expressing the quantity of aqueous solution adsorbed per unit of mass of adsorbent according to the concentration of the aqueous solution to the state of balance.

It is a law in the form

$$\frac{x}{m} = f(C_e)$$

X (mg): express the quantity of adsorbed aqueous solution

m: mass adsorbent (g)

C_e: concentration of the aqueous solution to the state of balance (mg/L)

From table 4 we determined the equations relating to the isotherms of adsorption (figures 6 and 7) as well as the parameters relating to the law of Freundlich (N and K) and to that of Langmuir (B and q_m).

3.3.1 The equation of Freundlich

The equation of Freundlich is form:

$$\frac{x}{m} = K C_e^{\frac{1}{n}}$$

The linearization of this expression in form logarithmic curve gives the following function.

$$\text{Log}(x/m) = 1/n \cdot \log C_e + \log K$$

K and N are constants of balance

For our test:

$$Y = 0,7352x + 1,8468$$

$$\text{Thus } \log K = 1,8468 \rightarrow K = 70,27$$

$$1/n = 0,7352 \rightarrow n = 1,36$$

$$R^2 = 0,95$$

3.3.2 Equation to langmuir

$$q = \frac{x}{m} = q_m X \frac{b C_e}{1 + b C_e}$$

x/m: Quantity of adsorbed in mg/g to balance

q_m = maximum capacity (ultimate) of adsorption

b = constant related to the energy of adsorption

C_e: Concentration with the balance (mg/l) of the organic compound

After passage to the opposite of function

$$\frac{x}{m},$$

the linearized form is the following one:

$$\frac{1}{q} = \frac{1}{qm} + \frac{1}{qmb} \left(\frac{1}{Ce} \right)$$

Figure 7 shows the variation

$$\frac{1}{x/m}$$

according to

$$\frac{1}{Ce}$$

$$Y = 0,0134 X + 0,0018$$

$$R^2 = 0,96$$

$$\frac{1}{x/m} = 0,0134 \text{ thus } \frac{x}{m} = 74,62 \text{ mg/g}$$

$$b = 7,44$$

The calculation

$$\frac{x}{m}$$

of watch which the bentonite could adsorb ~75 mg of phenol substances per gram of bentonite. We also note that the isotherms obtained follow best the law of Langmuir ($R^2 = 0,96$). Table 5 presents the variation of the outputs of elimination of phenol according to time and figure 8, representing the abatement of phenol according to time, shows that the kinetics of adsorption slows down according to the reaction time. One can separate the phenomenon in two distinct stages:

- The first stage shows a fast increase in the yields of elimination during the first two hours of contact, which can be explained by the fixing of phenol on the surface of the adsorbent
- The second phase corresponds to the external mass transfer which is fast. shows a slow increase in the yield of elimination until the time of balance, which means that there is an internal mass transfer of the absorbable which generally corresponds to a phenomenon of diffusion in the internal porosity of the adsorbent.

Temps (min)	0	5	15	30	45	60	120	180	240	300	360
Co (mg/l)	5	5	5	5	5	5	5	5	5	5	5
Ct (mg/l)	5	4,14	3,98	3,70	3,5	2,96	2,59	2,10	1,95	1,8	1,8
R (%)	0	17,12	20,4	26	30	40,8	48,2	58	61	64	64
Ct/Co		0,828	0,796	0,74	0,70	0,592	0,518	0,42	0,39	0,36	0,36
T ^{1/2} (min ^{1/2})		2,236	3,872	5,477	6,708	7,745	10,954	13,416	15,491	17,320	18,973
1-(Ct/Co)		0,172	0,203	0,260	0,300	0,408	0,482	0,580	0,610	0,640	0,640

Table 5. Variation yield of elimination of phenol according to time

A few hours of contact with the adsorbent are enough to trap phenol by adsorption effectively. Indeed, the speed of adsorption is one kinetics of first order, function of the surface of the particles but inversely proportional to the diameter of these. The right obtained on figure 9, according to the square root of time, explains the diffusion (coefficient of correlation $R^2 = 0,98$).

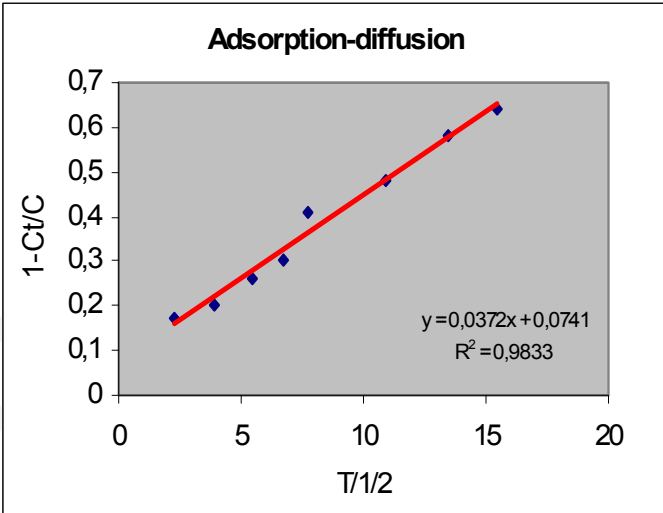


Fig. 8. Adsorption–diffusion on distilled water

Results can be compared with those of published diverse works. For example, Dali-Youcef and al., (2006) measured the adsorption of phenols on a local (bentonite) clay and a mud of dam. The results indeed confirm the capacities of the bentonite retaining more phenol with regard to the mud of dam and his capacity of adsorption is 32 mg /g. Banat and al., (2000) determined a weather of balance for the adsorption of the phenol about 6 hours and showed that the retention rate depended on the initial concentration and on the mass of bentonite used.

Al-Asheh and Al, (2003) examined the possibilities of using a bentonite for the retention of phenols and noticed that the increase in the mass of the adsorbent reduces the residual quantities of phenol in the final solution. Tests of adsorption of phenol on peat ashes and a bentonite were carried out by Viraraghavan and Alfaro, (1997). Their results indicate that the bentonite could retain phenol 46%. YU and Al, (2004) also showed that the adsorption of the phenol compounds by a montmorillonite increases with the initial phenol concentrations. In addition, more recently, of the tests of adsorption carried out by Nayak and Al, (2007) related to the retention of phenol on natural clay and modified clays. They concluded that it is possible to improve the capacity of adsorption of clays by specific treatments. Lastly, Boufatit and Al, (2007), which studied the adsorption of organic compounds by Algerian clays rich in montmorillonite, show that the chlorinated phenols resulting from the degradation of the aromatic compounds (pesticides), are easily adsorbed on these clays.

Other materials were used for the retention of phenols in water. In particular, Guesbaya, (2005) used coagulation-flocculation with aluminium sulphate for water containing of phenol, but the retention remains very weak because the simple organic compounds tested are slightly eliminated whatever the amount from coagulant (sulphate of alumina) or the initial concentration of the compound. According to Al-Asheh and Al, (2003), in comparison with bentonite, the activated carbons have a higher adsorption capacity for the phenolic compounds. However, because of the relatively high cost of the activated carbon, the natural adsorbents, in spite of a lower performance, remain a solution interesting for the elimination of the contaminants of worn water.

4. Conclusion

The goal of this work was to study, experimentally, potential of bentonite gross of M' Zila in the adsorption of phenol pollutants. The study of the isotherms of adsorption enabled us to evaluate characteristics the characteristics adsorption of this bentonite. The results of the tests carried out in laboratory show the elimination of 64% of the concentrations (5 mg/L) of phenol and the bentonite can adsorb 75 mg/L phenol substances per gram and could be interesting in the elimination of the organic matter present in water. However, the optimum conditions for its use remain to be determined. The analysis of the isotherms makes it possible to determine if purification by adsorption can be carried out or not according to the initial phenol rate in water as well as an estimate of the mass of adsorbent making it possible to reduce in an important way the concentrations in pollutants. The preliminary reduction in the organic matter rate should limit the formation of potentially carcinogenic organochlorinated compounds likely to occur during a secondary treatment to chlorine.

5. References

- Amar H. & A. Gaid (1987). Fixation on bentoniques clays of metallic ions in residual waters, *Rev. Sci. de l'Eau*, 3, 33-40.
- Al-Ashehs., F. Banat & L. Abu-Aitah (2003). Adsorption of phenol using different types of activated bentonites. *Separation and Purification Technology*, 33, 1-10.


- Andreozzi R., V. Caprio., A. Insola & R. Marotta (1999). Advanced oxidation process (AOP) for water purification and recovery. *Catal. Today*, 53, 51-59.
- Auerbach S.M., K.A. Carrado & P.K. Sutta (2004). *Handbook of Layered Materials*, Marcel Dekker, New York, USA, 650 p.
- Banat F. A., B. Al-Bashir., S. Al-Asheh & O. Hayajneh (2000). Adsorption of phenol by bentonite. *Environmental Pollution*, 107, 391-398.
- Bartschat B.M., S.E. Cabanis & F.M. Morel (1992). Oligoelectrolyte model for cation binding by humic substances. *Environ. Sci. Technol.*, 26, 284-294.
- Bergaya F., B.K.G. Theng & LAGALY G. (2006). *Handbook of clay science*, Developpement in clay science, series volume 1, 124 p.
- Bersillon J.L. (1983). The mechanism of organic removal during coagulation. Thesis, Mc Master University, Hamilton Ontario, USA, 188 p.
- Bersillon J.L., B. Lartiges, F. Thomas & L. Michot (1999). The transformation of water quality: from contribution to water treatment. Effect of mineral-organic-microorganism interactions on soil and Freshwater Environments. Kluwer Academic, Plenum Publisher, pp. 367-373.
- Boudhar H. (1999). Improvement of the functioning of the small units of treatment of drinking water to eliminate néoformés elements, THM et turbidité. *Office International de l'Eau*.
- Boufatit M., H. Ait-Amar & W.R. Mcwhinnie (2007). Development of Algerian material montmorillonite clay. Adsorption of phenol, 2-dichlorophenol and 2,4,6-trichlorophenol from aqueous solutions onto montmorillonite exchanged with transition metal complexes. *Desalination*, 206, 394-406.
- Bouras O. (2003). Properties adsorbantes of pontées organophiles clays: synthesis and characterization, Doctoral thesis, Univ. Limoges, France.
- Cailliere S., S. Henin & M. Rantureau (1982). *Minéralogie des argiles*. Masson, tome 1 et 2, pp. 184-189.
- Chiron S., A. Fernandez-Alba, A. Rodriguez & E. Garcia-Calvo (2000). Pesticide chemical oxidation: State of the art. *Water Research*, 34, 366-377.
- Dali-Youcef Z., H. Bouabdasselem & N. Bettahar (2006). Elimination of organic compounds by local clays. *Comptes Rendus de Chimie*, 9 (10), 1295-1300.
- Decarreau A. (1990). Clayey materials: structure, properties and applications (collective work), Ed. Société Française de Minéralogie et de Cristallographie, pp. 8-21.
- Dore, M. (1989). *Chimie des oxydants et traitement des eaux*, Ed.Tech. & Doc ; Lavoisier, Paris.
- Dulin B.E. & W.R. Knocke (1989). The impact of incorporated organic matter on the dewatering characteristics of aluminium hydroxide Sludge. *Journal AWWA*, 81, 74-79.
- Dussert B.W (1997). Advanced oxidation. UK: *Industrial wastewater*, pp.29-34.
- Dutta n.N., G.S. Patil et S. Brothakur (1992). Phase transfer catalyzed extraction of phenolic substances from aqueous alkaline stream. *Separation Science and Technology*, 27, 1435.

- Dutta N.N., S. Brothakur et R. Baruah (1998). A novel process for recovery of phenol from alkaline wastewater: laboratory study and predesign cost estimate. *Water Environ. Res.*, 70, 4-9.
- ENOF (1997). Rapport d'analyse de la bentonite de M'Zila, Mostaghanem, Laboratoire Enof, Algérie.
- Essington M.E. (1994). Adsorption of aniline and toluidines on montmorillonite, *Soil Science*, 158(3), 180-188.
- Galze H., F. Beltran, T. Tuhkanen & J.W. Kang (1992). Chemical models of advanced oxidation processes. *Water Poll. Res. J. Canada*, 27, 23-42.
- Guesbaya A. N. (2005). Coagulation-floculation by the sulfate of aluminum of phenolic organic compounds and humiques substances. *Larhyss Journal*, 4, 153-168.
- Golich r. & D. Bahnemann (1997). Solar Water Treatment: Principles and Reactors, Intercalibration of Radical Sources and Water Quality Parameters, Swiss Federal Institute for *Environmental Science and Technology EAWAG*, Switzerland, pp. 137-148.
- Hoang L. (2009). *Comparison of the energy returns on degradation of organic three by several processes of oxidation advanced(moved) in aqueous environment(middle)*, Doctoral thesis, Univ. Poitiers, France.
- Hooper S.M., R.S. Summers, S. Gabriele & D.M. OWEN (1996). Improving GAC performance by optimized coagulation. *Journal AWWA*, 88, 107-120.
- Lefebvre e. & B. Legube (1990). Iron III Coagulation of humic substances extracted from surface waters: effect of pH and humic substances concentration. *Water Research*, 24, 591-606.
- Meier, J.R. (1988). Genotoxic, Activity of organic chemicals in drinking water, *Mutation Res.*, 196, 211- 245.
- Najm i.n., V.L. Snoeyink & Y. Richard (1993). Removal of 2, 4, 6-trichlorophénol and natural organic matter from water supplies using PAC in floc- blanket reactors. *Water Research*, 27, 551-560.
- Nayak P. S. & B. K. Singh (2007). Removal of phenol from aqueous solutions by sorption on low cost clay. *Desalination*, 207, 71-79.
- Safarzadeh-Amiri A., J.R. Bolton & S.R. Caster (1996). The use of iron in advanced oxidation processes. *J. Adv. Oxid. Technol.*, 1, 18-26.
- Terrisse V. (2000). Interaction of constituent hydrated, main Silicates of Calcium of the cement, with the chlorides of alkaline. Analogy with clays, Doctoral thesis, Univ. de Bourgogne, Dijon, France.
- Tippinge. (1993). Modelling the competition alkaline earth cations and trace species for binding by humic substances. *Environ.Sci.Technol.*, 27, 520-529.
- Stevens A.A., C.J. Slocum, D. Seeger & G.G. Robeck (1976). Chlorination of organics in drinking water. *Journal AWWA*, 68, 615-620.
- Viraraghavan T. & F. Alfaro (1997). Adsorption of phenol from wastewater by peat, fly ash and bentonite. *Journal of Hazardous Materials*, 57, 59-70.
- Wiesner M.R., M.M. Clark & J. Malleviale (1989). Membrane filtration of coagulated suspensions. *J. Environ. Engin.*, 115, 20-40. .

YU J., M. Shin, J. Noh & J. Seo (2004). Adsorption of phenol and chlorophenols on Ca-montmorillonite in aqueous solutions. *Geosciences Journal*, 8(2), 185-189.

IntechOpen

IntechOpen

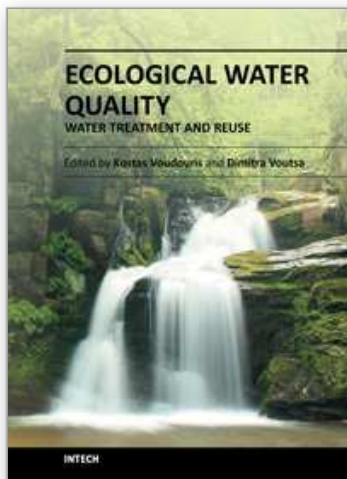

Ecological Water Quality - Water Treatment and Reuse

Edited by Dr. Voudouris

ISBN 978-953-51-0508-4

Hard cover, 496 pages

Publisher InTech

Published online 16, May, 2012

Published in print edition May, 2012

This book attempts to cover various issues of water quality in the fields of Hydroecology and Hydrobiology and present various Water Treatment Technologies. Sustainable choices of water use that prevent water quality problems aiming at the protection of available water resources and the enhancement of the aquatic ecosystems should be our main target.

How to reference

In order to correctly reference this scholarly work, feel free to copy and paste the following:

Bachir Meghzili, Medjram Mohamed Salah, Boussaa Zehou El-Fala Mohamed and Michel Soulard (2012). Elimination of Phenols on a Porous Material, Ecological Water Quality - Water Treatment and Reuse, Dr. Voudouris (Ed.), ISBN: 978-953-51-0508-4, InTech, Available from:
<http://www.intechopen.com/books/ecological-water-quality-water-treatment-and-reuse/elimination-of-phenols-on-a-porous-material>

INTECH
open science | open minds

InTech Europe

University Campus STeP Ri
Slavka Krautzeka 83/A
51000 Rijeka, Croatia
Phone: +385 (51) 770 447
Fax: +385 (51) 686 166
www.intechopen.com

InTech China

Unit 405, Office Block, Hotel Equatorial Shanghai
No.65, Yan An Road (West), Shanghai, 200040, China
中国上海市延安西路65号上海国际贵都大饭店办公楼405单元
Phone: +86-21-62489820
Fax: +86-21-62489821

© 2012 The Author(s). Licensee IntechOpen. This is an open access article distributed under the terms of the [Creative Commons Attribution 3.0 License](#), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

IntechOpen

IntechOpen