

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

6,900

Open access books available

186,000

International authors and editors

200M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.
For more information visit www.intechopen.com



Recent Characterisation of Sol-Gel Synthesised TiO₂ Nanoparticles

Muhamad Zamri Yahaya, Mohd Asyadi Azam,
Mohd Asri Mat Teridi, Pramod Kumar Singh and
Ahmad Azmin Mohamad

Additional information is available at the end of the chapter

<http://dx.doi.org/10.5772/67822>

Abstract

High demand and current applications have led to continuous study and subsequent improvement of TiO₂ nanoparticles. The versatility of the sol-gel method allows employing different process parameters to influence the resultant properties of TiO₂ nanoparticles. The evaluation and characterisation process of the synthesised TiO₂ nanoparticles commonly involves a series of methods and techniques. Such characterisation methods include phase, structural, morphology and size analysis. A combination of data from these evaluations provides the relationship between the synthesis parameters and the end properties of TiO₂ nanoparticles. Apart from the research findings on TiO₂ nanoparticles, the characterisation used to obtain these findings is equally important. Thus, this chapter highlights the recent characterisation techniques and practices employed for TiO₂ nanoparticles synthesised by the sol-gel method.

Keywords: TiO₂ nanoparticles, sol-gel, phase analysis, Rietveld refinement, morphology, particle size

1. Introduction

Developments in the polymorphic TiO₂ nanoparticles have extensively drawn major interest of researchers and scholars. The wide exploitation of TiO₂ nanoparticles includes the study and application in photovoltaics [1], photocatalysis [2], batteries [3], filler material in composites [4] and biomedical products [5]. The key issues addressed focused on achieving better characteristics of TiO₂ nanoparticles as well as improved performance of end devices. This

explains the large number of ongoing research studies considering the versatility of TiO_2 nanoparticles in a broad range of applications.

The significant interest on TiO_2 nanoparticles was driven by the unique characteristics of the material, such as low preparation cost, non-toxic, favourable band edge positions and diverse morphologies possibilities [6–8]. Factors determining these end properties are mainly dependent on the synthesis routes used to produce TiO_2 nanoparticles. Since 1971, the sol-gel has been the most significant synthesis method known and applied in producing multi-component oxides such as TiO_2 [9]. Parameters such as the type of precursors [10], the pH of solution [11], preliminary solution treatment [12] and calcination temperatures [13] yielded varying properties of the resultant TiO_2 nanoparticles.

The process of evaluating the performance/defects of TiO_2 nanoparticles involves a series of characterisation methods. To ensure sufficient data, the selection of characterisation methods is highly important. Highly practised characterisations attributed to the evaluation of TiO_2 nanoparticles include:

- (i) Structural and phase analysis
- (ii) Morphological observations
- (iii) Particle size analysis

These analyses allow researchers to determine the effects of the sol-gel parameters for the synthesised TiO_2 nanoparticles. Such information is vital to continuously develop TiO_2 nanoparticles. This explains the reasons why such characterisation methods are highly preferred in the current research works related to TiO_2 nanoparticles.

Currently, there are several available review articles on TiO_2 nanoparticles, which discuss the photocatalytic performances in various applications [14–16]. The preparation and synthesis were critically reviewed as well [17–19]. Other available reviews include the phase and structural transformation of TiO_2 nanoparticles [20, 21]. Technical review on TiO_2 nanoparticles characterisation, however, has received only little attention although it is significantly relevant to the evaluation of TiO_2 nanoparticles.

Thus, this chapter focuses on recent characterisation of TiO_2 nanoparticles synthesised by the sol-gel method. Commonly practised configuration of characterisation corresponding to TiO_2 nanoparticles for over 7 years (2010–2016) is selectively reviewed in this chapter. Few earlier articles were also referred to strengthen the overall understanding on the subject matter.

2. Chemical reaction of the sol-gel method

The sol-gel method is the process of transforming sols (solid particles suspended in liquid) into gels (particulate networks of sols). This involves two main reactions: hydrolysis and condensation, prior to obtaining crystalline TiO_2 nanoparticles by calcination (**Figure 1**). For synthesising TiO_2 nanoparticles, commonly used precursors include $\text{Ti}(\text{OBU})_4$ [22], TiCl_3 [10],

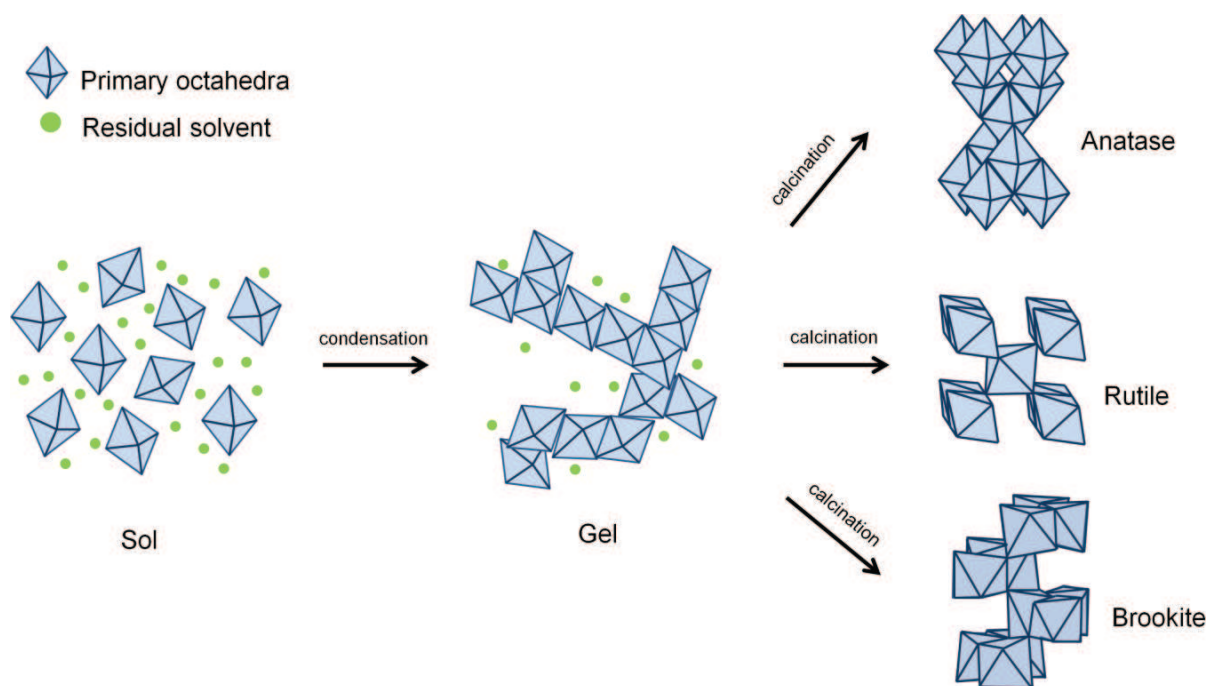


Figure 1. The hydrolysis, condensation and calcination process of the sol-gel method in synthesising the crystalline anatase, rutile and brookite TiO₂ nanoparticles.

TiCl₄ [23], TiBr₄ [24] and Ti[OCH(CH₃)₂]₄ (TTIP) [25]. These precursors were then hydrolysed by adding water (hydrolysis), resulting in the formation of complex three-dimensional network (condensation) as shown in the following equations:

Hydrolysis:



Condensation:



where R in the equation represents ethyl, i-propyl, n-butyl and so on [26, 27]. The titanium precursor is often diluted before adding water. This reduces the rapid reaction rate of the hydrolysis process.

Size and morphology of the end TiO₂ nanoparticles are highly influenced by the precursor–water ratio [28]. Lower ratio of water–precursor resulted in monodisperse particle of 0.5–1 nm in diameter [11]. For higher ratio values, unstable colloidal and predicateds would form and aggregate. Peptisation is commonly carried out for these aggregates to achieve the final size, which is usually less than 100 nm [29]. Higher pH of solution contributed to increased

particle size of TiO_2 nanoparticles [30]. The calcination process should be carefully determined as the phase transformation of TiO_2 is highly influenced by the employed temperature [31]. The end structures of crystalline TiO_2 polymorphs (anatase, rutile or brookite) are thus formed from the colloidal suspension, depending on the above parameters.

3. Phase and structural characterisation

The phase and structural analyses are significant characterisation techniques that are usually associated with the main discussion in analysing the current sol-gel-synthesised TiO_2 nanoparticles. The means of X-ray diffraction (XRD) are utilised to qualitatively identify the phases obtained by referring to the XRD databases [32]. Additionally, the data then can be subjected to the Rietveld refinement to yield significant fitting parameters for quantitative evaluations.

Due to nanosized TiO_2 nanoparticles (<100 nm), deviations on the diffraction signal can be avoided to achieve a reliable XRD analysis. Physically, the fine powder form of the TiO_2 nanoparticles provides relatively easy sample handling and preparation, ensuring smooth and flat surface. This is important as sample displacement is the main factor contributing to errors in the determination of structural parameters. The dominant TiO_2 diffraction peaks were found to lie between the angle of $2\theta = 25\text{--}30^\circ$. Thus, Bragg angle range of $2\theta = 20\text{--}80^\circ$ was practically applied in analysing TiO_2 nanoparticles [33, 34]. Due to the increase in crystallinity, TiO_2 nanoparticles subjected to calcination were commonly associated to higher peak intensities compared with the untreated TiO_2 nanoparticles [35]. The lattice plane corresponding to the particular peak reflects the preferable growth orientation of TiO_2 nanoparticles crystal [32, 36, 37]. Additionally, by employing the Debye-Scherrer equation, the crystallite sizes of the synthesised TiO_2 nanoparticles can be calculated directly.

Examples of phase determination (by search and match) can be observed from the work by Banerjee et al. [38] in examining the addition of Pd and Ga on synthesised TiO_2 nanoparticles. In addition to the observation on the intensities reduction (**Figure 2a**), the observed peak broadening (**Figure 2b**) and deconvolution of peaks (**Figure 2c–e**) in the XRD pattern is also another indication that can be discussed in parallel to the phase identification. These phenomena, however, are often related to structural alteration due to the presence of non-uniform strain, posed by the substitutional and interstitial dopants [39, 40]. Similarly, the work by Chen et al. [33] also utilise the phase analysis in investigating the Fe^{3+} -doped TiO_2 nanoparticles. With reference matched only to the JCPDS File No. 21-1272, the formation of pure anatase phase was reported. Additionally, as secondary phases were absent in the observed XRD pattern, it can be concluded that the added Fe^{3+} from the ferric nitrate had been completely incorporated into the TiO_2 nanoparticles. Relating to the current sol-gel practices, such phase identification is essential as most sol-gel synthesis approaches involve a wide diversity in chemical variations. Apart from that, other effects of Fe^{3+} addition, such as reduction of the peak intensities, were also compared in explaining the crystallinity of TiO_2 nanoparticles.

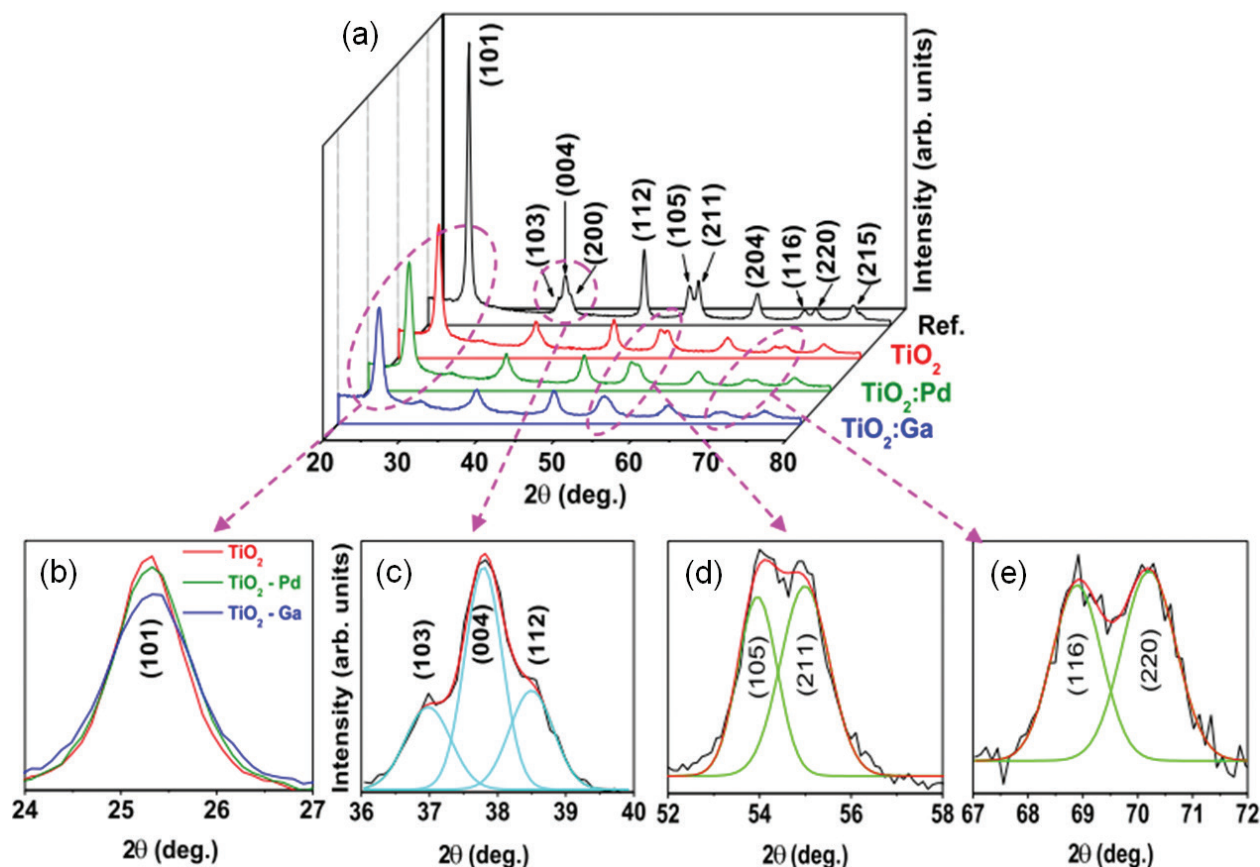


Figure 2. Comparison of XRD patterns for (a) pure TiO₂ nanoparticles and TiO₂ nanoparticles doped with Pd and Ga, (b-e) overlapped XRD curves representing peak broadening and deconvolution with respect to the crystallographic orientation. Reprinted with permission from Ref. [38]. Copyright 2016, Elsevier.

Furthermore, comparison by the phase analysis is highly preferable in investigating large variation of sol-gel techniques. As an example, from the spectra comparison, synthesis with different precipitation conditions clearly portrayed a significant influence on the resultant structural analysis of the TiO₂ nanoparticles (**Figure 3a–b**). It is shown that the storage condition favours earlier rutile transformation as compared to the centrifuge condition [41]. Other example includes the studies on the use of weak/strong acids in favouring different mixtures of TiO₂ polymorphs. Interestingly, pure anatase phase was reported to be more favourable with the usage of milder acid [42]. In another case, different mixtures of anatase and rutile phases were also obtained in the XRD spectra. However, these preferences were mainly associated to the different ranges of applied calcination temperature [43]. In most cases, higher calcination temperature tended to produce rutile, mainly due to its stability compared with anatase and brookite [43, 44]. Apart from that, Potlog et al. [45] reported that the reverse transformation of rutile to anatase is possible by utilising the H₂ environment. Such behaviour can be distinguished clearly from the XRD curves after annealing, which indicates the absence of the rutile (110) peak when compared to before annealing in the H₂ environment.

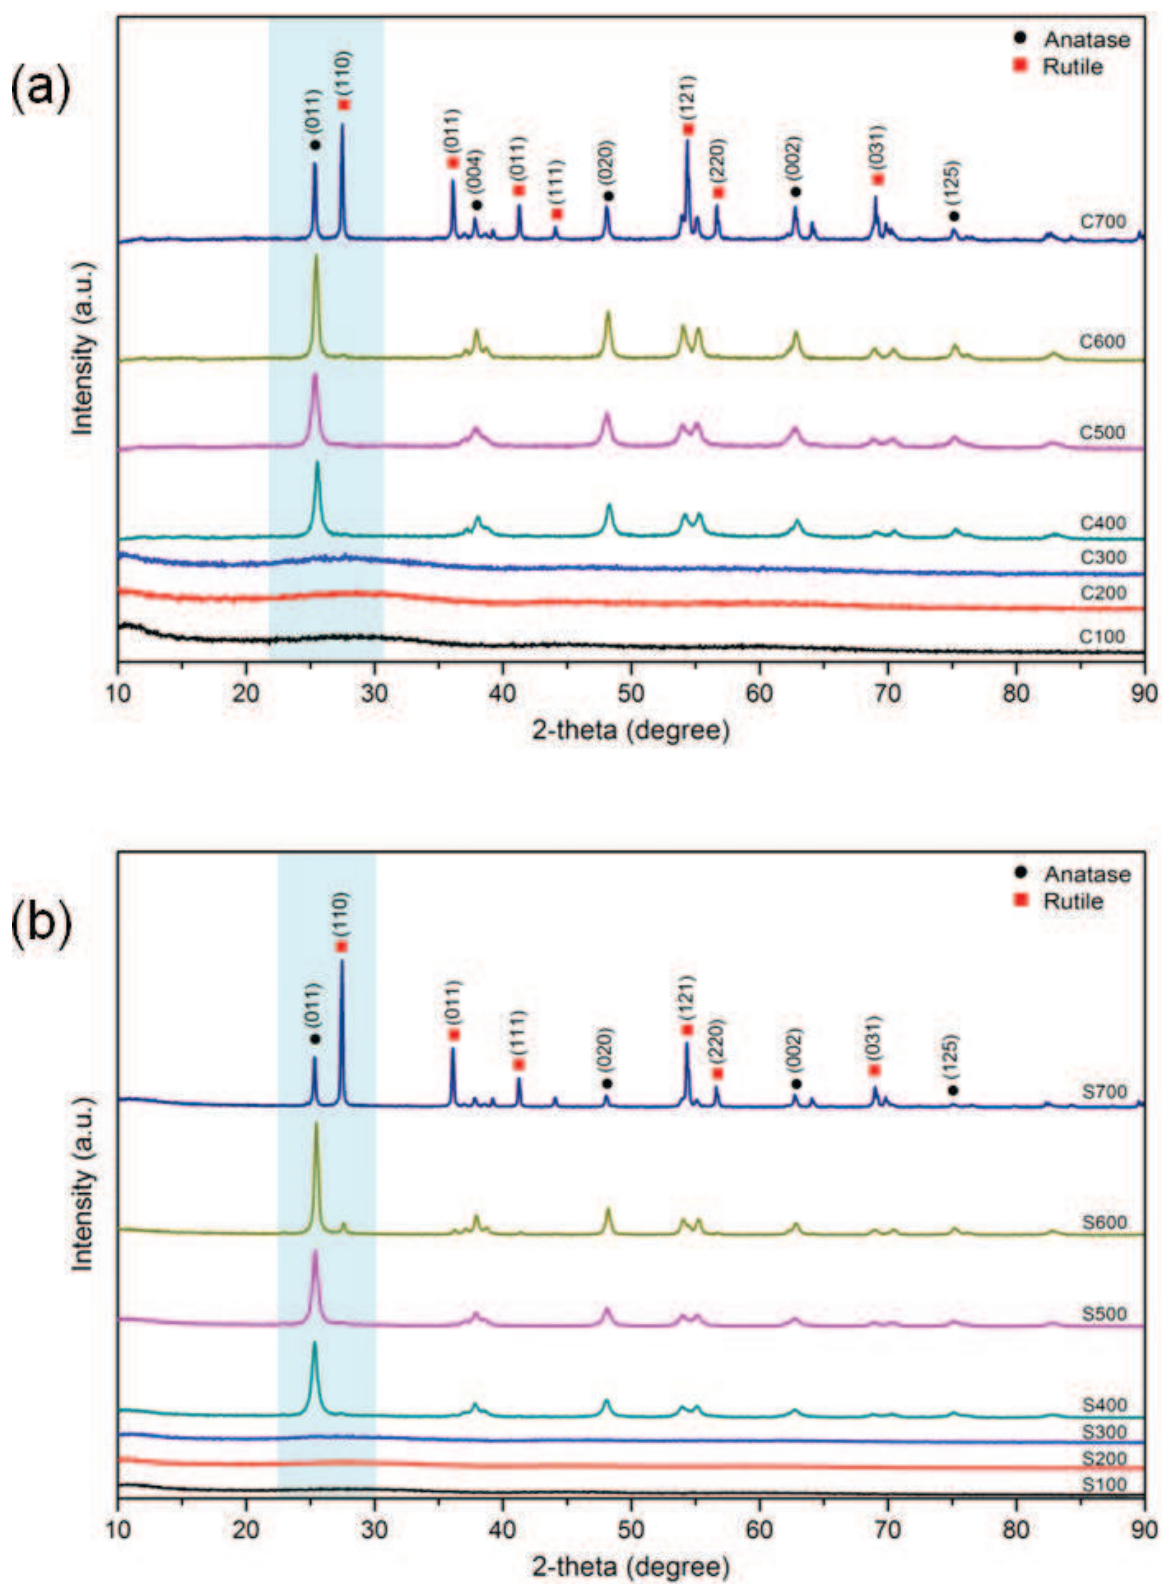


Figure 3. X-ray diffraction patterns of TiO_2 nanoparticles at various calcination temperatures synthesised through (a) centrifuge and (b) storage precipitation conditions (the shaded area represents changes on the anatase and rutile peak). Reprinted with permission from Ref. [41]. Copyright 2015, Elsevier.

4. Rietveld refinement

In Rietveld analysis, the experimental XRD pattern is fitted onto a reference data, yielding a resulted/simulated XRD model. Differences between the experimental and simulated XRD produce the fitting parameters through the Rietveld algorithm. Such parameters (goodness of fit (GOF), R_{exp} and R_{wp}) reflect the reliability of the corresponding XRD pattern. To relate, the analysis was significantly practised to further characterise TiO₂ nanoparticles, indicating the reliability of the XRD analysis and the synthesis process as a whole.

The refinement process utilises the pattern and data obtained from XRD. Thus, factors that affect the XRD analysis are also responsible in determining the accuracy of the Rietveld refinement. In the phase quantification analysis, the evaluations are attributed to the intensities of the diffraction peaks, yielding the phase percentages of TiO₂ anatase, rutile or brookite. Additionally, the increment on the full width at half maximum (FWHM) of TiO₂ polymorph peaks reduces the resultant crystallite sizes of these phases [46].

During refinement, various parameters (peak shape, lattice parameter and atomic position) were adjusted to achieve the best-fit model, commonly discussed as the visual fit process. These optimised models were generated from the differences between the observed and computed intensities to yield fitting parameters such as the weighted R profile (R_{wp}), R expected (R_{exp}) and the goodness of fit (GOF) [47]. The values vary accordingly to the different sol-gel approach employed in synthesising TiO₂ nanoparticles. For instance, typical GOF values obtained for the anatase TiO₂ synthesised by various heat treatments were in the range of 1.0–2.0 [41, 48].

As an example, the fitted model obtained by Yahaya et al. [41] was used in determining the structural parameters of TiO₂ nanoparticles synthesised by centrifuge and storage precipitation (**Figure 4a**). Most Rietveld discussions focused on this crucial plot (as it is the sole figure directly representing the visual fit) by observing the displacement of the peaks between the calculated and observed pattern. Then, from such displacement, the fitting parameters were generated (**Figure 4b–c**). From these quality indicators (R_{wp} , R_{exp} and GOF), the centrifuge condition was quantitatively determined as the synthesis route to ensure better reliability in the XRD analysis. In most refinement works, these parameters are the commonly reported results, which, however, are significant towards the phase and structural analysis/discussion of the synthesised TiO₂ nanoparticles [49].

In different cases, the usefulness of the Rietveld analysis was capitalised in investigating chemical reactions of TiO₂ composite coatings [50]. The approach was to compare the refined pattern of pure rutile and anatase TiO₂ with the refined pattern of the hydroxyapatite (HAP)/TiO₂ composite coatings. Two main points were used to prove that the chemical reactions did not occur. The first was by obtaining similar structural parameters of TiO₂ and HAP in the composites compared with the parameters of the corresponding phases individually. The second was by obtaining comparable occupancy factor value (acquired from the refinement) of the HAP for all HAP/TiO₂ composite samples (similar values indicate retaining of its structure by HAP, which reflect the absence of any reactions) [51]. In complex TiO₂ sol-gel synthesis,

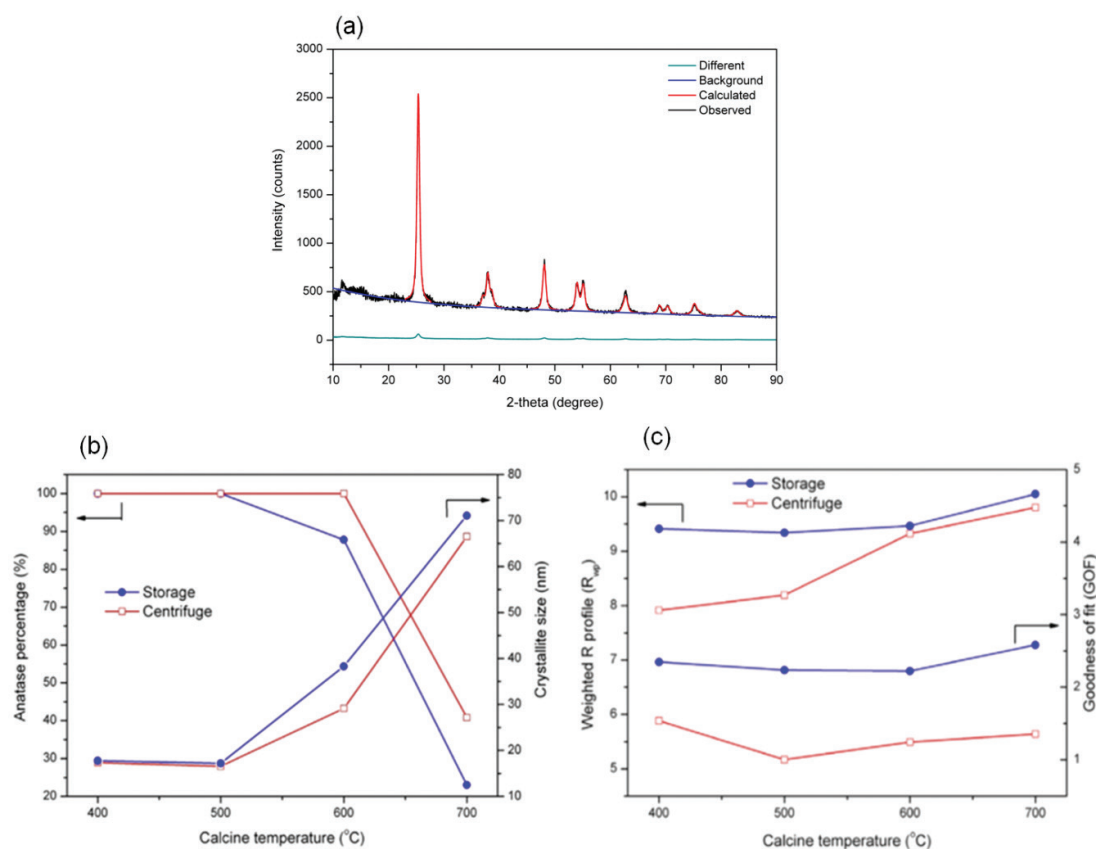


Figure 4. Example of the fitted profile for (a) the TiO_2 nanoparticles synthesised by centrifuging and 500°C calcination temperature and the Rietveld analysis for the synthesised TiO_2 nanoparticles, (b) Anatase percentage and crystallite size and (c) Weighted R profile. Reprinted with permission from Ref. [41]. Copyright 2015, Elsevier.

this approach (occupancy value determination) is highly essential in phase investigation/studies, as it provides quantitative comparison—an added bonus apart from the conventional phase analysis from the XRD.

5. Microstructural and elemental characterisation

Morphologies observation is an important qualitative characterisation in analysing TiO_2 nanoparticles. Observation on the microstructural behaviour of nanoparticles was done based on the micrograph obtained from electron microscopy, commonly the FESEM [52] and HRTEM [53]. Selection of the characterisation method usually depends on the samples' suitability and resolution of the techniques. Methods such as the FESEM and HRTEM offer higher versatility, as both can be further exploited to compensate additional analysis such as the elemental analysis.

5.1. Field emission scanning electron microscope

In FESEM imaging, the secondary electron (SE) mode is more preferable compared with the backscattered electron (BSE) mode. SE mode allows more detailed surface images of TiO_2 nanoparticles, which is more significant compared with the BSE mode [52]. This is significant

in allowing better interpretation on micrographs as TiO₂ nanoparticles are commonly subjected to agglomerations.

The observation of the TiO₂ nanoparticles' morphology commonly requires magnification up to 30,000 times [54]. However, higher magnification up to 200,000 times has also been reported in characterising the surface morphology of TiO₂ nanoparticles [52, 55]. These mainly depend on the condition of TiO₂ nanoparticles prior to characterisation. In addition, dry TiO₂ nanoparticles resulting from calcination allow higher magnification observation compared with uncalcined nanoparticles. Coatings with conductive metals such as gold are required prior to the imaging process. In terms of image acquisition, less crystalline TiO₂ nanoparticles were commonly subjected to higher charging effects during imaging, causing whitish disturbance, which can be wrongly interpreted to the actual TiO₂ nanoparticles.

Good examples of how SE images are much preferable for TiO₂ nanoparticles can be demonstrated by the significant differences on the morphology of the rutile and anatase phases which was attained by different route of sol-gel synthesis [41]. With magnification of up to 30,000 times, the shapes and sizes of both centrifuge and storage TiO₂ nanoparticles were clearly distinguishable from the micrographs (**Figure 5a–f**). Additionally, the capability to go as high as such magnification was also contributed by high calcination temperature (450–700°C) [52]. Apart from providing easier observation and interpretation on TiO₂ nanoparticles, the ability to go for high magnification allows accurate size determination of the particles (size determination from SEM micrograph currently gained significant interest in TiO₂ nanoparticles characterisation). A similar approach was also demonstrated by Khatun et al. [55] in observing agglomerated TiO₂ nanoparticles. Images obtained with magnification up to 200,000 times clearly distinguished the morphological behaviour of the TiO₂ nanoparticles. Due to that, the fusing of individual TiO₂ nanoparticles into larger agglomerates was proven in the work. The initial decarburisation process at 450°C for 6 h allowed such SEM observation. Furthermore, most relatively high heat-treating processes (mainly above 400°C) allowed good observation on the sol-gel synthesised TiO₂ nanoparticles during SEM imaging [35, 56].

5.2. High-resolution transmission electron microscope

The main difference of the HRTEM technique from that of the FESEM is how images are generated by the transmission of electron through TiO₂ nanoparticles. Thus, a very thin sample is required for observation through HRTEM.

In the initial preparation, TiO₂ nanoparticles were suspended in a solution and then deposited onto a silicon oxide film supported by a Cu mesh. This allowed observing individual and non-agglomerate particles of TiO₂. Apart from morphological and surface behaviour characterisations, higher resolution of HRTEM provided observation and measurement on the lattice fringes of TiO₂ nanoparticles as well. This was used for the validation of the structural analysis from XRD and to observe the possible growth plane of TiO₂ nanoparticles [34]. The common magnification range used to observe TiO₂ nanoparticles ranged from 195,000 times for shape and distribution observation to 610,000 times for lattice fringes analysis [57].

Observation on the shape of TiO₂ nanoparticles synthesised by the centrifuge precipitation sol-gel method was obtained by Yahaya et al. [41] by utilising a magnification of 610,000 times.

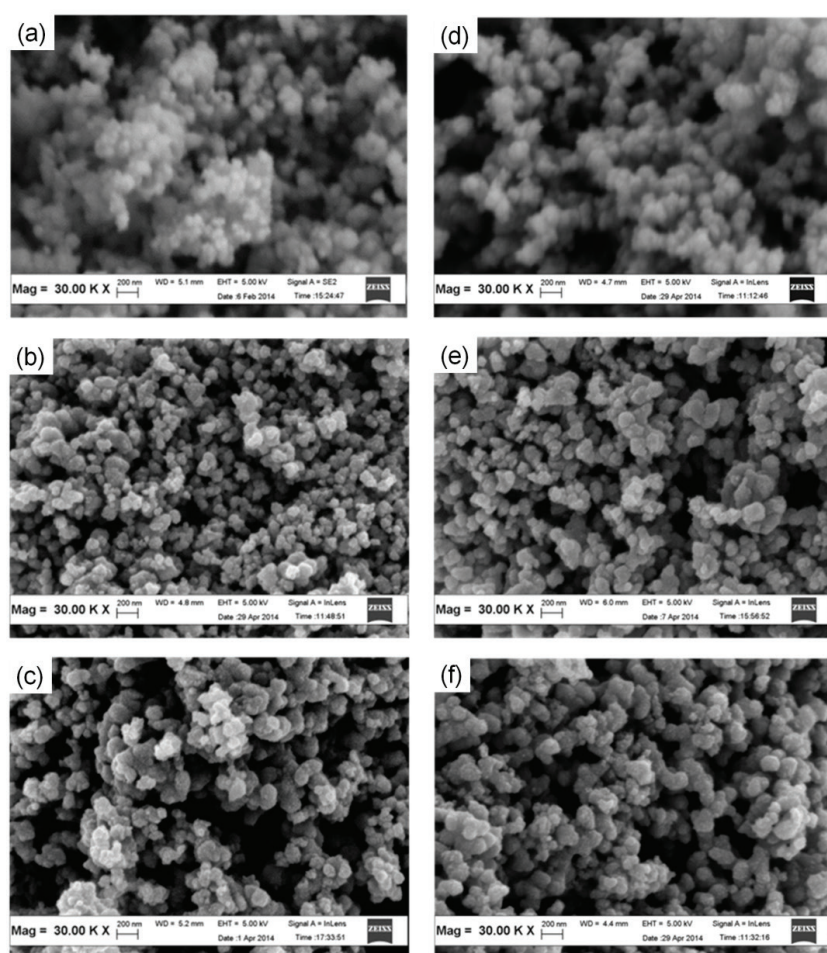


Figure 5. SEM images of the TiO_2 nanoparticles synthesised by the sol-gel method for (a) as synthesised centrifuge, (b) centrifuge calcined at 500°C , (c) centrifuge calcined at 600°C , (d) as synthesised storage (e) storage calcined at 500°C , and (f) storage calcined at 500°C . Reprinted with permission from Ref. [41]. Copyright 2015, Elsevier.

The preferable circular shapes of the TiO_2 nanoparticles favour by such synthesis method were obviously revealed with such high magnification (**Figure 6a, b**). Similar magnification was also employed by Shen et al. [34] in observing the rectangular shape of the microwave-assisted sol-gel-synthesised TiO_2 nanoparticles. Making such observation is the main benefit of employing HRTEM when compared with SEM. However, HRTEM is mainly employed for sol-gel-synthesised TiO_2 nanoparticles, which also depend on the lattice fringes measurement and observation [43]. Additionally, high-resolution images (**Figure 6c**) of the TiO_2 nanoparticles indicated favourable crystal growth along the (011), evaluated by the lattice fringes (**Figure 6d**).

Apart from morphological analysis, common practices involving HRTEM micrograph include the validation of structural analysis from XRD [32]. For instance, in this work, the measured lattice distance was comparable with the d-spacing value, thus supporting the initial XRD evaluation by the author. As an example, lattice fringes of anatase (0.347 nm) were evaluated from the HRTEM images (**Figure 6d**), indicating a good correlation to the values attained from the structural analysis [41]. Other than single-phase studies, such approaches were also widely applied in investigating mixtures of TiO_2 polymorphs [58]. This kind of evaluation was indeed to further prove the co-existence of the phases in the TiO_2 mixtures [59]. It

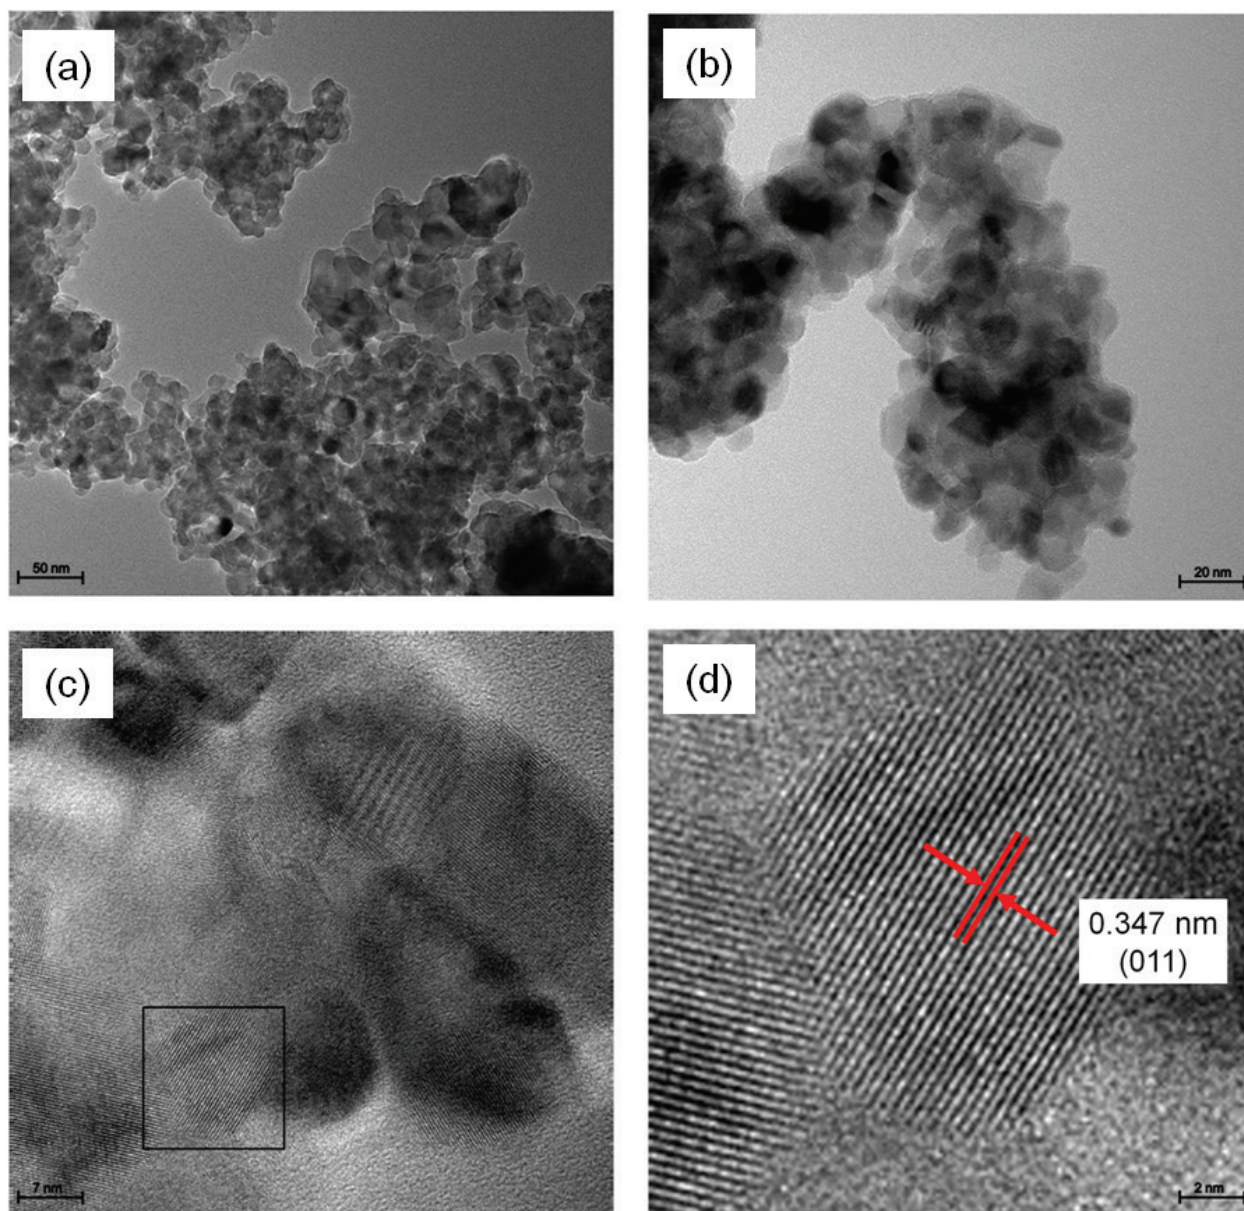


Figure 6. TEM and HRTEM images of TiO₂ nanoparticles synthesised by centrifuge sol-gel method at magnification of (a) 97 kx, (b) 195 kx, (c) 610 kx and (d) magnified image of selected square in (c). Reprinted with permission from Ref. [41]. Copyright 2015, Elsevier.

was clear that HRTEM provides a direct relation between the qualitative analysis (from the images) and the quantitative analysis (structural parameters) from the XRD. In the context of sol-gel synthesis, this clearly opened up more plausible explanation when investigating and characterising TiO₂ nanoparticles.

5.3. Elemental analysis

Parallel to FESEM and HRTEM, the electron dispersive X-ray (EDX) paired to the equipment can simultaneously provide the elemental analysis based on the emitted characteristic X-rays. Area scan EDX is commonly practised in providing the overall elemental analysis of TiO₂

nanoparticles due to the involvement of only single phase [41]. The elemental analysis generally follows subsequently after FESEM or HRTEM characterisation by employing the micrograph selected by the two techniques.

In sample preparation, suitable coating elements should be carefully selected to avoid coatings being detected by EDX to avoid misleading analysis. The EDX analysis provides elemental data strictly on atomic behaviour as opposed to molecular information [60]. The information from area under the EDX spectrum, the accelerating voltage and sensitivity factor were mathematically translated into the elemental information consisting of the atomic percent (at. %) and the weight percent (wt. %) values.

For instance, the elemental analyses conducted on the SEM micrograph were used to confirm the existence of titanium and oxygen in the synthesised TiO_2 nanoparticles (**Figure 7a–f**) [41]. In general, such presence of the particular Ti and O element from the EDX spectrum also highly support other characterisation especially the phase and structural analysis [61]. Additionally, the EDX analysis is useful in explaining the effects of certain parameters on

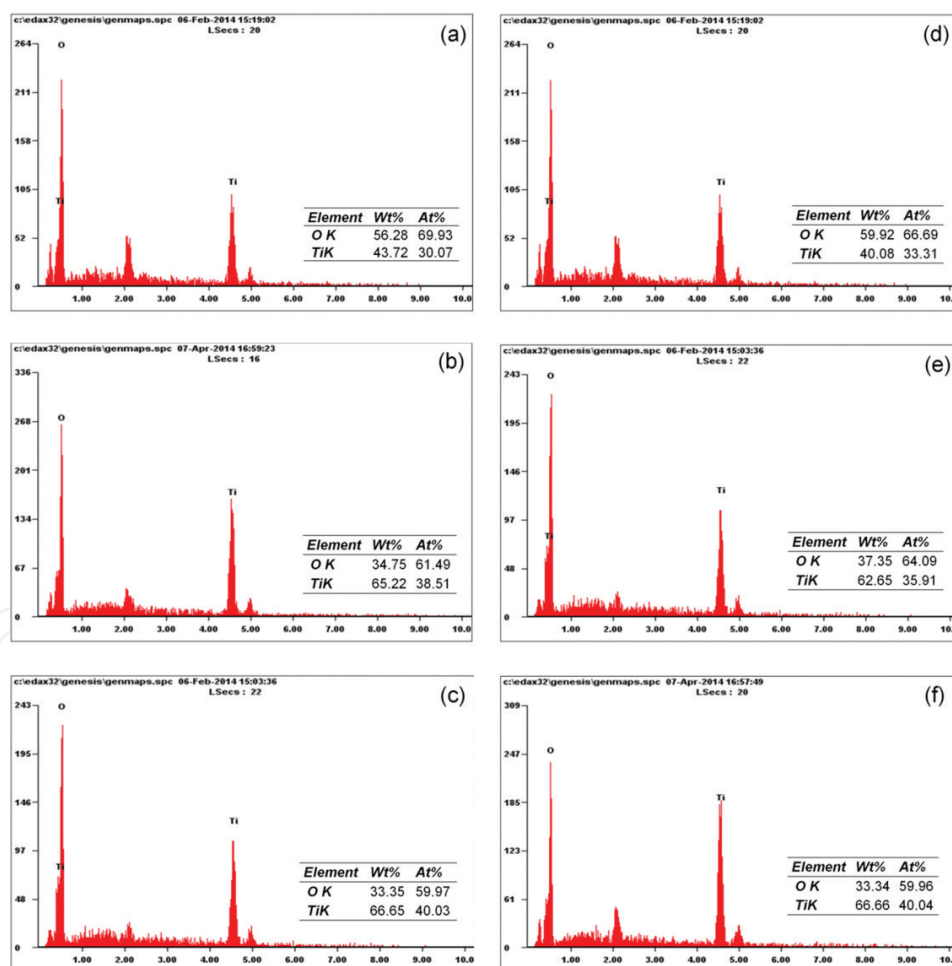


Figure 7. EDX spectrum of the TiO_2 nanoparticles, obtained by centrifuge and calcination at (a) 0°C, (b) 500°C and (c) 600°C, by storage and calcination at (d) 0°C, (e) 500°C and (f) 600°C temperature under ambient atmosphere. Reprinted with permission from Ref. [41]. Copyright 2015, Elsevier.

the corresponding elements such as heat treatment [41]. As an example, the variations on the elemental composition from the EDX spectra obtained in this work explained the influence of calcination temperatures on the resultant TiO₂ nanoparticles. It was clearly observed that higher calcination temperature depleted the oxygen content in the EDX spectra. As current TiO₂ nanoparticles synthesis by the sol-gel involves various changes in chemical parameters, the EDX acts as an important tool to validate the presence/absence of any additional elements from such a complexity. This can be viewed from the work by Martins et al. [62], where the EDX analysis was used to investigate TiO₂ nanoparticles synthesised with the addition of activated carbon. The presence of oxygen, titanium and carbon on the EDX patterns in such cases confirmed the elements presence on the material surface, which in turn indicates the occurrence of carbon reaction during the synthesis process.

6. Particle size analysis

Size determination of TiO₂ nanoparticles was highly practised in conjunction to other characterisation methods. This analysis is significantly crucial as the size factor greatly influences the end properties of TiO₂ nanoparticles. There are few available techniques that allow such analysis to be conducted on the synthesised TiO₂ nanoparticles. However, each selected application is mainly dependent on the research requirement and suitability.

Size determination through FESEM and HRTEM is commonly practised and utilised. The drawback is the need to carry out the initial morphology observation before the actual size determination. A more straightforward approach can be espoused through the use of the particle size analyzer. For example, the use of laser diffraction provides a fast and reproducible particle size analysis [63]. To aid the analysis, current practices are commonly incorporated in the preliminary dispersion process, which helps eliminate agglomeration issues of TiO₂ nanoparticles [64]. Other methods include the electrospray scanning mobility particle sizer (ES-SMPS) and the dynamic light scattering (DLS). As the DLS is suitable for evaluating hydrodynamic radius of particles, ES-SMPS was proven to yield reliable size distribution of nanoparticles larger than 5 nm [65].

A good example of the reliability of the technique can be observed from the investigation on the particle size by Abbas et al. [66], which employed the ES-SMPS method. In the report, high reproducibility of the particle size measurement had been obtained with negligible variations for all TiO₂ nanoparticles. The importance of the consistency is mainly to provide an accurate interpretation on the research parameters. For instance, in this work, the size distribution plotted from the reliable data of ES-SMPS evaluation reflects solely on the influence of the storage condition towards the resultant particle size (**Figure 8a, b**). However, recent work in size determination of TiO₂ nanoparticles mostly presents the measurement obtained from SEM/HRTEM micrographs [57, 67]. Although the processes are more convenient due to the readily available images from SEM/HRTEM, the average size obtained was limited to the particles' presence in the micrograph. Unlike from the particle size analyzer, larger samples quantity can be analysed, thus practically representing better average size value of TiO₂ nanoparticles.

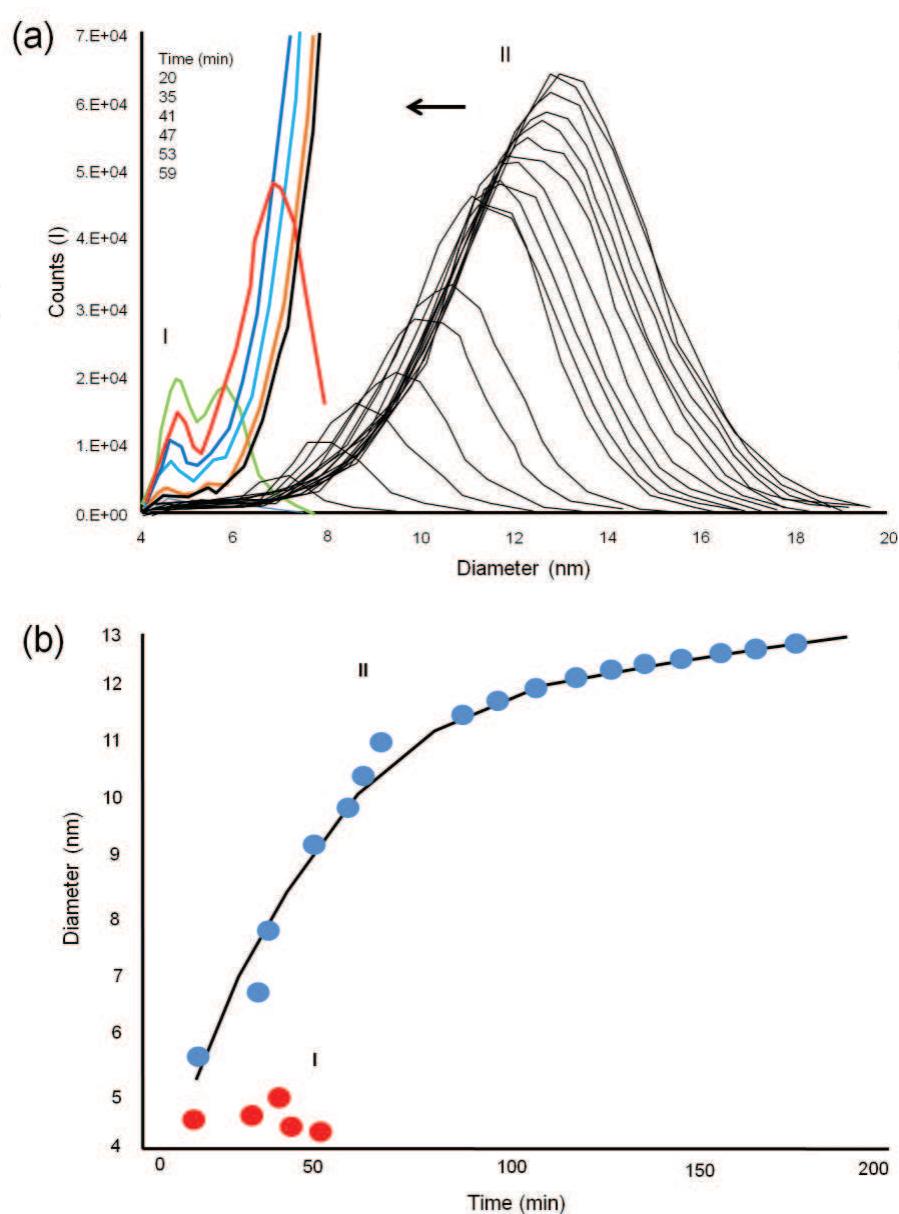


Figure 8. Particle size distribution obtained by the ES-SMPS method for (a) growth over the period of 200 min (II). The data for short times are enlarged by a factor of 10 (I), (b) the changes in the average diameter of the particles during growth. Reprinted with permission from Ref. [66]. Copyright 2011, Elsevier.

Considering the one-step approach rather than measurement from the image (two steps: imaging from SEM/HRTEM then measurement), the particle size analyzer is most suitable for research work focusing on particle size, in addition to higher reliability and accuracy.

7. Conclusion and perspective

Driven by the potential of TiO_2 nanoparticles, continuous development involving numerous research works is expected to rapidly increase in the future. The versatility provided by the

sol-gel method makes these efforts to synthesise TiO₂ nanoparticles better and more relevant, considering the demands in the current applications. Parallel to the research and development process, characterisation of the synthesised TiO₂ nanoparticles is unavoidable. Despite the large availability of experimental alternatives, characterisation methods such as phase, structural, morphologies and size analysis were highly popular among researchers in different TiO₂-related fields. It is apparent that the characterisation techniques will be constantly used in research studies of TiO₂ nanoparticles.

For future work, it is suggested that the studies on the synthesised TiO₂ nanoparticles should be augmented towards structural modelling and simulation. With recent literatures focusing on the use of dopants, such theoretical works are essential in structurally visualising the doping mechanism. This is practically more significant in terms of discussing the performance and properties of the synthesised TiO₂ nanoparticles. Due to advances in computers and software technologies, the properties of the modelled TiO₂ nanoparticles can be completely simulated. Thus, another interesting approach would be to provide a comparison between the generated properties with the results from the experimental work. Additionally, simulation works can eventually show the potential of a particular formulation, thus providing an insight for researchers before venturing into the actual synthesis of TiO₂ nanoparticles.

Acknowledgements

M.Z.Y. would like to acknowledge the MyBrain15 Fellowship scheme. The authors appreciate the financial support provided by the USM-RUI grant (1001/PBahan/814262).

Author details

Muhamad Zamri Yahaya¹, Mohd Asyadi Azam², Mohd Asri Mat Teridi³, Pramod Kumar Singh⁴ and Ahmad Azmin Mohamad^{1*}

*Address all correspondence to: aam@usm.my

1 School of Materials and Mineral Resources Engineering, Universiti Sains Malaysia, Nibong Tebal, Pulau Pinang, Malaysia

2 Carbon Research Technology Research Group, Advanced Manufacturing Centre, Faculty of Manufacturing Engineering, Universiti Teknikal Malaysia Melaka, Durian Tunggal, Melaka, Malaysia

3 Solar Energy Research Institute, National University of Malaysia (UKM), Bangi, Selangor Darul Ehsan, Malaysia

4 Material Research Laboratory, School of Basic Sciences & Research, Sharda University, Greater Noida, India

References

- [1] Lee Y, Chae J, Kang M. Comparison of the photovoltaic efficiency on DSSC for nanometer sized TiO_2 using a conventional sol-gel and solvothermal methods. *Journal of Industrial and Engineering Chemistry*. 2010;**16**:609-614. DOI: <http://dx.doi.org/10.1016/j.jiec.2010.03.008>
- [2] Metzler DM, Li M, Erdem A, Huang C. Responses of algae to photocatalytic nano- TiO_2 particles with an emphasis on the effect of particle size. *Chemical Engineering Journal*. 2011;**170**:538-546. DOI: <http://dx.doi.org/10.1016/j.cej.2011.02.002>
- [3] Panda SK, Yoon Y, Jung HS, Yoon W-S, Shin H. Nanoscale size effect of titania (anatase) nanotubes with uniform wall thickness as high performance anode for lithium-ion secondary battery. *Journal of Power Sources*. 2012;**204**:162-167. DOI: <http://dx.doi.org/10.1016/j.jpowsour.2011.12.048>
- [4] Tang Y, Li G, Pan Y. Effects of TiO_2 nanoparticles addition on microstructure, microhardness and tensile properties of Sn-3.0 Ag-0.5 Cu-x TiO_2 composite solder. *Materials & Design*. 2014;**55**:574-582. DOI: <http://dx.doi.org/10.1016/j.matdes.2013.10.033>
- [5] Wu S, Weng Z, Liu X, Yeung K, Chu P. Functionalized TiO_2 based nanomaterials for biomedical applications. *Advanced Functional Materials*. 2014;**24**:5464-5481. DOI: 10.1002/adfm.201400706
- [6] Wu L, Buchholz D, Bresser D, Chagas LG, Passerini S. Anatase TiO_2 nanoparticles for high power sodium-ion anodes. *Journal of Power Sources*. 2014;**251**:379-385. DOI: <http://dx.doi.org/10.1016/j.jpowsour.2013.11.083>
- [7] Sadovnikov S, Gusev A. Chemical deposition of nanocrystalline lead sulfide powders with controllable particle size. *Journal of Alloys and Compounds*. 2014;**586**:105-112. DOI: <http://dx.doi.org/10.1016/j.jallcom.2013.10.008>
- [8] Kubiak P, Geserick J, Hüsing N, Wohlfahrt-Mehrens M. Electrochemical performance of mesoporous TiO_2 anatase. *Journal of Power Sources*. 2008;**175**:510-516. DOI: <http://dx.doi.org/10.1016/j.jpowsour.2007.09.044>
- [9] Dislich H. New routes to multicomponent oxide glasses. *Angewandte Chemie International Edition in English*. 1971;**10**:363-370. DOI: 10.1002/anie.197103631
- [10] Kumar SG, Rao KK. Polymorphic phase transition among the titania crystal structures using a solution-based approach: From precursor chemistry to nucleation process. *Nanoscale*. 2014;**6**:11574-11632. DOI: 10.1039/C4NR01657B
- [11] Mahshid S, Ghamsari MS, Askari M, Afshar N, Lahuti S. Synthesis of TiO_2 nanoparticles by hydrolysis and peptization of titanium isopropoxide solution. *Journal of Materials Processing Technology*. 2007;**189**:296-300. DOI: <http://dx.doi.org/10.1016/j.jmatprotec.2007.01.040>

- [12] Latt KK, Kobayashi T. TiO₂ nanosized powders controlling by ultrasound sol-gel reaction. *Ultrasonics Sonochemistry*. 2008;**15**:484-491. DOI: <http://dx.doi.org/10.1016/j.ultsonch.2007.08.001>
- [13] Loryuenyong V, Angamnuaysiri K, Sukcharoenpong J, Suwannasri A. Sol-gel derived mesoporous titania nanoparticles: Effects of calcination temperature and alcoholic solvent on the photocatalytic behavior. *Ceramics International*. 2012;**38**:2233-2237. DOI: <http://dx.doi.org/10.1016/j.ceramint.2011.10.072>
- [14] Kumar SG, Devi LG. Review on modified TiO₂ photocatalysis under UV/visible light: Selected results and related mechanisms on interfacial charge carrier transfer dynamics. *Journal of Physical Chemistry A*. 2011;**115**:13211-13241. DOI: 10.1021/jp204364a
- [15] Daghrir R, Drogui P, Robert D. Modified TiO₂ for environmental photocatalytic applications: A review. *Industrial & Engineering Chemistry Research*. 2013;**52**:3581-3599. DOI: 10.1021/ie303468t
- [16] Ni M, Leung MKH, Leung DY, Sumathy K. A review and recent developments in photocatalytic water-splitting using TiO₂ for hydrogen production. *Renewable and Sustainable Energy Reviews*. 2007;**11**:401-425. DOI: <http://dx.doi.org/10.1016/j.rser.2005.01.009>
- [17] Diebold U. Structure and properties of TiO₂ surfaces: A brief review. *Applied Physics A: Materials Science & Processing*. 2003;**76**:681-687. DOI: 10.1007/s00339-002-2004-5
- [18] Gupta SM, Tripathi M. A review of TiO₂ nanoparticles. *Chinese Science Bulletin*. 2011;**56**:1639-1657. DOI: 10.1007/s11434-011-4476-1
- [19] Macwan D, Dave PN, Chaturvedi S. A review on nano-TiO₂ sol-gel type syntheses and its applications. *Journal of Materials Science*. 2011;**46**:3669-3686. DOI: 10.1007/s10853-011-5378-y
- [20] Gupta SM, Tripathi M. A review on the synthesis of TiO₂ nanoparticles by solution route. *Central European Journal of Chemistry*. 2012;**10**:279-294. DOI: 10.2478/s11532-011-0155-y
- [21] Reyes-Coronado D, Rodríguez-Gattorno G, Espinosa-Pesqueira ME, Cab C, De Coss R, Oskam G. Phase-pure TiO₂ nanoparticles: Anatase, brookite and rutile. *Nanotechnology*. 2008;**19**:145605. DOI: <https://doi.org/10.1088/0957-4484/19/14/145605>
- [22] Liao D, Wu G, Liao B. Zeta potential of shape-controlled TiO₂ nanoparticles with surfactants. *Colloids and Surfaces A*. 2009;**348**:270-275. DOI: <http://dx.doi.org/10.1016/j.colsurfa.2009.07.036>
- [23] Fang C-S, Chen YW. Preparation of titania particles by thermal hydrolysis of TiCl₄ in n-propanol solution. *Materials Chemistry and Physics*. 2003;**78**:739-745. DOI: [http://dx.doi.org/10.1016/S0254-0584\(02\)00416-9](http://dx.doi.org/10.1016/S0254-0584(02)00416-9)
- [24] Németh Z, Horváth E, Magrez A, Réti B, Berki P, Forró L, Hernádi K. Preparation of titania covered multi-walled carbon nanotube thin films. *Materials & Design*. 2015;**86**:198-203. DOI: <http://dx.doi.org/10.1016/j.matdes.2015.07.048>

- [25] Liu AR, Wang SM, Zhao YR, Zhen Z. Low-temperature preparation of nanocrystalline TiO_2 photocatalyst with a very large specific surface area. *Materials Chemistry and Physics*. 2006;**99**:131-134. DOI: <http://dx.doi.org/10.1016/j.matchemphys.2005.10.003>
- [26] Vorkapic D, Matsoukas T. Effect of temperature and alcohols in the preparation of titania nanoparticles from alkoxides. *Journal of the American Ceramic Society*. 1998;**81**:2815-2820. DOI: [10.1111/j.1151-2916.1998.tb02701.x](http://dx.doi.org/10.1111/j.1151-2916.1998.tb02701.x)
- [27] Brinker CJ, Scherer GW. *Sol-gel Science: The Physics and Chemistry of Sol-gel Processing*. 1st ed. USA: Academic Press; 2013. p. 912 DOI: <http://dx.doi.org/10.1016/B978-0-08-057103-4.50007-6>
- [28] Watson SS, Beydoun D, Scott JA, Amal R. The effect of preparation method on the photoactivity of crystalline titanium dioxide particles. *Chemical Engineering Journal*. 2003;**95**:213-220. DOI: [http://dx.doi.org/10.1016/S1385-8947\(03\)00107-4](http://dx.doi.org/10.1016/S1385-8947(03)00107-4)
- [29] Look JL, Zukoski C. Colloidal stability and titania precipitate morphology: Influence of short-range repulsions. *Journal of the American Ceramic Society*. 1995;**78**:21-32. DOI: [10.1111/j.1151-2916.1995.tb08356.x](http://dx.doi.org/10.1111/j.1151-2916.1995.tb08356.x)
- [30] Li Z, Zhu Y, Wang J, Guo Q, Li J. Size-controlled synthesis of dispersed equiaxed amorphous TiO_2 nanoparticles. *Ceramics International*. 2015;**41**:9057-9062. DOI: <http://dx.doi.org/10.1016/j.ceramint.2015.03.278>
- [31] Naghibi S, Sani MAF, Hosseini HRM. Application of the statistical Taguchi method to optimize TiO_2 nanoparticles synthesis by the hydrothermal assisted sol-gel technique. *Ceramics International*. 2014;**40**:4193-4201. DOI: <http://dx.doi.org/10.1016/j.ceramint.2013.08.077>
- [32] Liang D, Cui C, Hu H, Wang Y, Xu S, Ying B, Li P, Lu B, Shen H. One-step hydrothermal synthesis of anatase TiO_2 /reduced graphene oxide nanocomposites with enhanced photocatalytic activity. *Journal of Alloys and Compounds*. 2014;**582**:236-240. DOI: <http://dx.doi.org/10.1016/j.jallcom.2013.08.062>
- [33] Chen C-C, Hu S-H, Fu YP. Effects of surface hydroxyl group density on the photocatalytic activity of Fe^{3+} -doped TiO_2 . *Journal of Alloys and Compounds*. 2015;**632**:326-334. DOI: <http://dx.doi.org/10.1016/j.jallcom.2015.01.206>
- [34] Shen P-S, Tai Y-C, Chen P, Wu Y-C. Clean and time-effective synthesis of anatase TiO_2 nanocrystalline by microwave-assisted solvothermal method for dye-sensitized solar cells. *Journal of Power Sources*. 2014;**247**:444-451. DOI: <http://dx.doi.org/10.1016/j.jpowsour.2013.08.104>
- [35] He F, Ma F, Li J, Li T, Li G. Effect of calcination temperature on the structural properties and photocatalytic activities of solvothermal synthesized TiO_2 hollow nanoparticles. *Ceramics International*. 2014;**40**:6441-6446. DOI: <http://dx.doi.org/10.1016/j.ceramint.2013.11.094>
- [36] Maurya A, Chauhan P, Mishra SK, Srivastava RK. Structural, optical and charge transport study of rutile TiO_2 nanocrystals at two calcination temperatures. *Journal of Alloys and Compounds*. 2011;**509**:8433-8440. DOI: <http://dx.doi.org/10.1016/j.jallcom.2011.05.108>

- [37] Gao Y, Wang H, Wu J, Zhao R, Lu Y, Xin B. Controlled facile synthesis and photocatalytic activity of ultrafine high crystallinity TiO₂ nanocrystals with tunable anatase/rutile ratios. *Applied Surface Science*. 2014;**294**:36-41. DOI: <http://dx.doi.org/10.1016/j.apsusc.2013.12.107>
- [38] Banerjee AN, Hamnabard N, Joo SW. A comparative study of the effect of Pd-doping on the structural, optical, and photocatalytic properties of sol-gel derived anatase TiO₂ nanoparticles. *Ceramics International*. 2016. DOI: <http://dx.doi.org/10.1016/j.ceramint.2016.04.128>
- [39] Husain S, Alkhtaby LA, Giorgetti E, Zoppi A, Miranda MM. Investigation of the role of iron doping on the structural, optical and photoluminescence properties of sol-gel derived TiO₂ nanoparticles. *Journal of Luminescence*. 2016;**172**:258-263. DOI: <http://dx.doi.org/10.1016/j.jlumin.2015.12.002>
- [40] Ivanov S, Barylyak A, Besaha K, Dimitrova A, Krischok S, Bund A, Bobitski J. Enhanced lithium ion storage in TiO₂ nanoparticles, induced by sulphur and carbon co-doping. *Journal of Power Sources*. 2016;**326**:270-278. DOI: <http://dx.doi.org/10.1016/j.jpowsour.2016.06.116>
- [41] Yahaya MZ, Abdullah MZ, Mohamad AA. Centrifuge and storage precipitation of TiO₂ nanoparticles by the sol-gel method. *Journal of Alloys and Compounds*. 2015;**651**:557-564. DOI: <http://dx.doi.org/10.1016/j.jallcom.2015.08.110>
- [42] Vinogradov AV, Vinogradov VV. Low-temperature sol-gel synthesis of crystalline materials. *Royal Society of Chemistry Advances*. 2014;**4**:45903-45919. DOI: 10.1039/C4RA04454A
- [43] Wang C-L, Hwang W-S, Chu H-L, Lin H-J, Ko H-H, Wang M-C. Kinetics of anatase transition to rutile TiO₂ from titanium dioxide precursor powders synthesized by a sol-gel process. *Ceramics International*. 2016;**42**:13136-13143. DOI: <http://dx.doi.org/10.1016/j.ceramint.2016.05.101>
- [44] Sarma BK, Pal AR, Bailung H, Chutia J. Effect of post-deposition annealing on the growth of nanocrystalline TiO₂ thin films and elastic anisotropy of rutile phase at different temperatures. *Journal of Alloys and Compounds*. 2013;**577**:261-268. DOI: <http://dx.doi.org/10.1016/j.jallcom.2013.05.137>
- [45] Potlog T, Dobromir M, Luca D, Onufrijevs P, Medvids A, Shamardin A. Rutile to anatase phase transition in TiO₂: Nb thin films by annealing in H₂ atmosphere. *Current Applied Physics*. 2016;**16**:826-829. DOI: <http://dx.doi.org/10.1016/j.cap.2016.04.021>
- [46] Delekar S, Yadav H, Achary S, Meena S, Pawar S. Structural refinement and photocatalytic activity of Fe-doped anatase TiO₂ nanoparticles. *Applied Surface Science*. 2012;**263**:536-545. DOI: <http://dx.doi.org/10.1016/j.apsusc.2012.09.102>
- [47] Toby BH. R factors in Rietveld analysis: How good is good enough? *Powder Diffraction*. 2006;**21**:67-70. DOI: <https://doi.org/10.1154/1.2179804>
- [48] Djerdj I, Tonejc A. Structural investigations of nanocrystalline TiO₂ samples. *Journal of Alloys and Compounds*. 2006;**413**:159-174. DOI: <http://dx.doi.org/10.1016/j.jallcom.2005.02.105>

- [49] Masson O, Rieux V, Guinebretière R, Dauger A. Size and shape characterization of TiO_2 aerogel nanocrystals. *Nanostructured Materials*. 1996;**7**:725-731. DOI: [http://dx.doi.org/10.1016/S0965-9773\(96\)00049-9](http://dx.doi.org/10.1016/S0965-9773(96)00049-9)
- [50] Sarkar A, Kannan S. In situ synthesis, fabrication and Rietveld refinement of the hydroxyapatite/titania composite coatings on 316L SS. *Ceramics International*. 2014;**40**:6453-6463. DOI: <http://dx.doi.org/10.1016/j.ceramint.2013.11.096>
- [51] Tripathi AK, Mathpal MC, Kumar P, Singh MK, Mishra SK, Srivastava RK, Chung JS, Verma G, Ahmad M, Agarwal A. Synthesis based structural and optical behavior of anatase TiO_2 nanoparticles. *Materials Science in Semiconductor Processing*. 2014;**23**:136-143. DOI: <http://dx.doi.org/10.1016/j.mssp.2014.02.041>
- [52] Ning F, He Y-B, Li B, Du H, Zhai D, Kang F. Effects of TiO_2 crystal structure on the performance of $\text{Li}_4\text{Ti}_5\text{O}_{12}$ anode material. *Journal of Alloys and Compounds*. 2012;**513**:524-529. DOI: <http://dx.doi.org/10.1016/j.jallcom.2011.10.109>
- [53] Ghows N, Entezari MH. Ultrasound with low intensity assisted the synthesis of nanocrystalline TiO_2 without calcination. *Ultrasonics Sonochemistry*. 2010;**17**:878-883. DOI: <http://dx.doi.org/10.1016/j.ultsonch.2010.03.010>
- [54] Dittmann R, Wintermantel E, Graule T. Sintering of nano-sized titania particles and the effect of chlorine impurities. *Journal of the European Ceramic Society*. 2013;**33**:3257-3264. DOI: <http://dx.doi.org/10.1016/j.jeurceramsoc.2013.05.028>
- [55] Khatun N, Rini E, Shirage P, Rajput P, Jha S, Sen S. Effect of lattice distortion on bandgap decrement due to vanadium substitution in TiO_2 nanoparticles. *Materials Science in Semiconductor Processing*. 2016;**50**:7-13. DOI: <http://dx.doi.org/10.1016/j.mssp.2016.04.002>
- [56] Vranješ M, Šaponjić ZV, Živković LS, Despotović VN, Šojić DV, Abramović BF, Čomor MI. Elongated titania nanostructures as efficient photocatalysts for degradation of selected herbicides. *Applied Catalysis B-Environmental*. 2014;**160**:589-596. DOI: <http://dx.doi.org/10.1016/j.apcatb.2014.06.005>
- [57] Farbod M, Khademalrasool M. Synthesis of TiO_2 nanoparticles by a combined sol-gel ball milling method and investigation of nanoparticle size effect on their photocatalytic activities. *Powder Technology*. 2011;**214**:344-348. DOI: <http://dx.doi.org/10.1016/j.powtec.2011.08.026>
- [58] Wetchakun N, Incessungvorn B, Wetchakun K, Phanichphant S. Influence of calcination temperature on anatase to rutile phase transformation in TiO_2 nanoparticles synthesized by the modified sol-gel method. *Materials Letters*. 2012;**82**:195-198. DOI: <http://dx.doi.org/10.1016/j.matlet.2012.05.092>
- [59] Mutuma BK, Shao GN, Kim WD, Kim HT. Sol-gel synthesis of mesoporous anatase-brookite and anatase-brookite-rutile TiO_2 nanoparticles and their photocatalytic properties. *Journal of Colloid and Interface Science*. 2015;**442**:1-7. DOI: <http://dx.doi.org/10.1016/j.jcis.2014.11.060>

- [60] Ngo PD. Energy dispersive spectroscopy. In: Lawrence C, editor. Failure Analysis of Integrated Circuits. 1st ed. USA: Springer; 1999. p. 205-215. DOI: 10.1007/978-1-4615-4919-2_12
- [61] Dwivedi C, Raje N, Nuwad J, Kumar M, Bajaj PN. Synthesis and characterization of mesoporous titania microspheres and their applications. Chemical Engineering Journal. 2012;193:178-186. DOI: <http://dx.doi.org/10.1016/j.cej.2012.04.029>
- [62] Martins AC, Cazetta AL, Pezoti O, Souza JR, Zhang T, Pilau EJ, Asefa T, Almeida VC. Sol-gel synthesis of new TiO₂/activated carbon photocatalyst and its application for degradation of tetracycline. Ceramics International. 2016. DOI: <http://dx.doi.org/10.1016/j.ceramint.2016.12.088>
- [63] Black DL, McQuay MQ, Bonin MP. Laser-based techniques for particle-size measurement: A review of sizing methods and their industrial applications. Progress in Energy and Combustion Science. 1996;22:267-306. DOI: [http://dx.doi.org/10.1016/S0360-1285\(96\)00008-1](http://dx.doi.org/10.1016/S0360-1285(96)00008-1)
- [64] Song D, Hatami M, Wang Y, Jing D, Yang Y. Prediction of hydrodynamic and optical properties of TiO₂/water suspension considering particle size distribution. International Journal of Heat and Mass Transfer. 2016;92:864-876. DOI: <http://dx.doi.org/10.1016/j.ijheatmasstransfer.2015.08.101>
- [65] Lenggoro IW, Xia B, Okuyama K, de la Mora JF. Sizing of colloidal nanoparticles by electrospray and differential mobility analyzer methods. Langmuir. 2002;18:4584-4591. DOI: 10.1021/la015667t
- [66] Abbas Z, Holmberg JP, Hellström AK, Hagström M, Bergenholtz J, Hassellöv M, Ahlberg E. Synthesis, characterization and particle size distribution of TiO₂ colloidal nanoparticles. Colloids and Surfaces A. 2011;384:254-261. DOI: <http://dx.doi.org/10.1016/j.colsurfa.2011.03.064>
- [67] Jiang Z-Z, Gu D-M, Wang Z-B, Qu W-L, Yin G-P, Qian K-J. Effects of anatase TiO₂ with different particle sizes and contents on the stability of supported Pt catalysts. Journal of Power Sources. 2011;196:8207-8215. DOI: <http://dx.doi.org/10.1016/j.jpowsour.2011.05.063>

IntechOpen

