

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

6,900

Open access books available

185,000

International authors and editors

200M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.
For more information visit www.intechopen.com



Biocompatible Magic Sized Quantum Dots: Luminescent Markers and Probes

Anielle Christine Almeida Silva,
Lucas Ian Veloso Correia,
Marcelo José Barbosa Silva,
Mariana Alves Pereira Zóia,
Fernanda Van Petten Vasconcelos Azevedo,
Jéssica Peixoto Rodrigues, Luiz Ricardo Goulart,
Veridiana de Melo Ávila and Noelio Oliveira Dantas

Additional information is available at the end of the chapter

<http://dx.doi.org/10.5772/intechopen.72841>

Abstract

Nanoscience and nanobiotechnology have aroused great academic and technological interest. Works relating biomaterials at the nanoscale can reach new biotechnologies and help in the development and use of tools for bioimage and diagnosis applications. In this work we demonstrated the advantages of magic sized quantum dots as luminescent markers and probes to bioimage applications. The visualization of MSQDs bioconjugated with biological probes in cells were performed at periods greater than 2 h, and visualization with no commercial dye would not be possible. Therefore, we demonstrated that these biocompatible nanocrystals are luminescent markers and probes to diagnosis.

Keywords: nanocrystals, biocompatibility, luminescence, bioconjugation, probes

1. Introduction

Nanotechnology in life sciences has as one of its objectives to diagnose diseases in a precise, fast and effective way, offering improvements to the existing diagnostic methods. In this sense, several nanomaterials have been studied and developed to benefit the biomedical technologies.

One of the nanomaterials with high potential for application in nanomedicine is the quantum dot, which is a semiconductor nanoparticle. This nanoparticle is a promising material for the diagnosis and understanding of cell biology, being used both for image generation and for detection of signals through [1–3].

Measures based on fluorescence have biochemical specificity and high sensitivity. There is considerable interest in the use of quantum dots as inorganic fluorophores because they have significant advantages over conventionally used fluorescent markers. For this, it is necessary that these nanoparticles are biocompatible so that they are conjugated properly to biological molecules, by means of bioconjugation techniques [4–7].

In cell biology it has been a practice to use fluorescent labels such as organic dyes, coordinating compounds of lanthanide ions and recombinant fluorescent proteins [8–12]. Organic fluorophores are used as molecular markers to identify structural compartments, molecules, or organelles. These fluorophores can be linked (conjugated) to the target directly or indirectly through conjugation with antibodies and other molecules that bind secondarily to the target. The fluorophore DAPI (4'6-diamidino-2-phenylindole), for example, has affinity for DNA molecules, and is commonly employed for labeling in cell nuclei.

Although they are widely used in the labeling of cellular structures, tissues and organisms, some limitations of these fluorophores should be considered. An irreversible photochemical reaction common to fluorophores is the photobleaching or photodegradation caused by the photochemical destruction of the fluorophore, causing them to irreversibly lose their fluorescence, either after being excited or after a few minutes, depending on the intensity of the source of excitation [13–15].

In this way, samples stained with such dyes need to be kept in dark environments and the microscopy section needs to be performed quickly, making it difficult to monitor a whole cellular process. In addition to photodegradation, other disadvantages involved in these types of labeling are: high toxicity and cell death using ultraviolet (UV) [16–18]. Fluorescent proteins such as GFP (Green Fluorescent Protein) are apparently non-toxic, but may induce undesired cellular processes, and it is a laborious technique.

Due to the disadvantages in the use of conventional fluorophores, several researches have been directed towards the development and reproducibility in the synthesis of nanocrystals for use in bio detection and bioimaging [19–21]. In particular, quantum dots (QDs) have been extensively studied because they exhibit high absorption and the absorption and emission spectra are easily controlled as a function of size, shape and crystalline phase [15, 19, 22], this enables tuning of the emission length as well as high efficiency. Like this, multicolored images can be obtained with the same material when it has different diameters [19, 21, 23, 24].

Unlike most conventional dyes which have a narrow absorption spectrum, the QDs have the additional advantage that a single laser can excite luminescence at different wavelengths while each organic dye must be excited over a long length of single wave and well defined [25–29].

The studies and applications of QDs reveal their efficacy as new luminescent probes for diagnostic purposes, enabling real-time acquisition of a single cell surface receptor, as well as the development of non-invasive models for the detection of small tumors [30]. Another highlight is the application of the QDs in living cells and tissues. Depending on the binder attached to

the quantum dots, they can be injected into cells by the micro injection technique. Once inside the cells, the QDs biochemical reaction [27, 31–33].

Recently, it has been shown that the magic-sized quantum dots (MSQDs) present great advantages in the medical and biological area. These MSQDs are quantum dots with extremely small sizes (<2 nm) and physical properties that are completely different from those presented by QDs [34, 35]. These MSQDs present thermodynamically stable structures, wide luminescence range, great size stability over time, relatively narrow absorption spectra, and heterogenic growth [36, 37]. The term magic size is related to a (magic) number of atoms in the structure that makes MSQDs extremely stable. The wide luminescence spectrum occurs because MSQDs have internal atomic defects [38].

The MSQDs can be important tools in the investigation of metastases and have been proposed as vehicles for administering drugs that can initiate certain photoactivated chemical reactions due to highly stable luminescence over time [39]. The cultures of cells marked with MSQDs continue to maintain their functions, remaining viable for analysis for prolonged periods of time [39–42].

In this chapter we highlight the advantages of MSQDs as a biocompatible luminescent marker and its use as a specific probe. In the biological labeling assays, we use CdSe/CdS MSQDs bioconjugated with Pepstatin A, BnSP-6, BthTx-II and a specific BC Fab antibody to allow its tracking within the cell and, in addition, to verify the specificity of this treatment for breast cancer cells.

2. Magic quantum dots luminescent markers and probes

Figure 1a shows the absorption and emission spectra of CdSe/CdS MSQDs that observed a narrow band around 428 nm and a broad emission spectrum, respectively [41]. This broad emission is characteristics of the MSQDs and that is of great applicability in biological processes, enabling their visualization in different detection channels, varying from blue to red (**Figure 1a**) [43]. Using the three detection filters, the fluorescence images of the MSQDs in the cells were recorded (**Figure 1b–d**) [39–41].

One of the major problems of organic fluorophores besides cytotoxicity is the duration of luminescence, making it impossible to trace and observe biological assays as a function of time. Quantum dots present high intensity of luminescence compared to dyes and a monitoring time greater than 2 h, but after this time is observed a drastic decrease of luminescence intensity, that difficult of monitoring. This occurs because QDs interact with cellular proteins and decrease the luminescence intensity over time [17]. However, the high stability of MSQDs allows the highly stable luminescence, even after 36 h, (**Figure 2**) [39].

The fluorescence images of the CdSe MSQDs in HeLa cells after (a) 24 h and (b) 36 h are shown in **Figure 2**. It is verified that even after 36 h it is possible to visualize the luminescence of MSQDs. In **Figure 2(c)** it is shown that the observed luminescence is due to a set of MSQDs and that they were constructed with the CdSe core, a thin layer of CdS and functionalized with hydroxyl groups. These results show that the MSQDs can be used as biocompatible luminescent markers [39].

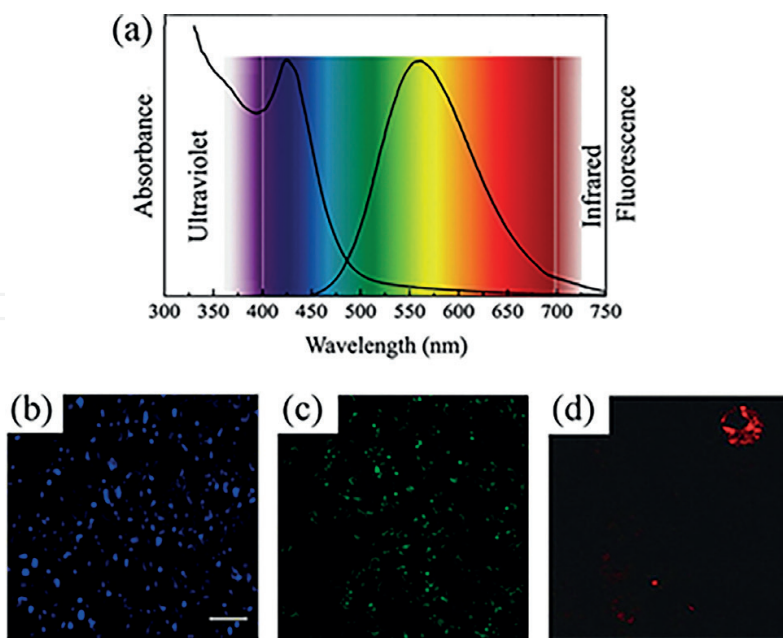


Figure 1. (a) Absorption and fluorescence spectra of CdSe/CdS MSQDs, (b)–(d) fluorescence images of MSQDs in cells using the blue, green and red detection filters, respectively [39–41].

Therefore, the photostable MSQDs allow researchers to investigate the distinct cellular process, in the form of experiments with phagocytosis and vesicles intracellular traffic [44]. Regarding *in vivo* experiments, stable luminescence MSQDs could be used for tumor cells migration since the monitoring could be done for days.

It is crucial the high biocompatibility of MSQDs, in other words, they cannot be harmful to the cells. It is well known that MSQDs have cadmium ions (Cd^{2+}) adsorbed in their superficies. The manipulation of the composition and diameter of core and shell of MSQDs reduce the cellular contact with Cd^{2+} . In this scenario, Cd^{2+} could stimulate various noxious effects as apoptosis, necrosis and DNA damage by the induction of reactive oxygen species production. Such effects extremely change the biology of the cells. For example, in an experiment with phagocytosis and intracellular traffic, apoptotic cells present a deficient phagocytose process which can infer misunderstand able results [39].

To investigate the true cause of the cytotoxic effect of cadmium chalcogenides QDs, we synthesized CdSe MSQDs with different amounts of Cd^{2+} adsorbed on their surface and have shown that this quantity is directly related to cytotoxicity (**Figure 3 a,b**). The biocompatibility is increased with decrease of Cd^{2+} adsorbed on MSQDs surface (**Figure 3b**). In addition, the decrease of Cd^{2+} is confirmed by the lower expression of the protein (**Figure 3c**). Thus, based on this, we developed new synthesis methodologies to develop a CdS shell using the Cd^{2+} adsorbed [45, 46]. Thus, we have shown in our recent studies that this shell increases biocompatibility and has no immunological effects [41].

Figure 4 shows fluorescence images of CdSe/CdS MSQDs alone and bioconjugated Pepstatin A, BnSP-6, BthTx-II and a specific BC Fab antibody in the MDA-MB-23.1 [40, 41]. The fluorescence from MSQDs bioconjugated was detected inside the cells' nuclei compartment of MDA-MB-231. Notably, we verified that the MSQDs alone were not internalized in MDA-MB-231 (**Figure 4a**) [40].

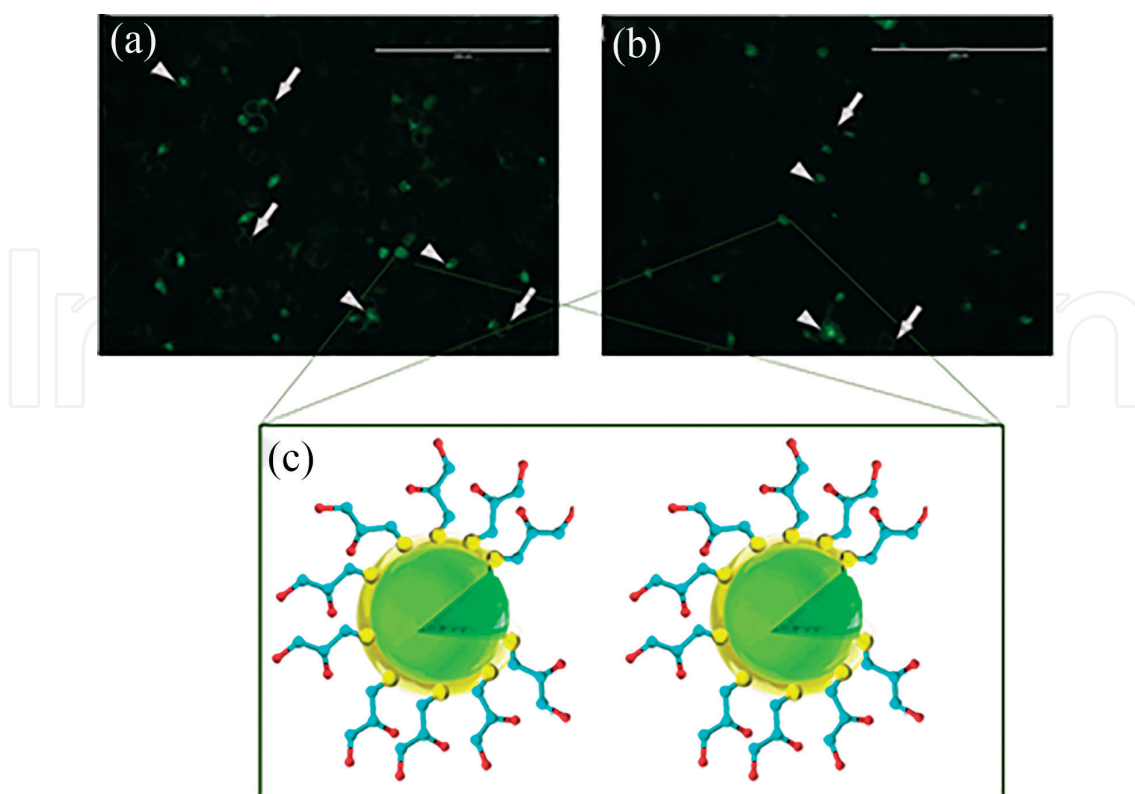


Figure 2. Fluorescent image of incubation with 0.05 M of MSQDs (a) after 24 h and (b) after 36 h. White arrow indicates MSQDs interacted to cellular membrane. Arrows head indicates MSQDs inside the cells. Scale bar = 200 μm. (c) Representation of a set of MSQDs [39].

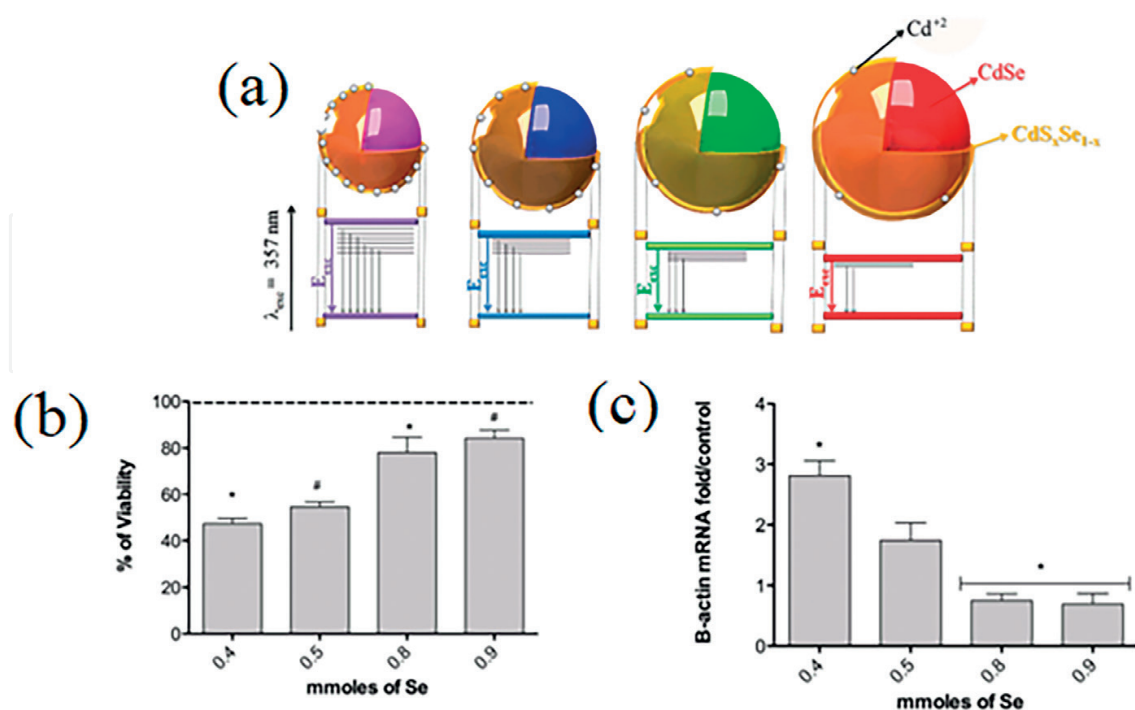


Figure 3. (a) Representation of CdSe MSQDs with different amounts of Cd²⁺ adsorbed on their surface, (b) Viability in function of diminution of Cd²⁺ and (c) B-actin mRNA fold/control in function of diminution of Cd²⁺ (increase of Se).

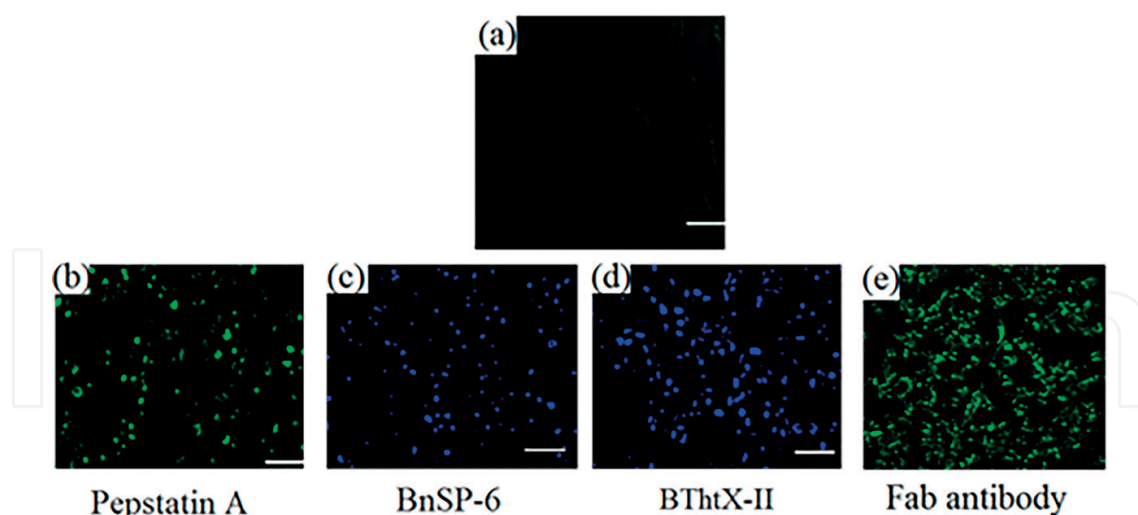


Figure 4. Fluorescence images of (a) CdSe/CdSe MSQDs, bioconjugated (b) Pepstatin in 6 h after treatment, (c) BnSP-6 in 3 h after treatment, (d) BthTx-II in 3 h after treatment and (e) a specific BC Fab antibody in the MDA-MB-23.1 [40, 41].

This result confirms the bioconjugation of the MSQDs with biological probes and in addition, all the assays were performed at periods greater than 2 h, and visualization with no commercial dye would not be possible. Therefore, the group presents experience in the development of new biocompatible luminescent markers specific to each type of treatment.

Author details

Anielle Christine Almeida Silva^{1*}, Lucas Ian Veloso Correia², Marcelo José Barbosa Silva³, Mariana Alves Pereira Zóia⁴, Fernanda Van Petten Vasconcelos Azevedo², Jéssica Peixoto Rodrigues⁴, Luiz Ricardo Goulart⁴, Veridiana de Melo Ávila² and Noelio Oliveira Dantas¹

*Address all correspondence to: aniellechristineas@gmail.com

1 Laboratory of New Insulation and Semiconductor Materials, Institute of Physics, Federal University of Uberlândia, Brazil

2 Laboratory of Biochemistry and Animal Toxins, Institute of Genetics and Biochemistry, Federal University of Uberlândia, Brazil

3 Laboratory of Immunoparasitology, Institute of Biomedical Sciences, Federal University of Uberlândia, Brazil

4 Laboratory of Nanobiotechnology, Institute of Genetics and Biochemistry, Federal University of Uberlândia, Brazil

References

- [1] Du W, Liao L, Yang L, Qin A, Liang A. Aqueous synthesis of functionalized copper sulfide quantum dots as near-infrared luminescent probes for detection of Hg^{2+} , Ag^+ and Au^{3+} . *Scientific Reports*. 2017;7(1):11451
- [2] Liu J, Lv G, Gu W, Li Z, Tang A, Mei L. A novel luminescence probe based on layered double hydroxides loaded with quantum dots for simultaneous detection of heavy metal ions in water. *Journal of Materials Chemistry C*. 2017;5(20):5024-5030
- [3] Ren D, Wang B, Hu C, You Z. Quantum dot probes for cellular analysis. *Analytical Methods*. 2017;9(18):2621-2632
- [4] Yukawa H, Baba Y. *In vivo* fluorescence imaging and the diagnosis of stem cells using quantum dots for regenerative medicine. *Analytical Chemistry*. 2017;89(5):2671-2681
- [5] Kim J, Biondi MJ, Feld JJ, Chan WCW. Clinical validation of quantum dot barcode diagnostic technology. *ACS Nano*. 2016;10(4):4742-4753
- [6] Zhou S, Huo D, Hou C, Yang M, Fa H. Hyaluronan functionalizing QDs as turn-on fluorescent probe for targeted recognition CD44 receptor. *Journal of Nanoparticle Research*, 2017;19(9):319
- [7] Tsuboi S, Sasaki A, Sakata T, Yasuda H, Jin T. Immunoglobulin binding (B1) domain mediated antibody conjugation to quantum dots for in vitro and in vivo molecular imaging. *Chemical Communications*, 2017;9450(53):9450-9453
- [8] Liu J-J, Chang Q, Bao M-M, Yuan B, Yang K, Ma Y-Q. Silicon quantum dots delivered phthalocyanine for fluorescence guided photodynamic therapy of tumor. *Chinese Physics B*, 2017;26(9):98102
- [9] Lv Y, Wu R, Feng K, Li J, Mao Q, Yuan H, Shen H, Chai X, Li LS. Highly sensitive and accurate detection of C-reactive protein by CdSe/ZnS quantum dot-based fluorescence-linked immunosorbent assay. *Journal of Nanobiotechnology*. 2017;15(1):35
- [10] Jiang P, Zhu CN, Zhang ZL, Tian ZQ, Pang DW. Water-soluble Ag_2S quantum dots for near-infrared fluorescence imaging in vivo. *Biomaterials*. 2012;33:5130-5135
- [11] Zhao P, Xu Q, Tao J, Jin Z, Pan Y, Yu C, Yu Z. Near infrared quantum dots in biomedical applications: Current status and future perspective. *Wiley Interdisciplinary Reviews. Nanomedicine and Nanobiotechnology*. 2017;1-16
- [12] Zhu Z-J, Yeh Y-C, Tang R, Yan B, Tamayo J, Vachet RW, Rotello VM. Stability of quantum dots in live cells. *Nature Chemistry*. 2011;3(12):963-968
- [13] Zhou J, Yang Y, Zhang CY. Toward biocompatible semiconductor quantum dots: From biosynthesis and bioconjugation to biomedical application. *Chemical Reviews*. 2015;115(21):11669-11717

- [14] Pelaz B, Alexiou C, Alvarez-Puebla RA, Alves F, Andrews AM, Ashraf S, Balogh LP, Ballerini L, Bestetti A, Brendel C, Bosi S, Carril M, Chan WCW, Chen C, Chen X, Chen X, Cheng Z, Cui D, Du J, Dullin C, Escudero A, Feliu N, Gao M, George M, Gogotsi Y, Grünweller A, Gu Z, Halas NJ, Hampp N, Hartmann RK, Hersam MC, Hunziker P, Jian J, Jiang X, Jungebluth P, Kadhiresan P, Kataoka K, Khademhosseini A, Kopeček J, Kotov NA, Krug HF, Lee DS, Lehr CM, Leong KW, Liang XJ, Ling Lim M, Liz-Marzán LM, Ma X, Macchiarini P, Meng H, Möhwald H, Mulvaney P, Nel AE, Nie S, Nordlander P, Okano T, Oliveira J, Park TH, Penner RM, Prato M, Puntès V, Rotello VM, Samarakoon A, Schaak RE, Shen Y, Sjöqvist S, Skirtach AG, Soliman MG, Stevens MM, Sung HW, Tang BZ, Tietze R, Udugama BN, VanEpps JS, Weil T, Weiss PS, Willner I, Wu Y, Yang L, Yue Z, Zhang Q, Zhang Q, Zhang XE, Zhao Y, Zhou X, Parak WJ. Diverse applications of nanomedicine. *ACS Nano*. 2017;**11**(3):2313-2381
- [15] Wegner KD, Hildebrandt N. Quantum dots: Bright and versatile in vitro and in vivo fluorescence imaging biosensors. *Chemical Society Reviews*. 2015;**44**(14):4792-4834
- [16] Panchuk-Voloshina N, Haugland R, Bishop-Stewart J, Bhalgat M, Millard P, Mao F, Leung W, Haugland R. Alexa dyes, a series of new fluorescent dyes that yield exceptionally bright, photostable conjugates. *Journal of Histochemistry and Cytochemistry*. 1999;**47**:1179-1188
- [17] Resch-Genger U, Grabolle M, Cavaliere-Jaricot S, Nitschke R, Nann T. Quantum dots versus organic dyes as fluorescent labels. *Nature Methods*. 2008;**5**:763-75
- [18] Akinfiev O, Nabiev I, Sukhanova A. New directions in quantum dot-based cytometry detection of cancer serum markers and tumor cells. *Critical Reviews in Oncology/Hematology*. 2013;**86**(1):1-14
- [19] Bera D, Qian L, Tseng TK, Holloway PH. Quantum dots and their multimodal applications: A review. *Materials (Basel)*. 2010;**3**(4):2260-2345
- [20] Biju V, Mundayoor S, Omkumar RV, Anas A, Ishikawa M. Bioconjugated quantum dots for cancer research: Present status, prospects and remaining issues. *Biotechnology Advances*. 2010;**28**(2):199-213
- [21] Matea CT, Mocan T. Quantum dots in imaging , drug delivery and sensor applications. *International Journal of Nanomedicine*. 2017;**12**:5421-5431
- [22] McBride JR, Dukes AD, Schreuder MA, Rosenthal SJ. On ultrasmall nanocrystals. *Chemical Physics Letters*. 2010;**498**(1-3):1-9
- [23] Xing Y, Rao J. Quantum dot bioconjugates for in vitro diagnostics & in vivo imaging. *Cancer Biomarkers*. 2008;**4**(6):307-319
- [24] Petryayeva E, Algar WR, Medintz IL. Quantum dots in bioanalysis: A review of applications across various platforms for fluorescence spectroscopy and imaging. *Applied Spectroscopy*. 2013;**67**(3):215-252
- [25] Alivisatos AP. Semiconductor clusters, quantum nanocrystals, quantum dots. *Science* (80-.). 1996;**271**(5251):933-937

- [26] Sagar D, Cooney R, Sewall S, Dias E, Barsan M, Butler I, Kambhampati P. Size dependent, state-resolved studies of exciton-phonon couplings in strongly confined semiconductor quantum dots. *Physical Review B*. 2008;**77**(23):235321
- [27] Sukhanova A, Nabiev I. Fluorescent nanocrystal quantum dots as medical diagnostic tools. *Expert Opinion on Medical Diagnostics*. 2008;**2**(4)
- [28] Deerinck TJ. The application of fluorescent quantum dots to confocal, multiphoton, and electron microscopic imaging. *Toxicologic Pathology*. 2008;**36**(1):112-116
- [29] Banyai L, Koch SW. *Semiconductor Quantum Dots*. Singapore: World Scientific; 1993
- [30] Goldman ER, Balighian ED, Mattoussi H, Kuno MK, Mauro JM, Tran PT, Andersont GP. Avidin: A natural bridge for quantum dot-antibody conjugates. *Journal of the American Chemical Society*. 2002;**124**(22):6378-6382
- [31] Alivisatos AP, Gu W, Larabell C. Quantum dots as cellular probes. *Annual Review of Biomedical Engineering*. 2005;**7**(1):55-76
- [32] Revon LB, Chiang H-J, Huang Y-W, Chan M-H, Chen H-H, Lee H-J. Cellular internalization of quantum dots mediated by cell-penetrating peptides. *Pharmaceutical Nanotechnology*. 2013;**1**(2):151-161
- [33] Parak WJ, Gerion D, Pellegrino T, Zanchet D, Micheel C, Williams SC, Boudreau R, Le Gros MA, Larabell CA, Alivisatos AP. Biological applications of colloidal nanocrystals. *Nanotechnology*. 2003;**14**:R15-R27
- [34] Bowers MJ, McBride JR, Rosenthal SJ. White-light emission from magic-sized cadmium selenide nanocrystals. *Journal of the American Chemical Society*. 2005;**127**(44):15378-15379
- [35] Kudera S, Zanella M, Giannini C, Rizzo A, Li Y, Gigli G, Cingolani R, Ciccarella G, Spahl W, Parak WJ, Manna L. Sequential growth of magic-size CdSe nanocrystals. *Advanced Materials*. 2007;**19**(4):548-552
- [36] Dukes AD, McBride JR, Rosenthal SJ. Synthesis of magic-sized CdSe and CdTe nanocrystals with diisooctylphosphinic acid. *Chemistry of Materials*. 2010;**22**(23):6402-6408
- [37] Nguyen KA, Day PN, Pachter R. Understanding structural and optical properties of nanoscale CdSe magic-size quantum dots: Insight from computational prediction. *Journal of Physical Chemistry C*. 2010;**114**(39):16197-16209
- [38] Ouyang J et al. Multiple families of magic-sized CdSe nanocrystals with strong bandgap photoluminescence via noninjection one-pot syntheses. *Journal of Physical Chemistry C*. 2008;**112**:13805-13811
- [39] Silva ACA, de Deus SLV, Silva MJB, Dantas NO. Highly stable luminescence of CdSe magic-sized quantum dots in HeLa cells. *Sensors & Actuators, B: Chemical*. 2014;**191**:108-114
- [40] Silva ACA, Azevedo FVPV, Zóia MAP, Rodrigues JP, Dantas NO, Melo VRÁ, Goulart LR. Magic sized quantum dots as a theranostic tool for breast cancer. In: *Recent Studies & Advances in Breast Cancer*. Wilmington: Open Access eBooks; 2017. pp. 1-10

- [41] Silva ACA, Freschi APP, Rodrigues CM, Matias BF, Maia LP, Goulart LR, Dantas NO. Biological analysis and imaging applications of CdSe/CdS_xSe_{1-x}/CdS core-shell magic-sized quantum dot. *Nanomedicine: Nanotechnology, Biology, and Medicine*. 2016;**12**(5):1421-1430
- [42] Silva ACA, Dantas NO, Silva MJB, Spanó MA, Goulart LR. Functional nanocrystals: Towards biocompatibility , nontoxicity and biospecificity. In: *Advances in Biochemistry & Applications in Medicine*. 1st ed. Wilmington: Open Access eBooks; 2017. pp. 1-27
- [43] Harrell SM, McBride JR, Rosenthal SJ. Synthesis of ultrasmall and magic-sized CdSe nanocrystals. *Chemistry of Materials*. 2013;**25**(8):1199-1210
- [44] Kosaka N, McCann TE, Mitsunaga M, Choyke PL, Kobayashi H. Real-time optical imaging using quantum dot and related nanocrystals. *Nanomedicine (London)*. 2010;**5**(5):765-776
- [45] Silva ACA, Neto ESF, da Silva SW, Morais PC, Dantas NO. Modified phonon confinement model and its application to CdSe/CdS core-shell magic-sized quantum dots synthesized in aqueous solution by a new route. *Journal of Physical Chemistry C*. 2013;**117**(4):1904-1914
- [46] Silva ACA, da Silva SW, Morais PC, Dantas NO. Shell thickness modulation in ultrasmall CdSe/CdS_xSe_{1-x}/CdS core/shell quantum dots via 1-thioglycerol. *ACS Nano*. 2014;**8**(2):1913-1922