

# We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

6,900

Open access books available

185,000

International authors and editors

200M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index  
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?  
Contact [book.department@intechopen.com](mailto:book.department@intechopen.com)

Numbers displayed above are based on latest data collected.  
For more information visit [www.intechopen.com](http://www.intechopen.com)



# Progress in Plasma-Assisted Catalysis for Carbon Dioxide Reduction

*Guoxing Chen, Ling Wang,  
Thomas Godfroid and Rony Snyders*

## Abstract

Production of chemicals and fuels based on CO<sub>2</sub> conversion is attracting a special attention nowadays, especially regarding the fast depletion of fossil resources and increase of CO<sub>2</sub> emissions into the Earth's atmosphere. Recently, plasma technology has gained increasing interest as a non-equilibrium medium suitable for CO<sub>2</sub> conversion, which provides a promising alternative to the conventional pathway for greenhouse gas conversion. The combination of plasma and catalysis is of great interest for turning plasma chemistry in applications related to pollution and energy issues. In this chapter a short review of the current progress in plasma-assisted catalytic processes for CO<sub>2</sub> reduction is given. The most widely used discharges for CO<sub>2</sub> conversion are presented and briefly discussed, illustrating how to achieve a better energy and conversion efficiency. The chapter includes the recent status and advances of the most promising candidates (plasma catalysis) to obtain efficient CO<sub>2</sub> conversion, along with the future outlook of this plasma-assisted catalytic process for further improvement.

**Keywords:** green energy, plasma-based CO<sub>2</sub> conversion, plasma catalysis, oxygen vacancies, synergistic effect

## 1. Introduction

The utilization of CO<sub>2</sub> for production of fuels, energy storage media, chemicals or aggregates is attracting interest worldwide due to the essential contribution of the greenhouse gases to the global warming. CO<sub>2</sub> capture and utilization are considered as a promising option for the mitigation of CO<sub>2</sub> emissions, which provides a lower carbon footprint for the synthesis of value-added products than those produced by conventional processes using fossil fuels. In spite of the continuously increasing interest for CO<sub>2</sub> recycling, there are significant challenges to overcome due to its stable molecular structure and low chemical activity. There are several methods that can be used to convert CO<sub>2</sub>, including traditional catalysis, photochemical, biochemical, solar thermochemical, electrochemical and plasma chemical. Snoeckx and Bogaerts recently made a detailed comparison of these technologies as shown in **Table 1** [1]. They concluded that the plasma technology fares very well in this comparison and is quite promising. Indeed, nonthermal plasma has attracted much attention of the scientific community as a non-equilibrium medium suitable for CO<sub>2</sub>

	Use of rare earth metals	Renewable energy	Turnkey process	Conversion and yield	Separation step needed	Oxygenated products (e.g. alcohols, acids)	Investment cost	Operating cost	Overall flexibility
Traditional catalysis	Yes	-	No	High	Yes	Yes	Low	High	Low
Catalysis by MW-heating	Yes	Indirect	No	High	Yes	Yes	Low	Low	Low
Electro-chemical	Yes	Indirect	No <sup>b</sup>	High	Yes <sup>c</sup>	Yes	Low	Low	Medium
Solar thermo-chemical	Yes	Direct	NA	High	No	No	High	Low	Low
Photo-chemical	Yes	Direct <sup>a</sup>	Yes	Low	Yes	Yes	Low	Low	Low
Biochemical	No	Direct <sup>a</sup>	No	Medium	Yes <sup>d</sup>	Yes	High /low	High	Low
Plasma-chemical	No	Indirect	Yes	High	Yes <sup>e</sup>	Yes	Low	Low	High


<sup>a</sup>Bio- and photochemical processes can also rely on indirect renewable energy when they are coupled with artificial lighting.  
<sup>b</sup>Electrochemical cells are turnkey, but generally the cells need to operate at elevated temperatures and the cells are sensitive to on/off fluctuations.  
<sup>c</sup>The need for post-reaction separation for the electrochemical conversion highly depends on the process and cell type used.  
<sup>d</sup>Biochemical CO<sub>2</sub> conversion requires very energy-intensive post-reaction separation and processing steps.  
<sup>e</sup>The need for post-reaction separation for plasma technology highly depends on the process.

**Table 1.**  
Comparing the advantages and disadvantages of the different technologies for CO<sub>2</sub> reduction (adapted from [1]).

conversion, which provides an attractive alternative to the conventional pathway for CO<sub>2</sub> recycling, such as traditional catalysis and solar thermochemical process.

Nonthermal plasmas have been successfully utilized in many applications for the environmental control (such as gaseous pollutant abatement), material science (such as surface treatment) and medical applications (such as wound and cancer treatment) [1–3]. Nowadays, an increasing interest has been focused on examining their use for CO<sub>2</sub> utilization [3–54]. In comparison to the other processes, plasma process is fast: plasma has the potential to enable thermodynamically unfavorable chemical reactions (e.g. CO<sub>2</sub> dissociation) to occur on the basis of its non-equilibrium properties, low-power requirement and its capacity to induce physical and chemical reactions at a relatively low temperature. In addition, plasma can be ignited and shut off quickly, which enables plasma technology powered by renewable energy to act as an efficient chemical switch for the conversion purposes. Although plasma technology shows great potential, there is always a trade-off between the energy efficiency and conversion efficiency in plasma-only process. Last but not least, the conversion efficiency can be significantly improved by combining plasma with catalyst while maintaining high-energy efficiency.

Plasma catalysis (also referred to as plasma-enhanced catalysis, plasma-driven catalysis or plasma-assisted catalysis) has gathered attention as a way of increasing energy efficiency and optimizing the byproduct distribution [55]. On one hand, the catalyst can increase reaction rates and overall process selectivity. The nonthermal plasma can provide energy to drive highly endothermic processes. Plasma-catalytic processes have great potential to reduce the activation barrier of different reactions and improve the conversion rates. In addition, the nonthermal plasma itself can influence the acid–base nature of the supports, enhance the dispersion of the

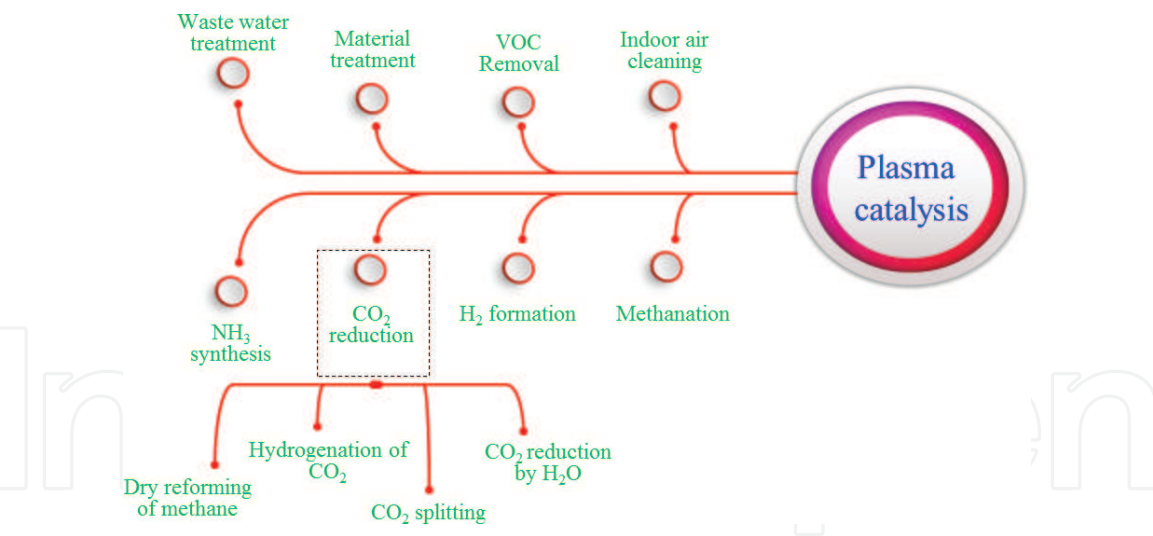

**Figure 1.**  
*Applications of plasma catalysis.*

supported metals and even adjust the microstructure of the metal nanoparticles and metal-support interface [56, 57] and in this way change the catalyst properties. All these factors contribute in different ways to the enhancement of energy efficiency of the plasma process as well as the catalyst stability, due to a synergy that occurs between the catalyst and the plasma [58]. This novel technique combines the advantages of high product selectivity from thermal catalysis and the fast startup from plasma technique. Plasma catalysis has been widely investigated for many applications. **Figure 1** briefly summarizes the main application areas of plasma catalysis. In the domain of energy applications, the use of plasma catalysis for dry reforming, CO<sub>2</sub> reduction, hydrogen production, methanation and ammonia (NH<sub>3</sub>) synthesis has been intensively studied. In this chapter, however, we focus only on their application for CO<sub>2</sub> conversion into value-added chemicals and fuels.

## 2. Brief theoretical background


### 2.1 CO<sub>2</sub> dissociation chemistry

As mentioned in Introduction, nonthermal plasma shows a great potential for an efficient CO<sub>2</sub> utilization. Different routes for CO<sub>2</sub> conversion have been investigated using plasma-catalytic process. **Table 2** summarizes some of the main reactions

Process	Reaction	Enthalpy (ΔH) kJ mol <sup>-1</sup>	Enthalpy (ΔH) eV/molecule
CO <sub>2</sub> splitting	CO <sub>2</sub> → CO + $\frac{1}{2}$ O <sub>2</sub>	279.8	2.9
Dry reforming of methane	CO <sub>2</sub> + CH <sub>4</sub> → 2CO + 2H <sub>2</sub>	247.4	2.6
Methanol synthesis	CO <sub>2</sub> + 3H <sub>2</sub> → CH <sub>3</sub> OH + H <sub>2</sub> O	-128	-1.3
Methanation	CO <sub>2</sub> + 4H <sub>2</sub> → CH <sub>4</sub> + 2H <sub>2</sub> O	-164.8	-1.7
Reverse water-gas shift reaction	CO <sub>2</sub> + H <sub>2</sub> → CO + H <sub>2</sub> O	41.2	0.4
Water-gas shift reaction	CO + H <sub>2</sub> O → CO <sub>2</sub> + H <sub>2</sub>	-41.2	-0.4
Methanation	CO + 3H <sub>2</sub> → CH <sub>4</sub> + H <sub>2</sub> O	-205.8	-2.1
Water spitting	H <sub>2</sub> O → H <sub>2</sub> + $\frac{1}{2}$ O <sub>2</sub>	250.9	2.6

**Table 2.**  
*Chemical reactions related to CO<sub>2</sub> reduction and their enthalpies.*

usually considered in plasma chemistry for CO<sub>2</sub> reduction using different pathways (such as dry reforming of methane, hydrogenation of CO<sub>2</sub>). Significant attention has been given to plasma-catalytic dry reforming of methane (DRM) using supported Ni catalysts. However, most of these studies focused primarily on identifying plasma-catalytic chemical reactions to maximize process performance. Optical emission spectroscopy and plasma chemical kinetic modeling should be used to achieve a better understanding on the formation of a wide range of reactive species in this plasma-catalytic reforming process. Recently, Chung et al. had described the mechanisms of catalysis promotion, elucidated the synergistic effects between catalyst and plasma and proposed possible approaches to optimize DRM process performance [2]. As explained by Fridman [3], cumulative vibrational excitations of the CO<sub>2</sub> molecule can result in a highly energy-efficient stepwise dissociation. Thus, CO<sub>2</sub> splitting using nonthermal plasmas has been considered as another promising pathway to produce synthetic fuels via CO, as an intermediate product. As well-accepted in the literature, dissociation of a CO<sub>2</sub> molecule in plasma is represented by the following global reaction [3]:




The main pathways for decomposition of CO<sub>2</sub> molecule include the electron impact dissociation:



which is often accompanied by the further recombination of atomic O:



In addition to this, the vibrationally excited CO<sub>2</sub> molecules may also undergo decomposition via the collisions with atomic O:



as well as with the plasma electrons:



Traditionally, to characterize the process efficiency, two main parameters reflecting the *conversion* efficiency and *energy* efficiency are used. The conversion efficiency ( $\chi$ ) and energy efficiency ( $\eta$ ) of CO<sub>2</sub> are defined as follows:

$$\chi = \frac{\text{moles of CO}_2 \text{ input} - \text{moles of CO}_2 \text{ output}}{\text{moles of CO}_2 \text{ input}} \quad (6)$$


$$\eta = \frac{\chi * 2.9 \text{ eV}}{\text{SEI}} \quad (7)$$

Here the specific energy input (SEI) per molecule is given by the ratio of the discharge power (P) to the gas flow rate (F) through the discharge volume.

## 2.2 Plasma catalysis

When catalysts are combined with plasmas, they can be classified into three systems, i.e. single stage, two stage, and multistage, depending on the location of




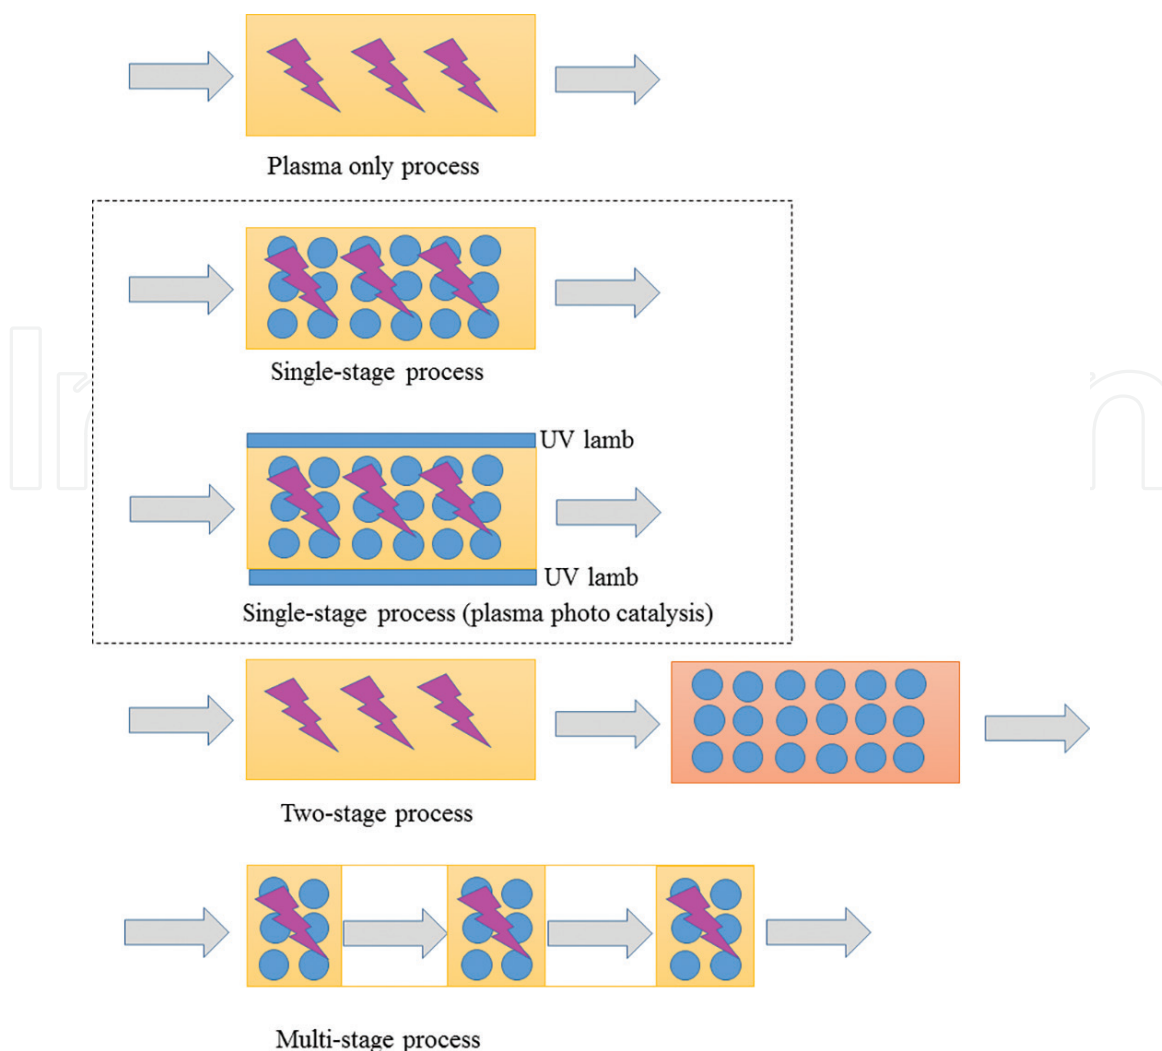

**Figure 2.**  
 Schematic diagram of different plasma-catalyst configurations according to the catalyst bed position and number.

the catalyst [59, 60]. These three configurations are illustrated in **Figure 2**. In all cases, the plasma can be used to supply energy for catalyst activation, and it can also provide the reactive gas species needed for reactions on the catalyst surface. The single-stage type is constructed by coating catalyst on the surface of electrode(s) or packing catalyst within the plasma zone, which is also called in-plasma catalysis (IPC). The catalysts could completely or just partially overlap with the plasma zone. In this manner, the plasma and catalysis could directly interact with each other. This single-stage system is also easy to combine with the UV irradiation, which is known as plasma photo catalysis, as shown in **Figure 2**. For the two-stage type, the catalyst is placed after the plasma discharge region; it is also called post-plasma catalysis (PPC). The plasma provides chemically reactive species for catalysis or pre-converts reactants into the easier-to-convert products to accelerate the catalysis. In the nonthermal plasma catalysis system, the long-lived reactive species produced by plasma, e.g. vibration-excited species, radicals, and ionized molecules, can react with the catalyst to induce catalytic reactions via either the Eley-Rideal mechanism or Langmuir-Hinshelwood mechanism [2, 59]. The multistage plasma catalysis system is a promising option for the industrial use in the future. Different functions of the catalysts can be combined to achieve certain expected reaction in the multi-stage system.

In the context of plasma catalysis, the synergy is referring to a surplus effect of combining the plasma with catalyst, namely, when the resulting effect has a higher

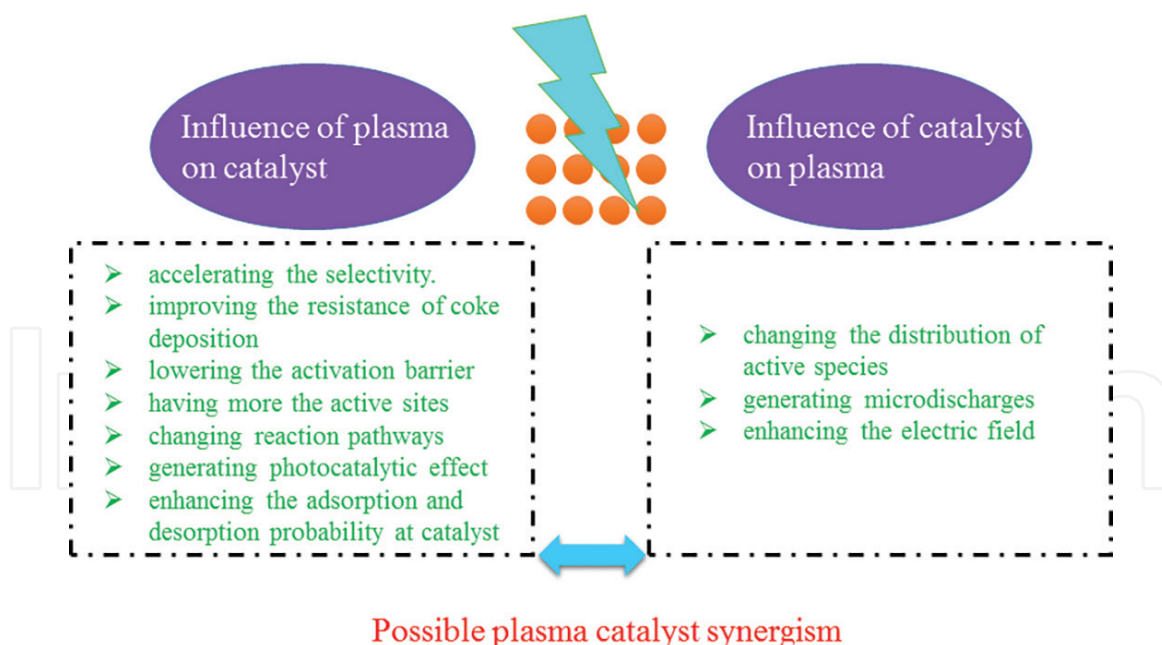

**Figure 3.**  
*Interaction between catalyst and plasma.*

impact than the sum of their individual impacts. In several studies, the combination of plasma and catalysts has been found to have synergistic effects [34, 35, 61, 62]. A highly important synergistic effect of plasma catalysis is promotion of catalyst activity at reduced temperatures, and hence, a significant reduction in the energy cost for activating the catalyst [34]. For example, Wang et al. illustrated such synergy for plasma catalysis of dry reforming methane (DRM) in the single-stage system with Ni/Al<sub>2</sub>O<sub>3</sub> catalyst but did not observe this synergy in the two-stage system or when the catalyst is only placed at the end of the plasma zone [62]. Typical synergistic effect factors of 1.25–1.5 were obtained. Zhang et al. presented the results on the plasma-catalyst synergy in the case of dry reforming methane using different Cu-Ni/γ-Al<sub>2</sub>O<sub>3</sub> catalysts [63]. The effect was observed on the conversions of CH<sub>4</sub> and CO<sub>2</sub>, where the result for the plasma-catalytic reaction was greater than the sum of the catalyst-only or plasma-only results. The selectivity towards H<sub>2</sub> and CO production was also enhanced by the use of plasma catalysis. In general, the enhanced performance of plasma catalysis can in part be attributed to vibrational excitation of CO<sub>2</sub> in the plasma, which enables easier dissociation at low temperature on the catalyst surface. The plasma electrons in turn affect the catalyst properties (chemical composition or catalytic structure). Synergistic effects in the plasma and catalyst are illustrated in **Figure 3**. Plasma can alter the physicochemical characteristics of catalyst via several routes, which are induced mainly by energetic electron generation. In the meantime, a catalyst can induce electric field concentration due to its pore structure and dielectric properties. Hence, both electric field distribution and catalyst characteristics are modified to have better DRM performance.

### 3. Plasma-assisted catalytic conversion of CO<sub>2</sub>

Nonthermal plasma technology provides an attractive alternative to the other (classical) technologies for converting inert carbon emissions. Different types of plasmas have already been used for CO<sub>2</sub> reduction, including dielectric barrier discharges (DBDs), glow discharges, radio frequency (RF) discharges, microwave (MW) discharges and gliding arc plasma (GAP) and corona discharges [8–39]. In this section, the most widely used discharges for CO<sub>2</sub> conversion are presented.


DBDs have been known for more than a century. They were first reported in 1857 by Siemens for the use in ozone production and were originally called 'silent' discharges [64]. The DBD is the most widely used discharge type for CO<sub>2</sub> conversion among the variety of other plasma sources because it is easy to handle with relatively cheap equipment and it operates at atmospheric pressure [34]. Even though the conversion efficiencies obtained in DBDs are generally quite low [1, 4, 5, 8, 9, 12, 13], the possibility to work at atmospheric pressure under non-equilibrium conditions is still a very strong advantage of these discharges. Combined with plasma catalysis, these discharges should also improve the selective production of the targeted compounds.

An atmospheric pressure GAP discharge can be formed between two flat knife-shaped electrodes with a gas flowing between them. These discharges are suitable for applications that require relatively large gas flows (several l/min). The gliding arc plasma can be operated in the thermal and nonthermal regime depending on the applied power and flow rate. Furthermore, the arc can be operated in the transition regime, which is an evolving arc starting in the thermal regime going to the nonthermal regime. This transition regime makes the discharge energy efficient for gas treatment. An energy efficiency of 43% was reported by Nunnally et al. for the decomposition of CO<sub>2</sub> in a reverse vortex flow gliding arc discharge, which is quite high compared to the efficiency obtained with DBDs (about 10%) [31]. The high level of efficiency can be attributed to non-equilibrium vibrational excitation of CO<sub>2</sub> and a high-temperature gradient between the gliding arc and the surrounding gas that results in fast quenching.

Plasmas generated by the injection of microwave power, i.e. electromagnetic radiation in the frequency range of 100 MHz–10 GHz, are called MW plasmas [65]. MW discharges are commonly generated using frequencies of 2.45 and 0.915 GHz. They can be operated over a wide pressure range (from few mTorr to the atmospheric pressure). The properties of the MW discharges operating at atmospheric pressure are close to those of thermal plasma. However, the MW discharges are far from thermodynamic equilibrium at low pressure. The performance of a microwave discharge in terms of efficiency of CO<sub>2</sub> dissociation process depends heavily on the plasma parameters such as power and operating pressure. The highest energy efficiency (about 90%) for pure CO<sub>2</sub> conversion was reported in a MW plasma operating with supersonic gas flows [22]. The ability to create a strong non-equilibrium environment in microwave discharges possesses highly vibrational states of CO<sub>2</sub> molecules, which are energy-efficient for CO<sub>2</sub> decomposition [3]. In general, the high efficiency of microwave plasmas is attained due to the high absorption of the applied power by electrons as well as relatively high excitation of the CO<sub>2</sub> asymmetric mode [24], which plays a key role for CO<sub>2</sub> decomposition [22]. In the low-pressure case, the microwave plasmas are typically characterized by an electron temperature around 1–2 eV and a gas temperature below 1500 K. Under these conditions, it has been estimated that about 95% of all the discharge energy is transferred from the plasma electrons to the CO<sub>2</sub> molecules, mostly to their asymmetric vibrational mode [3, 24].

Bogaerts et al. has presented some insights into how the electron energy is transferred to different channels of excitation, ionization or dissociation of the CO<sub>2</sub> molecules [1, 66]. **Figure 4** illustrates the fractional energy transferred from electrons to different channels of excitation, ionization and dissociation of CO<sub>2</sub>, as a function of the reduced electric field ( $E/n$ ) in a discharge. This plot is calculated based on the cross sections of the corresponding electron impact reactions [1, 37, 66]. In microwave plasma, the reduced electric field is typically around 50 Td, which is most appropriate for the vibrational excitation of CO<sub>2</sub>. Fridman has shown that up to 97% of the total nonthermal discharge energy can be transferred from the plasma electrons to vibrational excitation of CO<sub>2</sub> molecules at an electron temperature around 1–2 eV or a reduced electric field ( $E/n$ ) of about 20–40 Td [3, 36]. This is indeed indicated by the calculated curve referred to as the 'sum of all vibrations'



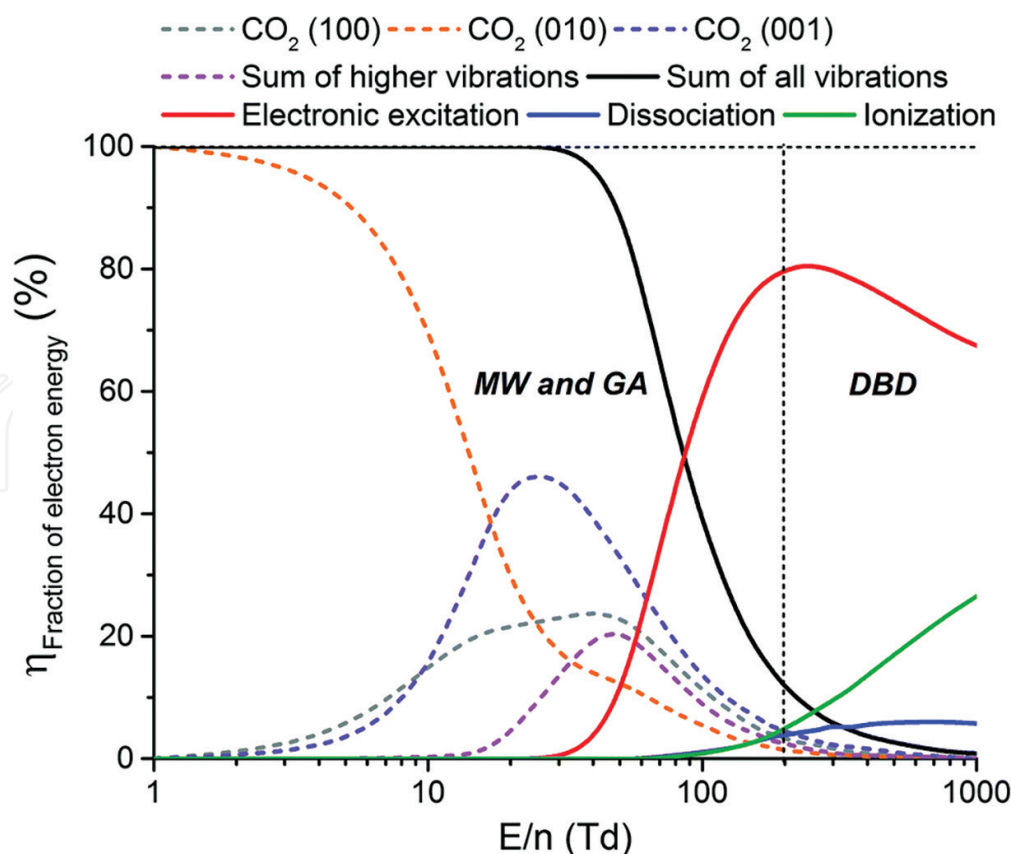

**Figure 4.**

The fraction of electron energy transferred to different channels of excitation as a function of the reduced electric field ( $E/n$ ) (adapted from [1]).


shown in **Figure 4**. Moreover, the purple curve in **Figure 4** has its particular importance as it represents the first vibrational level of the asymmetric vibrational mode of  $\text{CO}_2$ , which represents the most important channel for the dissociation [66]. The energy efficiency for the dissociation of  $\text{CO}_2$  is quite limited in a DBD plasma [3, 4, 11–13]. The electron temperature in a DBD is about 2–3 eV, which is somewhat high for efficient population of the  $\text{CO}_2$  vibrational levels. The reduced electric field values are being typically about 200 Td or even higher, indicated as ‘DBD region’ in the figure. As a result of previous studies on  $\text{CO}_2$  decomposition in plasma, it was concluded that higher pressures and lower values of reduced electric field make the vibrational excitation mechanism more favorable than the electronic excitation mechanism, explaining the higher energy efficiency of these types of discharges (e.g. MW, GAP) [1, 3, 22, 26, 28, 32, 33, 35, 37, 38].

### 3.1 MW region

In this chapter we have summarized the results from the recent publications on plasma set-ups with and without combining a catalyst for  $\text{CO}_2$  conversion in **Table 2** and discussed the current research status on this topic. Porous  $\text{Al}_2\text{O}_3$  ( $\alpha\text{-Al}_2\text{O}_3$  and  $\gamma\text{-Al}_2\text{O}_3$ ) has been investigated in a pulsed corona discharge reactor for  $\text{CO}_2$  conversion by Wen et al. [39].  $\gamma\text{-Al}_2\text{O}_3$  was found to enhance  $\text{CO}_2$  conversion due to its high surface area and strong adsorption capability. Zhang et al. investigated  $\text{CO}_2$  decomposition to CO and  $\text{O}_2$  in a DBD reactor packed with a mixture of Ni/ $\text{SiO}_2$  catalyst and  $\text{BaTiO}_3$  spheres. In comparison to the reaction in the absence of a Ni/ $\text{SiO}_2$  catalyst, introducing a Ni/ $\text{SiO}_2$  catalyst to the plasma reactor packed with  $\text{BaTiO}_3$  spheres slightly increase the  $\text{CO}_2$  conversion from 19 to 23.5% at low temperatures [17]. Van Laer demonstrated a packing of  $\text{ZrO}_2$  beads in a DBD reactor. The best combination of conversion (37.8%) and energy

(6.4%) efficiency was reached at a flow rate of  $20 \text{ mL min}^{-1}$  and an input power of  $60 \text{ W}$  [16]. Their simulation results suggest that the increased  $\text{CO}_2$  conversion is caused by the presence of strong electric fields and thus high electron energies at the contact points, which thereby lowers the breakdown voltage. These findings suggest that the interactions between plasma and packing materials play an important role in the plasma conversion of  $\text{CO}_2$ . Brock et al. studied the catalytic effect of metallic coating on the decomposition of  $\text{CO}_2$  in fan-type AC glow discharge plasma reactors, using a gas mixture of 2.5%  $\text{CO}_2$  in He [19]. They showed that an Rh-coated reactor has the highest activity for the  $\text{CO}_2$  decomposition compared to the reactors coated with Cu, Au, Pt and Pd and mixed rotor/stator systems (Rh/Au and Au/Rh).

In relation to microwave plasmas, Chen et al. reported that placing a NiO/ $\text{TiO}_2$  catalyst in the downstream of a low-pressure microwave plasma significantly increased the  $\text{CO}_2$  conversion efficiency and energy efficiency [25, 28]. They concluded that the oxygen vacancies provide the sites for adsorption of oxygen atoms from  $\text{CO}_2$ . The energetic electrons supplied by the plasma enhance the dissociative electron attachment of  $\text{CO}_2$  at the surface. Recently, Ray et al. found that  $\text{CO}_2$  conversion was enhanced upon packing  $\text{CeO}_2$  into the discharge region of a DBD reactor. They also suggest this enhancement can be mainly attributed to the formation of oxygen vacancy defects on the surface of  $\text{CeO}_2$ , to stabilize the produced atomic oxygen, thereby preventing the reverse reaction [18]. Spencer et al. experimentally investigated the conversion of  $\text{CO}_2$  in an atmospheric pressure microwave plasma-catalytic system [21]. The results showed that Rh/ $\text{TiO}_2$  coating on a monolithic cordierite structure used as a catalyst actually caused a drop in conversion efficiency due to reverse reactions occurring on the surface. Mei et al. demonstrated that the combination of plasma with  $\text{BaTiO}_3$  and  $\text{TiO}_2$  catalysts has a synergistic effect, which significantly enhances the conversion of  $\text{CO}_2$  and the energy efficiency by a factor of 2.5 compared to the plasma reaction in the absence of a catalyst [7]. The overall synergistic effect resulting from the integration of DBD with catalysis for  $\text{CO}_2$  conversion can be attributed to the dominant catalytic surface reaction driven by energetic electrons from the  $\text{CO}_2$  discharge. Theoretical and experimental studies consistently showed that the  $\text{CO}_2$  adsorption, activation and dissociation processes were significantly enhanced by the presence of oxygen vacancies [7, 23, 28, 67, 68]. The mechanism of plasma-catalytic  $\text{CO}_2$  conversion can be described by **Figure 5**. The oxygen vacancies provide sites for the adsorption of

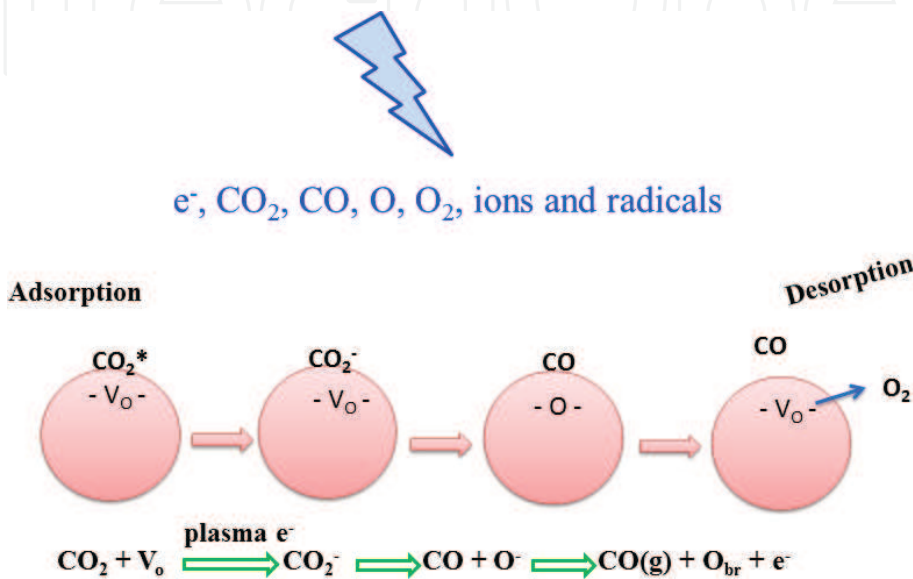

**Figure 5.**  
*Schematic mechanism of plasma-assisted catalytic process for  $\text{CO}_2$  conversion.*

Plasma type	Comments	Gas mixture	Catalyst	$\chi$ (%)	$\eta$ (%)	SEI eV/ molecule	Ref.
DBD		CO <sub>2</sub>	—	17	9	5.8	[4]
DBD		CO <sub>2</sub>	—	30	1	87	[5]
DBD		CO <sub>2</sub>	$\gamma$ -Al <sub>2</sub> O <sub>3</sub>	20	4.9	12	[6]
DBD		CO <sub>2</sub>	BaTiO <sub>3</sub>	38	17	6.5	[7]
DBD		CO <sub>2</sub>	—	18	4	13	[8]
DBD	Low flow rate	CO <sub>2</sub>	—	14	8	5.2	[9]
DBD	10% CO <sub>2</sub> in the gas mixture	CO <sub>2</sub> - H <sub>2</sub> O-Ar	Ni/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	36	23	4.5	[10]
DBD		CO <sub>2</sub>	—	35	2	50.8	[11]
DBD		CO <sub>2</sub>	—	28.2	11.1	7.4	[12]
DBD		CO <sub>2</sub> -N <sub>2</sub>	—	4.5	4.5	2.9	[13]
DBD		CO <sub>2</sub>	CaO	39.2	7.1	16	[14]
DBD		CO <sub>2</sub>	—	20	10.4	5.6	[15]
DBD		CO <sub>2</sub>	ZrO <sub>2</sub>	2.9	9.6	9.6	[16]
DBD		CO <sub>2</sub>	Ni/ SiO <sub>2</sub> + BaTiO <sub>3</sub>	23.5	2.31	29.5	[17]
DBD		CO <sub>2</sub>	CeO <sub>2</sub> (2 mm)	10.6	27.6	1.11	[18]
DBD		CO <sub>2</sub>	TiO <sub>2</sub> (3–4 mm)	8.2	15.54	1.53	[18]
Glow		CO <sub>2</sub> -Ar	Rh-coated	30	1.4	62	[19]
RF		CO <sub>2</sub>	—	20	3	19	[20]
MW		CO <sub>2</sub> -Ar	—	10	20	1.4	[21]
MW	Supersonic flow	CO <sub>2</sub>	—	10	90	0.3	[22]
MW		CO <sub>2</sub>	NiO/TiO <sub>2</sub>	42	18	7.0	[23]
MW		CO <sub>2</sub> -N <sub>2</sub>	—	80	6	39	[24]
MW		CO <sub>2</sub>	—	20	20	2.9	[25]
MW		CO <sub>2</sub>	—	12	45	0.8	[26]
MW	CO <sub>2</sub> :H <sub>2</sub> O = 1:1	CO <sub>2</sub> -H <sub>2</sub> O	—	12	8.7	4	[27]
MW		CO <sub>2</sub>	NiO/TiO <sub>2</sub>	45	56	2.3	[28]
MW		CO <sub>2</sub>	—				[29]
Corona		CO <sub>2</sub>	—	11	2	16	[30]
Gliding arc		CO <sub>2</sub>	—	4.6	43	0.3	[31]
Gliding arc		CO <sub>2</sub>	—	15	19	2.3	[32]
Gliding arc		CO <sub>2</sub>	—	10	34	0.85	[33]

**Table 3.**  
*Summary of the plasma-assisted catalytic CO<sub>2</sub> conversion for different discharge types.*

oxygen atoms from CO<sub>2</sub>. The energetic electrons supplied by the plasma enhance the dissociative electron attachment of CO<sub>2</sub> at the surface. Subsequently, CO desorbs or moves from the reactive site while the other O (bridging) atom ‘heals’ the oxygen vacancy. The oxygen vacancy can be regenerated via the recombination

on the surface of a bridging oxygen atom with a gaseous oxygen atom. Such regeneration maintains the equilibrium of the active sites in the catalyst and controls the CO<sub>2</sub> conversion [23]. If the catalyst is placed in the plasma zone (single stage), the electron–hole pairs can be created by highly energetic electrons from the discharge upon the surface of photocatalysts once plasma can generate electrons of very similar energy (3–4 eV) to the photons. In this case, oxygen vacancy can be regenerated by oxidizing the surface O<sub>2</sub><sup>−</sup> anions using holes, followed by releasing O<sub>2</sub> [7]. Plasma-catalytic conversion of CO<sub>2</sub> is a complex and challenging process involving a large number of physical and chemical reactions. The performance of the process is controlled by means of plasma parameters and the properties of the catalysts as well. This suggests that more systematic studies on both the plasma effects and the chemical effects of the catalyst are highly needed (**Table 3**).

#### 4. Conclusions and perspectives

Plasma-assisted catalytic processes used for CO<sub>2</sub> reduction are gaining increasing interest worldwide. There is still a room, however, for further improvement of the CO<sub>2</sub> conversion and energy efficiencies through the optimization of the plasma parameters (e.g. high pressure and high flow rate) as well as through modification of catalysts.

The plasma-catalytic activities can be controlled by numerous factors such as the nature of the catalyst support, active metal sites, surface area and the nanoparticle size. Let us note that the catalyst preparation (sometime called ‘activation’) plays a very important role in this regard. In addition to these factors and also due to their existence, the fine-tuning of a given catalyst is inevitable and crucial factor for enhancing plasma-catalytic process efficiency. Several methods, such as loading different metal nanoparticles, using different catalyst preparation schemes (sol gel, co-precipitation, deposition-precipitation or hydrothermal synthesis), using larger surface area of the support, etc., can be mentioned to realize the mentioned tuning.

An important factor which cannot be omitted here is that a chosen catalyst material should have rather low costs to be potentially commercialized and implemented in the industrial scale. Moreover, as a result of recent development of the microwave discharges, namely, a possibility to place catalyst packing directly in the discharge zone can be a powerful way to take advantage of the stepwise vibrational excitation on the catalyst surface. In addition, using plasma as a tool for the preparation (activation) of the catalyst surface may be another promising way. To improve its application, a better insight into the underlying mechanisms of the plasma catalysis is desirable. A greater understanding of the plasma chemistry, both by plasma modeling and by coupling with other techniques such as catalysis and membrane materials, will allow this field to expand. We expect that the results presented in this chapter will provide useful insights into the plasma-assisted CO<sub>2</sub> conversion in the presence or the absence of catalysts, which may be used for greenhouse gas conversion in the industry.

#### Acknowledgements

The authors acknowledge financial support from the network on the Physical Chemistry of Plasma-Surface Interactions—Interuniversity Attraction Poles phase VII project (<http://psi-iap7.ulb.ac.be/>), supported by the Belgian Federal Office for Science Policy (BELSPO). The support of the ‘REFORGAS GreenWin’ project, grant No. 7267 (for GC, TG), should be acknowledged.



IntechOpen

### Author details

Guoxing Chen<sup>1,2\*</sup>, Ling Wang<sup>4</sup>, Thomas Godfroid<sup>3</sup> and Rony Snyders<sup>1,3</sup>

1 Chemistry of Plasma Surface Interactions, University of Mons, Belgium

2 4MAT, Universite Libre de Bruxelles, Belgium

3 “Materia Nova” Research Center, Belgium

4 Institute for Materials Science, University of Stuttgart, Stuttgart, Germany

\*Address all correspondence to: guoxchen@ulb.ac.be

### IntechOpen

© 2018 The Author(s). Licensee IntechOpen. This chapter is distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/3.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited. 

## References

- [1] Snoeckx R, Bogaerts A. Plasma technology – a novel solution for CO<sub>2</sub> conversion. *Chemical Society Reviews*. 2017;**46**:5805-5863
- [2] Fridman A. *Plasma Chemistry*. London: Cambridge University Press; 2008
- [3] Chung WC, Chang MB. Review of catalysis and plasma performance on dry reforming of CH<sub>4</sub> and possible synergistic effects. *Renewable and Sustainable Energy Reviews*. 2016;**62**:13-31
- [4] Ozkan A, Dufour T, Bogaerts A, Reniers F. How do the barrier thickness and dielectric material influence the filamentary mode and CO<sub>2</sub> conversion in a flowing DBD? *Plasma Sources Science and Technology*. 2016;**25**(4):045016
- [5] Paulussen S, Verheyde B, Xin T, Bie CD, Martens T, Petrovic D, et al. Conversion of carbon dioxide to value-added chemicals in atmospheric pressure dielectric barrier discharges. *Plasma Sources Science and Technology*. 2010;**19**:034015
- [6] Yu Q, Kong M, Liu T, Fei J, Zheng X. Characteristics of the decomposition of CO<sub>2</sub> in a dielectric packed-bed plasma reactor. *Plasma Chemistry and Plasma Processing*. 2012;**32**:153-163
- [7] Mei D, Zhu X, Wu C, Ashford B, Williams PT, Tu X. Plasma-photocatalytic conversion of CO<sub>2</sub> at low temperatures: Understanding the synergistic effect of plasma-catalysis. *Applied Catalysis B: Environmental*. 2016;**182**:525-532
- [8] Duan X, Li Y, Ge W, Wang B. Degradation of CO<sub>2</sub> through dielectric barrier discharge microplasma. *Greenhouse Gases: Science and Technology*. 2015; **5**:131-140
- [9] Mei D, He YL, Liu S, Yan J, Tu X. Optimization of CO<sub>2</sub> conversion in a cylindrical dielectric barrier discharge reactor using design of experiments. *Plasma Processes and Polymers*. 2016;**13**:544-556
- [10] Mahammadunnisa S, Reddy L, Ray D, Subrahmanyam C, Whitehead JC. CO<sub>2</sub> reduction to syngas and carbon nanofibres by plasma-assisted in situ decomposition of water. *International Journal of Greenhouse Gas Control*. 2013;**16**:361-363
- [11] Aerts R, Somers W, Bogaerts A. Carbon dioxide splitting in a dielectric barrier discharge plasma: A combined experimental and computational study. *ChemSusChem*. 2015;**8**:702-716
- [12] Ozkan A, Dufour T, Silva T, Britun N, Snyders R, Bogaerts A, et al. The influence of power and frequency on the filamentary behavior of a flowing DBD—application to the splitting of CO<sub>2</sub>. *Plasma Sources Science and Technology*. 2016;**25**:025013
- [13] Snoeckx R, Heijckers S, Van Wesenbeeck K, Lenaerts S, Bogaerts A. CO<sub>2</sub> conversion in a dielectric barrier discharge plasma: N<sub>2</sub> in the mix as a helping hand or problematic impurity? *Energy and Environmental Science*. 2016;**9**:999-1011
- [14] Duan XF, Hu ZY, Li YP, Wang BW. Effect of dielectric packing materials on the decomposition of carbon dioxide using DBD microplasma reactor. *AIChE Journal*. 2015;**61**:898-903
- [15] Mei D, Tu X. Conversion of CO<sub>2</sub> in a cylindrical dielectric barrier discharge reactor: Effects of plasma processing parameters and reactor design. *Journal of CO<sub>2</sub> Utilization*. 2017;**19**:68-78
- [16] Van Laer K, Bogaerts A. Improving the conversion and energy efficiency

of carbon dioxide splitting in a zirconia-packed dielectric barrier discharge reactor. *Energy Technology*. 2015;**3**:1038-1044

[17] Zhang K, Zhang G, Liu X, Phan AN, Luo K. A Study on CO<sub>2</sub> Decomposition to CO and O<sub>2</sub> by the combination of catalysis and dielectric-barrier discharges at low temperatures and ambient pressure. *Industrial and Engineering Chemistry Research*. 2017;**56**:3204-3216

[18] Ray D, Subrahmanyam C. CO<sub>2</sub> decomposition in a packed DBD plasma reactor: Influence of packing materials. *RSC Advances*. 2016;**6**:39492-39499

[19] Brock SL, Marquez M, Suib SL, Hayashi Y, Matsumoto H. Plasma decomposition of CO<sub>2</sub> in the presence of metal catalysts. *Journal of Catalysis*. 1998;**180**:225-233

[20] Spencer LF, Gallimore AD. Efficiency of CO<sub>2</sub> dissociation in a radio-frequency discharge. *Plasma Chemistry and Plasma Processing*. 2011;**31**:79-89

[21] Spencer LF, Gallimore AD. CO<sub>2</sub> dissociation in an atmospheric pressure plasma/catalyst system: A study of efficiency. *Plasma Sources Science and Technology*. 2013;**22**:015019

[22] Asisov RI, Givotov VK, Krashenninnikov EG, Potapkin BV, Rusanov VD, Fridman A. *Soviet Physics–Doklady*. 1983;**271**:94

[23] Chen G, Georgieva V, Godfroid T, Snyders R, Delplancke-Ogletree M-P. Plasma assisted catalytic decomposition of CO<sub>2</sub>. *Applied Catalysis B: Environmental*. 2016;**190**:115-124

[24] Silva T, Britun N, Godfroid T, Snyders R. Optical characterization of a microwave pulsed discharge used for dissociation of CO<sub>2</sub>. *Plasma*

*Sources Science and Technology*. 2014;**23**:025009

[25] Chen G, Britun N, Godfroid T, Georgieva V, Snyders R, Delplancke-Ogletree M-P. An overview of CO<sub>2</sub> conversion in a microwave discharge: the role of plasma-catalysis. *Journal of Physics D: Applied Physics*. 2017;**50**:084001

[26] van Rooij GJ, van den Bekerom DCM, den Harder N, Minea T, Berden G, Bongers WA, et al. Taming microwave plasma to beat thermodynamics in CO<sub>2</sub> dissociation. *Faraday Discussions*. 2015;**183**:233

[27] Chen G, Silva T, Georgieva V, Godfroid T, Britun N, Snyders R, et al. Simultaneous dissociation of CO<sub>2</sub> and H<sub>2</sub>O to syngas in a surface-wave microwave discharge. *International Journal of Hydrogen Energy*. 2015;**40**:3789-3796

[28] Chen G, Godfroid T, Georgieva V, Britun N, Delplancke-Ogletree M-P, Snyders R. Plasma-catalytic conversion of CO<sub>2</sub> and CO<sub>2</sub>/H<sub>2</sub>O in a surface-wave sustained microwave discharge. *Applied Catalysis B: Environmental*. 2017;**214**:114-125

[29] Britun N, Silva T, Chen G, Godfroid T, Mullen J, Snyders R. Plasma-assisted CO<sub>2</sub> conversion: Optimizing performance via microwave power modulation. *Journal of Physics D: Applied Physics*. 2018;**51**:144002

[30] Mikoviny T, Kocan M, Matejcik S, Mason NJ, Skalny JD. Experimental study of negative corona discharge in pure carbon dioxide and its mixtures with oxygen. *Journal of Physics D: Applied Physics*. 2004;**37**:64

[31] Nunnally T, Gutsol K, Rabinovich A, Fridman A, Gutsol A, Kemoun A. Dissociation of CO<sub>2</sub> in a low current gliding arc plasmatron. *Journal of*

Physics D: Applied Physics. 2011;**44**: 274009

[32] Indarto A, Yang DR, Choi JW, Lee H, Song HK. Gliding arc plasma processing of CO<sub>2</sub> conversion. *Journal of Hazardous Materials*. 2007;**146**: 309-315

[33] Sun SR, Wang HX, Mei DH, Tu X, Bogaerts A. CO<sub>2</sub> conversion in a gliding arc plasma: Performance improvement based on chemical reaction modeling. *Journal of CO<sub>2</sub> Utilization*. 2017;**17**: 220-234

[34] Neyts EC, Ostrikov K, Sunkara MK, Bogaerts A. Plasma catalysis: Synergistic effects at the nanoscale. *Chemical Reviews*. 2015;**115**:13408-13446

[35] Chen G, Britun N, Godfroid T, Delplancke-Ogletree MP, Snyders R. Role of Plasma Catalysis in the Microwave Plasma-Assisted Conversion of CO<sub>2</sub>. *Green Processing and Synthesis*. Rijeka, Croatia: Intech Publishing. 2017. ISBN: 978-953-51-5330-6

[36] Fridman A, Rusanov VD. Theoretical basis of non-equilibrium near atmospheric pressure plasma chemistry. *Pure and Applied Chemistry*. 1994;**66**:1267-1278

[37] Bogaerts A, Kozák T, Van Laer K, Snoeckx R. Plasma-based conversion of CO<sub>2</sub>: Current status and future challenges. *Faraday Discussions*. 2015;**183**:217-232

[38] Britun N, Chen G, Silva T, Godfroid T, Delplancke-Ogletree M-P, Snyders R. *Green Processing and Synthesis*. Rijeka, Croatia: Intech Publishing. 2017. ISBN: 978-953-51-5330-6

[39] Wen Y, Jiang X. Decomposition of CO<sub>2</sub> using pulsed corona discharges combined with catalyst. *Plasma Chemistry and Plasma Processing*. 2001;**21**:665-678

[40] Wang S, Zhang Y, Liu X, Wang X. Enhancement of CO<sub>2</sub> conversion rate and conversion efficiency by homogeneous discharges. *Plasma Chemistry and Plasma Processing*. 2012;**32**(5):979-989

[41] Li R, Tang Q, Yin S, Sato T. Investigation of dielectric barrier discharge dependence on permittivity of barrier materials. *Applied Physics Letters*. 2007;**90**:131502

[42] Li R, Tang Q, Yin S, Sato T. Plasma catalysis for CO<sub>2</sub> decomposition by using different dielectric materials. *Fuel Processing Technology*. 2006;**87**: 617-622

[43] Indarto A, Choi JW, Lee H, Song HK. Conversion of CO<sub>2</sub> by gliding arc plasma. *Environmental Engineering Science*. 2006;**23**:1033-1043

[44] Silva T, Britun N, Godfroid T, Snyders R. Understanding CO<sub>2</sub> decomposition in microwave plasma by means of optical diagnostics. *Plasma Processes and Polymers*. 2017;**14**: 1600103

[45] Belov I, Paulussen S, Bogaerts A. Appearance of a conductive carbonaceous coating in a CO<sub>2</sub> dielectric barrier discharge and its influence on the electrical properties and the conversion efficiency. *Plasma Sources Science and Technology*. 2016;**25**:015023

[46] Ashford B, Tu X. Non-thermal plasma technology for the conversion of CO<sub>2</sub>. *Current Opinion in Green and Sustainable Chemistry*. 2017;**3**:45-49

[47] Xu S, Whitehead JC, Martin PA. CO<sub>2</sub> dissociation in a packed bed DBD reactor: First steps towards a better understanding of plasma catalysis. *Chemical Engineering Journal*. 2017;**326**:477-488

[48] Zou J, Liu C. Utilization of Carbon Dioxide through Nonthermal



Plasma Approaches. Weinheim: Wiley-VCH Press; 2010. ISBN: 978-3-527-32475-0

[49] Ray D, Saha R, Ch S. DBD plasma assisted CO<sub>2</sub> Decomposition: Influence of diluent gases. *Catalysts*. 2017;**7**:244

[50] Snoeckx R, Ozkan A, Reniers F, Bogaerts A. The quest for value-added products from carbon dioxide and water in a dielectric barrier discharge: A chemical kinetics Study. *ChemSusChem*. 2017;**10**:409-424

[51] Heijkers S, Snoeckx R, Kozák T, Silva T, Godfroid T, Britun N, et al. CO<sub>2</sub> conversion in a microwave plasma reactor in the presence of N<sub>2</sub>: Elucidating the role of vibrational levels. *Journal of Physical Chemistry C*. 2017;**119**(23):12815-12828

[52] Wang T, Liu H, Xiong X, Feng X. Conversion of carbon dioxide to carbon monoxide by pulse dielectric barrier discharge plasma. *IOP Conference Series: Earth and Environmental Science*. 2017;**52**:012100

[53] Fridman A, Kennedy LA. *Plasma Physics and Engineering*. New York: Taylor and Francis; 2011

[54] Spencer LF. The study of CO<sub>2</sub> conversion in a microwave plasma/catalyst system [PhD dissertation]. Michigan: The University of Michigan; 2012

[55] Whitehead JC. Plasma-catalysis: The known knowns, the known unknowns and the unknown unknowns. *Journal of Physics D: Applied Physics*. 2016;**49**:243001

[56] Chen HL, Lee HM, Chen SH, Chao Y, Chang MB. Review of plasma catalysis on hydrocarbon reforming for hydrogen production—interaction, integration, and prospects. *Applied Catalysis, B: Environmental*. 2008;**85**:1-9

[57] Liu C, Xu G, Wang T. Non-thermal plasma approaches in CO<sub>2</sub> utilization. *Fuel Processing Technology*. 1999;**58**:119-134

[58] Tu X, Whitehead JC. Plasma-catalytic dry reforming of methane in an atmospheric dielectric barrier discharge: Understanding the synergistic effect at low temperature. *Applied Catalysis, B: Environmental*. 2012;**125**:439-448

[59] Whitehead JC. Plasma catalysis: A solution for environmental problems. *Pure and Applied Chemistry*. 2010;**82**:1329-1336

[60] Kim HH, Teramoto Y, Ogata A, Takagi H, Nanba T. Plasma catalysis for environmental treatment and energy applications. *Plasma Chemistry and Plasma Processing*. 2016;**36**:45-72

[61] Neyts EC. Plasma-surface interactions in plasma catalysis. *Plasma Chemistry and Plasma Processing*. 2016;**36**:185-212

[62] Wang Q, Yan BH, Jin Y, Cheng Y. Dry reforming of methane in a dielectric barrier discharge reactor with Ni/Al<sub>2</sub>O<sub>3</sub> catalyst: Interaction of Catalyst and Plasma. *Energy Fuels*. 2009;**23**:4196-4201

[63] Zhang AJ, Zhu AM, Guo J, Xu Y, Shi C. Conversion of greenhouse gases into syngas via combined effects of discharge activation and catalysis. *Chemical Engineering Journal*. 2010;**156**:601-606

[64] Siemens W. Ueber die elektrostatische induction und die verzögerung des stroms in flaschendrähnen. *Annalen der Physik und Chemie*. 1857;**178**:66-122

[65] Lebedev YA. Microwave discharges: generation and diagnostics. *Journal of Physics: Conference Series*. 2010;**257**:012016

[66] Aerts R. Experimental and computational study of dielectric barrier discharges for environmental applications [PhD thesis]. Antwerpen: Universiteit Antwerpen; 2014

[67] Lee J, Sorescu DC, Deng X. Electron-induced dissociation of CO<sub>2</sub> on TiO<sub>2</sub> (110). *Journal of the American Chemical Society*. 2011;**133**:10066-10069

[68] Liu L, Li Y. Understanding the Reaction Mechanism of Photocatalytic Reduction of CO<sub>2</sub> with H<sub>2</sub>O on TiO<sub>2</sub>-Based Photocatalysts: A Review. *Aerosol and Air Quality Research*. 2014;**14**: 453-469