

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

6,900

Open access books available

186,000

International authors and editors

200M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.
For more information visit www.intechopen.com



Hybrid Two-step Preparation of Nanosized MgAl Layered Double Hydroxides for CO₂ Adsorption

Xiani Huang, Xiaogang Yang, Guang Li, Collins I. Ezech, Chenggong Sun and Collins Snape

Abstract

Hybrid Two-step synthesis method for preparation of MgAl LDHs materials for CO₂ adsorption has been employed because of the features of fast micromixing and enhanced mass transfer by using a 'T-mixer' reactor. MgAl LDHs with different morphologies were successfully obtained by three different synthesis routes: ultrasonication-intensified in 'T-mixer' (TU-LDHs), conventional co-precipitation (CC-LDHs) and ultrasonic-intensified in 'T-mixer' pretreatment followed by conventional co-precipitation (TUC-LDHs). The synthesized samples characterized by the XRD showed that LDHs formed a typical layered double hydroxide structure and no other impurities were identified in the compound. The SEM and TEM analyses also confirmed that the size distribution of TUC-LDHs was relatively uniform (with an average size of approximate 100 nm) and layered structure was clearly visible. The BET characterization indicated that such LDHs had a large surface area (235 m² g⁻¹), which makes it a promising adsorbent material for CO₂ capture in practical application. It can be found that the CO₂ adsorption capacities of TU-LDHs, CC-LDHs and TUC-LDHs at 80°C were 0.30, 0.22 and 0.28 mmol g⁻¹, respectively. The CO₂ adsorption capacities of TU-LDHs, CC-LDHs and TUC-LDHs at 200°C were 0.33, 0.25 and 0.36 mmol g⁻¹, respectively. The order of CO₂ adsorption capacity to reach equilibrium at 80°C seen in Avrami model is: TU-LDHs > TUC-LDHs > CC-LDHs. The CO₂ adsorption/desorption cycling test reveals that TU-LDHs and TUC-LDHs have good adsorption stability than CC-LDHs.

Keywords: MgAl LDHs, ultrasonic, co-precipitation, T-mixer, CO₂ adsorption capacity, Avrami model

1. Introduction

The removal of CO₂ emission from fossil fuel combustion, especially from coal-fired power stations, has attracted much attention in recent years because of its potential negative impact on global warming and on human beings. It was reported that CO₂ concentration in atmosphere now is close to 400 ppm, which is significantly higher than the reported industrial level of 300 ppm [1]. CO₂ capture and storage (CCS) technology is considered to be an effective means to cope with the global demand of CO₂ reduction in the long run. Among many technologies existing for CO₂ capture, the use of amine-based solutions is still the main practical

technology on a large scale capture operation which could produce a series of bad effects such as toxicity, degradability, high regeneration energy requirements and corrosivity [2]. Hence, developing efficient and environmental friendly CO₂ adsorbents will be crucial to CO₂ capture. Layered double hydroxides (LDHs) are considered as good candidates for CO₂ adsorption because of their fast sorption/desorption kinetics and simple regenerability [3, 4]. LDHs are a class of ionic lamellar compounds made up of positively charged brucite-like layers with an interlayer region containing charge compensating anions and solvation molecules. The typical structure of LDHs consists of positively charged brucite-like layers, containing anions and water molecules in the interlayer spaces. Metal cations occupy the centre of octahedral structures and hydroxides occupy the vertices. The general formula of LDHs can be expressed as $[M^{2+}_{1-x}M^{3+}_x(OH)_2][A^{n-}]_{x/n}zH_2O$, where M^{2+} are divalent cations, such as Mg^{2+} , Zn^{2+} , Ni^{2+} , etc., and M^{3+} are trivalent cations, such as Al^{3+} , Ga^{3+} , Fe^{3+} , Mn^{3+} , etc. A^{n-} is a non-framework charge compensating anion, such as CO_3^{2-} , Cl^- , SO_4^{2-} , etc., and the value of x is between 0.10 and 0.33 [5].

The performance of LDHs and derived CO₂ adsorbents have been investigated for several years, and most of the studies are focused on the effects of divalent cations [6, 7], trivalent cations [8], charge compensating anions [9, 10], Mg-Al ratio [6, 11, 12], alkaline metal cations (e.g. K^+ , Cs^+ , Na^+ , etc.) [13–16], synthetic method [17], the presence of SO₂ and H₂O [18, 19], particle size [3, 20] and calcination temperature or adsorption temperature [21, 22]. Yong and Rodrigues compared several commercial hydrotalcite-like compounds that can have the average CO₂ adsorption capacity (0.2–0.5 mmol g⁻¹) at 300°C and 1 bar of CO₂ [6]. Wang et al. found that similar CO₂ capture capacities (0.41–0.46 mmol g⁻¹) can be obtained when using Mg_3Al_1 , Mg_3Ga_1 and Mg_3Fe_1 at different calcination temperatures [8]. Except for changing the composition of LDHs, controlling its particle size is also believed to be an effective way for improvement of the CO₂ capture capacity. Significant amount of efforts have been made on developing new methods to control its particle size. Hanif et al. investigated the effect of synthetic routes (co-precipitation, ultrasonication and microwave irradiation) on improving the CO₂ adsorption capacity of hydrotalcite-based sorbents in the temperature range 300–400°C [17]. They have reported that the CO₂ adsorption capacity of LDHs prepared by ultrasound-assisted route and microwaving are better than that of co-precipitation method.

Adoption of confined impinging T-jet mixer (CITJ) is a simple component that contains two inlet tubes and let two streams flow out from the tube. The local micromixing effect could be intensified during the CITJ reactor, which is beneficial for a fast homogenization of reactors. The mass transfer rate and chemical reaction rate can also be enhanced during the preparation process. This has been confirmed by the studies on the preparation of FePO₄ nanoprecursor particles of LiFePO₄ cathode material where the high specific areas can be obtained [23, 24]. Co-precipitation method is the conventional procedure used for synthesis of hydrotalcites. Ultrasonication and microwave irradiation of the synthesis gel during hydrotalcite precipitation leads to disruption in the layer stacking which in turn increases surface area [17]. To the best of our knowledge, the effect of the synthesis for the preparation of LDHs by applying jointly co-precipitation and ultrasonication in a T-jet mixer on the CO₂ absorption capacity of LDHs has not yet been reported in the literature.

In the present study, we will present a hybrid two-step method approach for preparation of MgAl layered double hydroxide (MgAl LDHs). The novel two-step preparation route utilising the MgAl LDHs synthesized from confined impinging T-jet mixer (CITJ) as seeds for future preparation. The synthesized samples were

characterized using X-ray diffraction (XRD), scanning electron microscopy (SEM), transmission electron microscopy (TEM) and BET analysis. Their performance of CO₂ adsorption was evaluated using thermogravimetric analysis (TGA). The effect of the rate of addition of Mg(NO₃)₂ and Al(NO₃)₃ on improvement of the CO₂ capture capacity of MgAl LDHs and initial NH₃H₂O is also investigated.

2. Experimental

2.1 Materials preparation

2.1.1 LDH synthesized in T-Mixer with ultrasonic process

Salt solution A (100 mL) containing a mixture of 0.03 mol L⁻¹ Mg(NO₃)₂ and 0.01 mol L⁻¹ Al(NO₃)₃ and solution B-NH₃H₂O (100 mL) with certain concentration was simultaneously transported into a 'T-type' impinging-stream reactor by means of metering pumps at the rate of 100 r min⁻¹ to produce MgAl LDHs. Ultrasonic processing was also applied during this process and the frequency of ultrasonic processing kept to be 20 kHz. The pH of the whole solution was always kept to be 10 ± 0.2 though regulating the concentration of NH₃H₂O. The resulting mixture washed with water for several times until pH = 7 and then dried at 100°C in an oven. The resulting material was denoted as **TU-LDHs**.

2.1.2 LDH synthesized by conventional co-precipitation method

For the synthesis of traditional LDHs, LDHs was prepared by co-precipitation method. The salt solution with a fixed concentration of 0.03 mol L⁻¹ Mg(NO₃)₂ and 0.01 mol L⁻¹ Al(NO₃)₃-A (200 mL) with a certain rate of addition and 1 mol L⁻¹ of NH₃H₂O were simultaneously added to the mixture at the second step, where the pH of the whole solution was always kept to be 10 ± 0.2 and continuous stirring rate is 400 r min⁻¹. The mixture was then aged for further 4 h with stirring maintained. The final obtained materials were filtered and washed with distilled water until pH = 7, followed by drying at 100°C in an oven. The obtained material was denoted as **CC-LDHs**.

2.1.3 LDH synthesized by hybrid two-step method

MgAl layered double hydroxides (MgAl LDHs) were prepared using a hybrid two-step preparation approach. The hybrid two-step preparation consists of the mother solution prepared in 'T-mixer' accompanying with ultrasonic processing (first step) and the following step of co-precipitation (second step) process. The mother solution was synthesized according to the preparation method of the above section. About 50 mL of mother solution from the above solution was put into a beaker for continuous stirring with a rate of 400 r min⁻¹. Then, 150 mL of salt solution with a fixed concentration of 0.03 mol L⁻¹ Mg(NO₃)₂ and 0.01 mol L⁻¹ Al(NO₃)₃ and 1 mol L⁻¹ of NH₃H₂O were simultaneously added to the mixture at the second step. The addition rate of salt solution was controlled by regulating the speed of peristaltic pump, where the pH of the whole solution was always kept to be 10 ± 0.2. The whole preparation process of MgAl LDHs by two steps were illustrated in **Figure 1**. The final obtained materials were filtered and washed with distilled water until pH = 7, followed by drying at 100°C in an oven. The obtained material was denoted as **TUC-LDHs**.

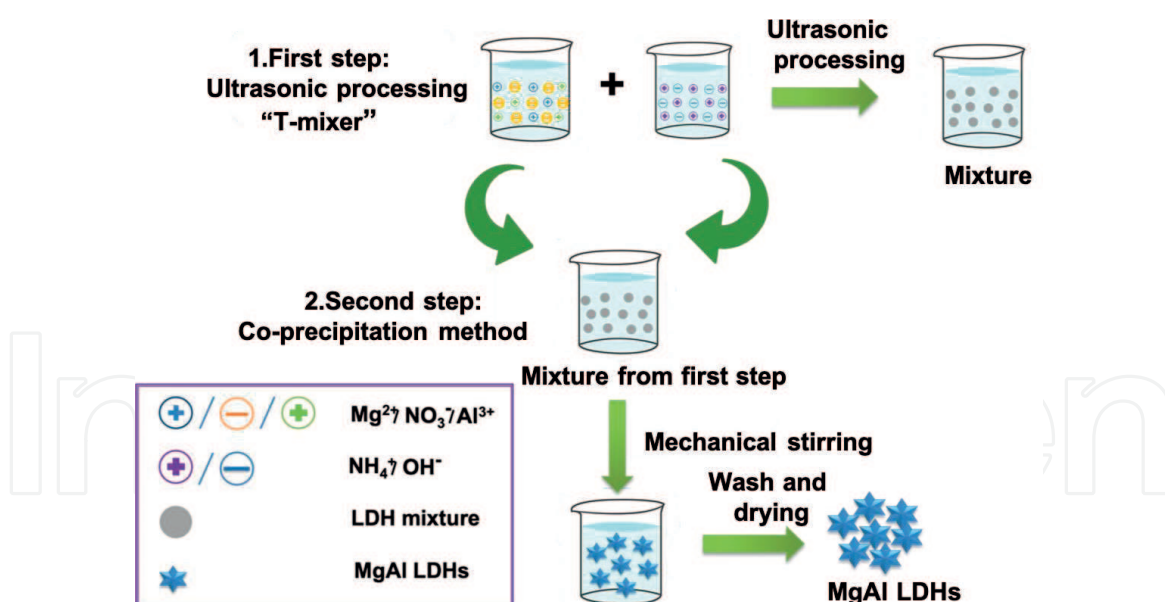


Figure 1.
Schematic illustrating the preparation process of MgAl LDHs by hybrid two steps.

2.2 Materials characterization

The structures of MgAl LDHs were characterized using a combination of methods including BET-specific surface areas, X-ray diffraction (XRD), scanning electron microscopy (SEM), energy dispersive X-ray spectroscopy (EDX) analysis and transmission electron microscope (TEM).

2.2.1 BET

Nitrogen adsorption/desorption isotherms were carried out on a Micromeritics ASAP2020 surface area and pore size analyser at 77 K. Before conducting each measurement, the prepared LDHs were first degassed at 110°C overnight.

2.2.2 XRD

The structure of the prepared samples were analysed by XRD through conducting in a Bruke-AXS D8 advance powder diffractometer using Cu-K α radiation ($\lambda = 1.5418 \text{ \AA}$) and a power of 40 kv*20 Ma, where the diffraction patterns were recorded in the range $2\theta = 5\text{--}80^\circ$ with a step size of 0.01° .

2.2.3 SEM and EDXS

The morphologies of synthesized LDHs were observed using SEM produced from ZEISS ZIGMA 174C CZ. The element analysis was conducted by use of an Oxford Instrument INCAx-act PentaFET® Precision EDXs.

2.2.4 TEM

High-resolution TEM images were obtained using JEM-2100 electron microscope operating at 200 kV, whereby a drop of solution was placed onto a Cu grid and dried in infrared lamp for several minutes.

2.3 Carbon dioxide adsorption measurements

The CO₂ adsorption test and regenerability of the synthesized adsorbents were measured by Netzsch TG 209 F1 thermogravimetric analyser (TGA) at atmosphere pressure under dry conditions. Pure CO₂ gas was used to carry out the whole adsorption/desorption measurement. Before adsorption test, all the samples were calcined at 500°C for 5 h in an Ar atmosphere. About 10 mg of sample loaded into an alumina crucible was heated from 25 to 105°C at 10°C min⁻¹ under N₂ atmosphere for 60 min and then switched to desired temperature (80, 150 and 200°C) at the rate of 10°C min⁻¹. During the isothermal stage, the gas input changed from N₂ to CO₂ and held for 90 min. The CO₂ adsorption capacity of the sample- q_t (mmol g⁻¹) was calculated according to the weight gain of the sample and expressed as the mole of CO₂ absorbed per gram of adsorbent:

$$q_t = \frac{m_t - m_o}{m \times M} \times 1000 \quad (1)$$

where m_o and m_t (mg) are the initial mass of adsorbent for CO₂ adsorption and mass of adsorbent for CO₂ adsorption at time t, respectively. m is the total mass of sorbent (mg) and M is molar mass of CO₂ (44 mol g⁻¹).

In the absorption/desorption cycle, about 10 mg of the above calcined samples was heated from 25 to 105°C at 10°C min⁻¹ under N₂ atmosphere (40 mL min⁻¹) for 60 min and then switched to 80°C at a cooling rate of 10°C min⁻¹. After adsorption, the desorption process was carried out as the gas input was switched from CO₂ to N₂ at 105°C. The adsorption/desorption process was repeated in six cycles.

2.4 Error analysis

To determine the validity of isotherm and kinetics models, two different error functions, i.e. chi-square (X^2) and normalized standard deviation $\Delta q(\%)$, and correlation coefficient equation R^2 were evaluated between experimental and calculated data, which are given by

$$\text{Chi - square : } X^2 = \sum_{i=1}^n \frac{(q_t - q_e)^2}{q_e} \quad (2)$$

$$\text{Normalized standard deviation : } \Delta q(\%) = \sqrt{\frac{\sum_{i=1}^n [(q_t - q_e)/q_e]^2}{n - 1}} \times 100 \quad (3)$$

$$\text{Correlation coefficient equation : } R^2 = 1 - \left(\frac{\sum_{j=1}^N (q_t - q_e)^2}{\sum_{j=1}^N (q_t - \bar{q}_e)^2} \right) \times \left(\frac{N - 1}{N - p} \right) \quad (4)$$

where q_t and q_e are CO₂ uptake determined by experiment and computed by model, respectively. q_e is the mean experimental data, p is the number of model parameters and N is total number of experimental points. The most suitable model to describe the CO₂ adsorption process is the one with highest R^2 value.

3. Results and discussion

3.1 Synthesis and characterization of LDHs prepared by different ways

Co-precipitation method is a common method used in preparation of MgAl LDHs materials in the previous studies. The main requirement for improving the CO₂ adsorption capacity of MgAl LDHs is to develop it with high surface area and pore volume. It is well known that the formation process of MgAl LDHs includes both nucleation and growth process. Controlling the process of nucleation properly may have an effect on the whole size of MgAl LDHs, thus increasing its surface area. Here, we reported the first synthesise of MgAl LDHs using a hybrid two-step method. At first step, the salt solution and initial concentration of NH₃H₂O solution were transported into ‘T-type’ impinging-stream reactor. Two solutions interact on each other on the ‘T-type’ impinging-stream reactor and ultrasonic wave were also applied in the interaction process. At second step, the conventional co-precipitation method was used. This means that a certain rate of salt solution and NH₃H₂O were simultaneously added to the mixture to produce the MgAl LDHs. The chemical and physical effects of ultrasonic irradiation originated from acoustic cavitation lead to rapid reaction rate and change the selectivity performance of the reaction [25], thus improving the nucleation of MgAl LDHs.

The XRD patterns of MgAl LDHs prepared using three different methods are shown in **Figure 2**. For all the samples, the characteristic reflections based on the structure of (PDF #35-0965) were clearly observed, which can be indexed to (i) (00 l) peaks of (003) and (006) with corresponding to the basal spacing and higher order reflections; (ii) (0 kl) peaks of (012), (015) and (018) with broad reflections; (iii) sharp ($hk0$) and (hkl) peaks of (110) and (113). It can be seen that LDHs samples synthesized under different conditions have similar structures. The lattice parameter a and c are calculated according to the parameters of (110) and (003) plane assuming a 3R stacking of layer structure, where the value a ($a = 2d_{110}$) represents average distance between two metal ions and c is three times of the brucite-like layer and interlayer distance (d_{003}). The lattice parameter a is almost independent of the synthesis method, which can be explained that it was affected

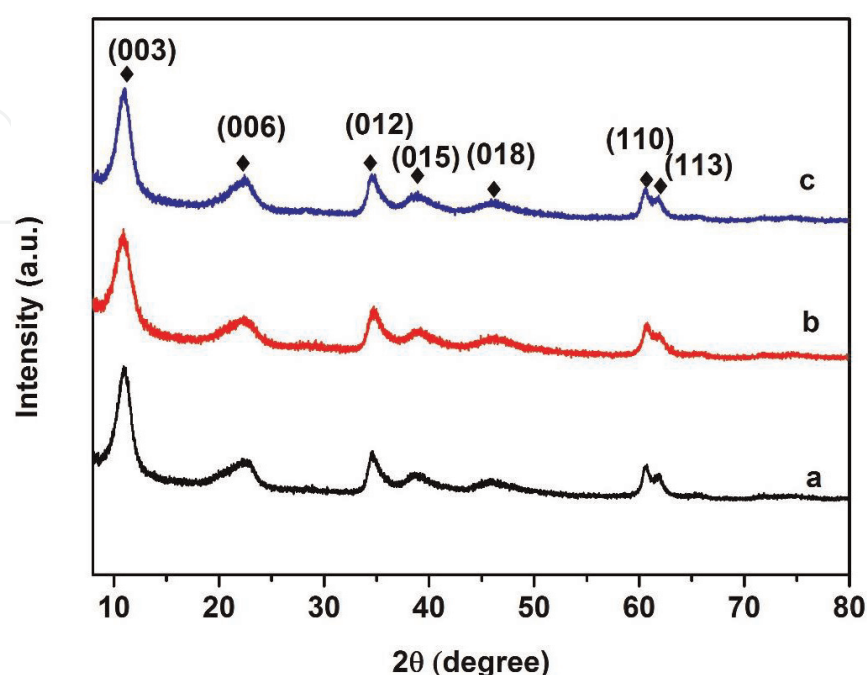


Figure 2.
XRD patterns for MgAl LDHs prepared using (a) TU method, (b) CC method and (c) TUC method.

by the type of metal cation (Mg²⁺ and Al³⁺). Although LDHs are prepared by three different ways, the metal cation of Mg²⁺ and Al³⁺ still keep the same without any change. Similar observations can be found in the research of Wang et al. for the formation of LDHs by co-precipitation and IEP method [20]. Concerning the lattice parameter c, it was affected by three main factors: the average charge of the metal cations, the nature of the interlayer anion and the water content. TU-LDHs have lowest lattice parameter c compared to other two LDHs. All the samples use the same anion and metal cations so that the slight difference between samples may be related to a slow water content in the layer.

The crystalline size of particles was calculated using the *Debye-Scherrer's formula*

$$D = \frac{0.89\lambda}{\beta \cos \theta} \tag{5}$$

where D is the grain size (nm), λ is the wavelength of the X-ray radiation, β is the full width at half maximum and λ, θ is the angle of diffraction. The crystallite size along the c direction was calculated according to (003) and (006) diffraction peaks. The values given in **Table 1** showed that the crystallite size in the c direction by TU-LDHs and TUC-LDHs were a slightly higher than the crystallite size of CC-LDHs. There is no obvious reduction of crystallite size in the c direction of materials prepared by three different methods.

N₂ adsorption-desorption isotherm of MgAl LDHs is given in **Figure 3**. All the adsorbents show a Type IV isotherm according to the IUPAC classification, which is associated with mesoporous materials [26]. TUC-LDHs and CC-LDHs show a H3 type hysteresis loop, suggesting that the pores are produced by ‘slit-shaped’ of plate-like particles [27]. This type of isotherm is commonly observed in the mesoporous stacking structure of sheet-like 2D crystallites [28]. In the case of TU-LDHs, it shows a H2 type hysteresis loop corresponding to a complex and interconnected pore structure, indicating that the pores are produced by rapid nucleation process. This difference could be related to the different synthetic route applied in this work. The surface area (S_{BET}) of the samples were determined using BET (Brunauer, Emmett and Teller) model. The total volumes (V_{Total}) were calculated according to the amount of nitrogen (N₂) absorbed at a relative pressure (P/P_O) of 0.99. The pore volumes were calculated from the desorption branch of the isotherms using the Barrett-Joyner-Halenda (BJH) method, for the pores between 1.7 and 300.0 nm. **Table 2** lists the textural parameters of MgAl LDHs obtained from N₂ adsorption-desorption isotherms. It can be seen clearly that the S_{BET} of TUC-LDHs is the highest of 235.3 m² g⁻¹ compared to 198.7 m² g⁻¹ for TU-LDHs and 148.1 m² g⁻¹ for CC-LDHs as well as the pore sizes (90.83 Å) and highest pore

Property	TU-LDHs	CC-LDHs	TUC-LDHs
<i>d</i> ₀₀₃ (nm)	0.7977	0.8058	0.8011
<i>d</i> ₁₁₀ (nm)	0.1518	0.1516	0.1519
<i>a</i> ^a (nm)	0.3036	0.3032	0.3038
<i>c</i> ^b (nm)	2.3931	2.4174	2.4033
Crystallite size in c direction (nm) ^c	8.65	7.35	8.63

^a*a* = 2*d*₁₁₀
^b*c* = 3*d*₀₀₃
^cValue calculated from (003) and (006), according to Debye-Scherrer's formula.

Table 1.
Lattice parameters of LDHs prepared by different methods.

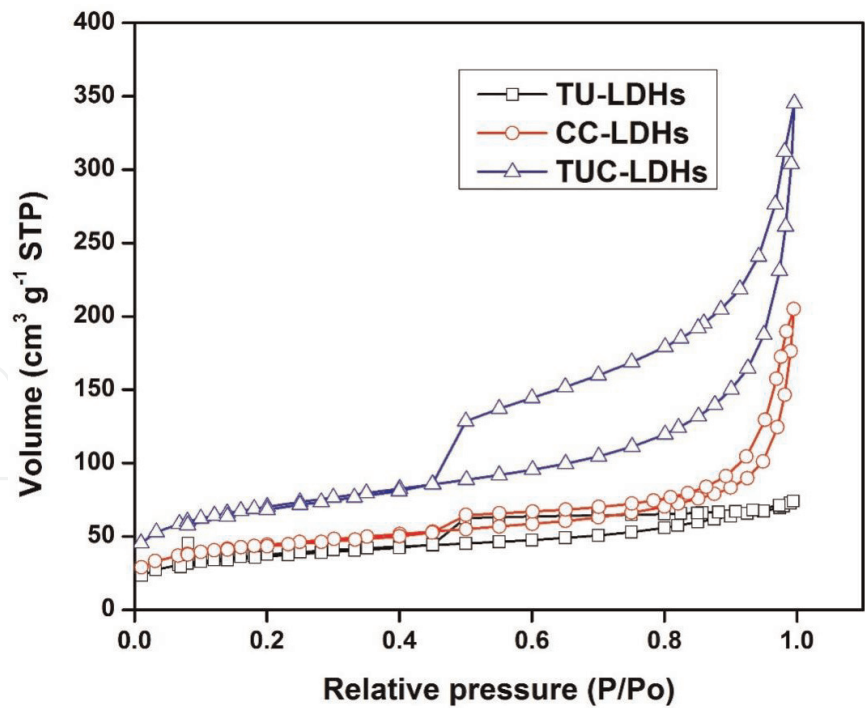


Figure 3.
Nitrogen adsorption-desorption isotherm for TU-LDHs, CC-LDHs and TUC-LDHs.

Sample name	BET surface area (m ² g ⁻¹)	Average pore diameter (Å)	Pore volume (cm ³ g ⁻¹)
TU-LDHs	198.7	24.4	0.08
CC-LDHs	148.1	85.61	0.28
TUC-LDHs	235.3	90.83	0.48

Table 2.
Textural parameters of MgAl LDHs obtained from N₂ adsorption-desorption isotherms.

volume (0.48 cm³ g⁻¹). Both of TUC-LDHs and CC-LDHs facilitate the macro-structure of pores. Although TU-LDHs has the second largest S_{BET}, its pore sizes (24.4 Å) and pore volume (0.08 cm³ g⁻¹) are the lowest in comparison with other two materials. This indicates that the TU method contributes to the formation of mesoporous structure. The increase in surface area of TU-LDHs is very likely caused by the enhanced micromixing in the ‘T-mixer’, where the use of ultrasonication can intensify the turbulent eddies and those microbubble bursting that erode the surface area of hydrotalcites of layered structure through removal of the interlayer anions [17]. This effect may be more evident as TUC-LDHs compared with CC-LDHs possess smaller size so that the erosion can be taking place for TUC-LDHs. This explanation seems to be supported by SEM and TEM observation of TUC-LDHs.

The size, morphologies and structure of MgAl LDHs prepared by different methods are characterized using FESEM. It can be clearly seen from **Figure 4(a)** that the morphology and structure of TU-LDHs looks like a house-of-cards-type stacking structure, which is similar to that from ‘exfoliation-self-assembly’ method. However, no significant differences can be observed between CC-LDHs and TUC-LDHs, as shown in **Figure 4(b)** and **(c)**. Both of them show rose-like morphology, while morphology of TUC-LDHs looks quite loose compared with CC-LDHs. In order to further explore the morphology and structure of the prepared LDHs, CC-LDHs and TUC-LDHs were also characterized using TEM analysis. The TEM image in **Figure 4(f)** shows that the TUC-LDHs has an average size of 100 nm and

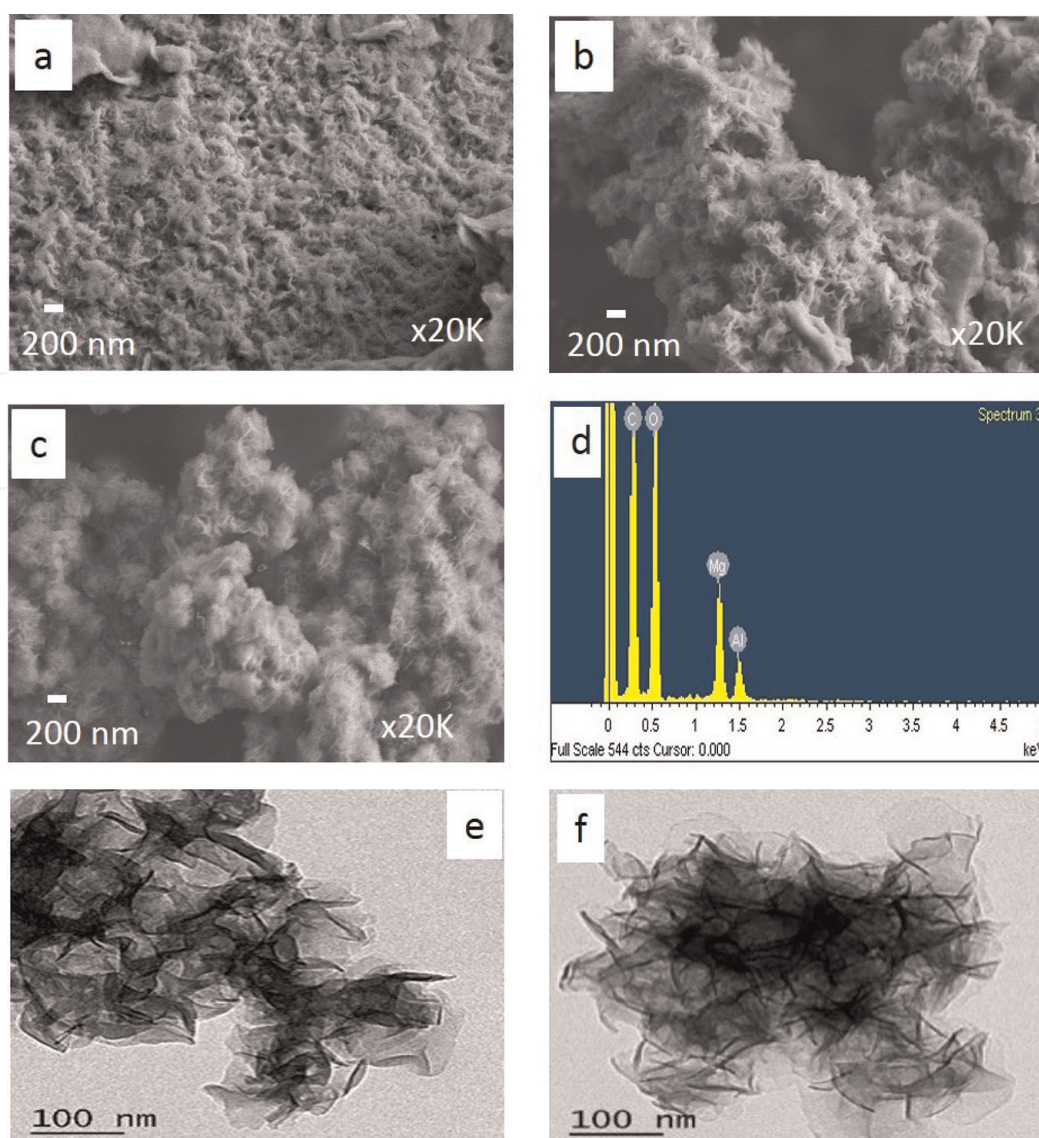


Figure 4. SEM images of MgAl LDHs for (a) TU-LDHs, (b) CC-LDHs and (c) TUC-LDHs; EDS of (d) TUC-LDHs; TEM of (e) CC-LDHs and (f) TUC-LDHs.

thickness of 10–20 nm. However, the average size and thickness of CC-LDHs (shown in **Figure 4(e)**) are significantly larger than in the case of TUC-LDHs. In addition, EDX analysis of TUC-LDHs (shown in **Figure 4(d)**) is given as a rough molar ratio of $M_{\text{Mg/Al}} \approx 3$, which is consistent with chemical composition of raw materials.

From the above XRD, BET, SEM and TEM results, further analyses are as follows. Mixing is very slow, relying on the molecular diffusion process due to the absence of turbulence in a low Reynold number. However, the mixing can be enhanced by changing the geometry of mixing channel from conventional agitated vessel to ‘T-mixer’. Ultrasonic wave, an external energy force, can generate additional force to interfere with the flow field in the ‘T-mixer’ channel so that a high level of supersaturation is generated and micromixing process of chemical reaction can be enhanced in extremely short time ($\sim 10^{-7}$ s) [23, 24]. Thus, the high level of supersaturation contributes to form large amounts of nuclei in a short time, resulting in a small average particle size accumulating together, which is consistent with the BET results in **Table 2**. Finally, the layered structure of TU-LDHs seems to stack together tightly. For TUC-LDHs, the presence of TU-LDHs during the growth of TUC-LDH may introduce defects into LDH structure, through modified nucleation conditions or induced curvature [29]. The final particles exhibit fluffy shapes

and the flake-like structures are formed. Another important reason may be related to the isoelectric point (IEP) of MgAl LDHs. The IEP of MgAl LDHs is around 10, so it can be positively ($\text{pH} > \text{IEP}$), neutrally ($\text{pH} = \text{IEP}$), or negatively ($\text{pH} < \text{IEP}$) charged depending on the relationship between the IEP and the pH. Because it is electronic neutrally on its surface, its growth is inhibited due to the repulsive force between negatively charged TUC-LDH primary particles and $\text{Al}(\text{OH})_4^-$, CO_3^{2-} , OH^- anions. Hence, the formation rate of LDHs is so fast that the growth in all directions under such basic conditions. It is well known that the formation process of TUC-LDH includes both nucleation and growth process. In our experiment, the growing of TUC-LDH is based on the mixture solution, which suggests that it supplies a nucleation environment for TUC-LDH growth, then the directions of LDHs growth could be determined. As reported in literature, the deposition of a colloidal suspension of TUC-LDH on substrates, such as glass or silicon, generally leads to the TUC-LDH nanoplatelets having preferred orientation with their c-axis perpendicular to the substrate. The fact that the MgAl- CO_3 LDH nanoplatelets are perpendicularly attached to the surface via their edges suggests they are grown onto the substrate via a strong chemical interaction. Wang et al. reported the first synthesis of nanosized spherical MgAl LDHs using IEP method [20].

3.2 TGA analysis

Calcination is a very important step for activating the MgAl LDHs, because the fresh LDHs do not contain much basic sites so that the CO_2 uptake capacity is quite low. **Figure 5** shows the TGA spectrum of the three different types of synthesized LDHs. The curves for the LDHs prepared by three methods are all fairly similar in shape. The TGA spectra of TU-LDHs show a weight loss of 13% between 50 and 207°C due to the loss of the physisorbed water. In the second weight loss, 33.2% occurred between 207 and 600°C, which is mainly caused by dehydroxylates and decarbonates of LDHs to a large extent, finally leading to the formation of a mixed oxide with a three-dimensional network [8]. For CC-LDHs, the first weight loss

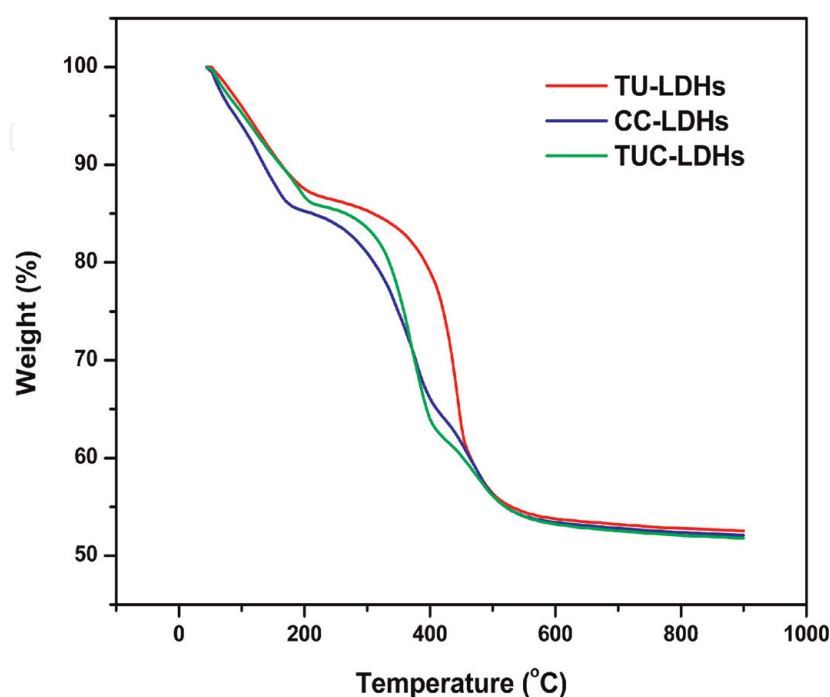


Figure 5.
TGA spectrum of the three different types of synthesized LDHs.

(14%) was found to occur between 50 and 170°C. In the temperature range of 50 and 214°C, TUC-LDHs observed a weight loss of 14%. There are no much differences during the second weight loss process among three samples.

3.3 CO₂ adsorption capacity

The CO₂ capture capacity of the above-mentioned three types of LDHs, including TU-LDHs, TUC-LDHs and CC-LDHs, were evaluated using isothermal CO₂ adsorption tests. In the present work, we are particularly interested in whether the modified methods would influence the final CO₂ adsorption capacity or not. The CO₂ adsorption capacities of the different types of LDHs are given in **Figure 6**. All the samples were first calcined at 500°C before each CO₂ adsorption test. Then, the thermogravimetric adsorptions of CO₂ on the samples were measured at 80, 150 and 200°C using a TGA analyser. It can be found that the CO₂ adsorption capacities of TU-LDHs, CC-LDHs and TUC-LDHs at 80°C are 0.30, 0.22 and 0.28 mmol g⁻¹, respectively. While for the sample at 200°C, the CO₂ adsorption capacities of TU-LDHs, CC-LDHs and TUC-LDHs are 0.33, 0.25 and 0.36 mmol g⁻¹, respectively. The CO₂ adsorption capacity of LDHs at 200°C was higher than that of 80 and 150°C. The main reason maybe that a surface phenomenon and chemical interactions are restricted at 80°C due to the higher activation energy [19]. We can see that TUC-LDHs had better adsorption capacity than other two TU-LDHs and CC-LDHs independent of adsorption temperature. The removal of water during calcination process leads to the formation of channels and pores. As the BET surface area of TUC-LDHs is higher than TU-LDHs and CC-LDHs, it could increase more basic sites for CO₂ adsorption [7].

3.4 Kinetic studies of CO₂ capture performance

In order to get a good adsorbent, fast adsorption kinetics is considered as one of the most important parameters to evaluate the adsorbent in a dynamic process. Hence, the ability of withstanding large adsorbate flows are connected with the rate of adsorption. Here, we mainly study the PFO model and Avrami model on the function of CO₂ adsorption on our LDHs [30]. The general sorption rate equations are expressed as:

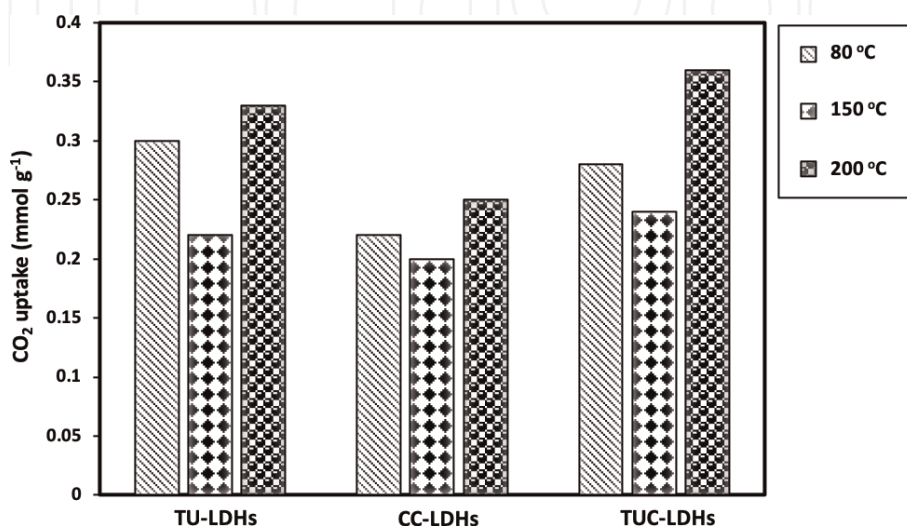


Figure 6.
CO₂ adsorption capacities of the different types of LDHs at different temperatures.

Pseudo-first-order (PFO) model:

$$q_t = q_e(1 - \exp(-k_f t)) \quad (6)$$

Avrami model:

$$q_t = q_e(1 - \exp(-(k_A t)^{n_A})) \quad (7)$$

where q_e is the adsorption capacity at equilibrium and at time t , respectively, k_f is the kinetic parameter of pseudo-first order model, k_A is the kinetic parameter of Avrami model, the Avrami exponent and n_A is a factionary number, which reflects the adsorption mechanism.

To investigate the CO₂ adsorption kinetics of LDHs, **Figure 7** shows that the CO₂ uptake vs. time of TU-LDHs, CC-LDHs and TUC-LDHs at 80, 150 and 200°C and the corresponding profiles as predicted by pseudo-first-order and Avrami kinetic models. From the figure, it could be seen that the adsorption curves of LDHs

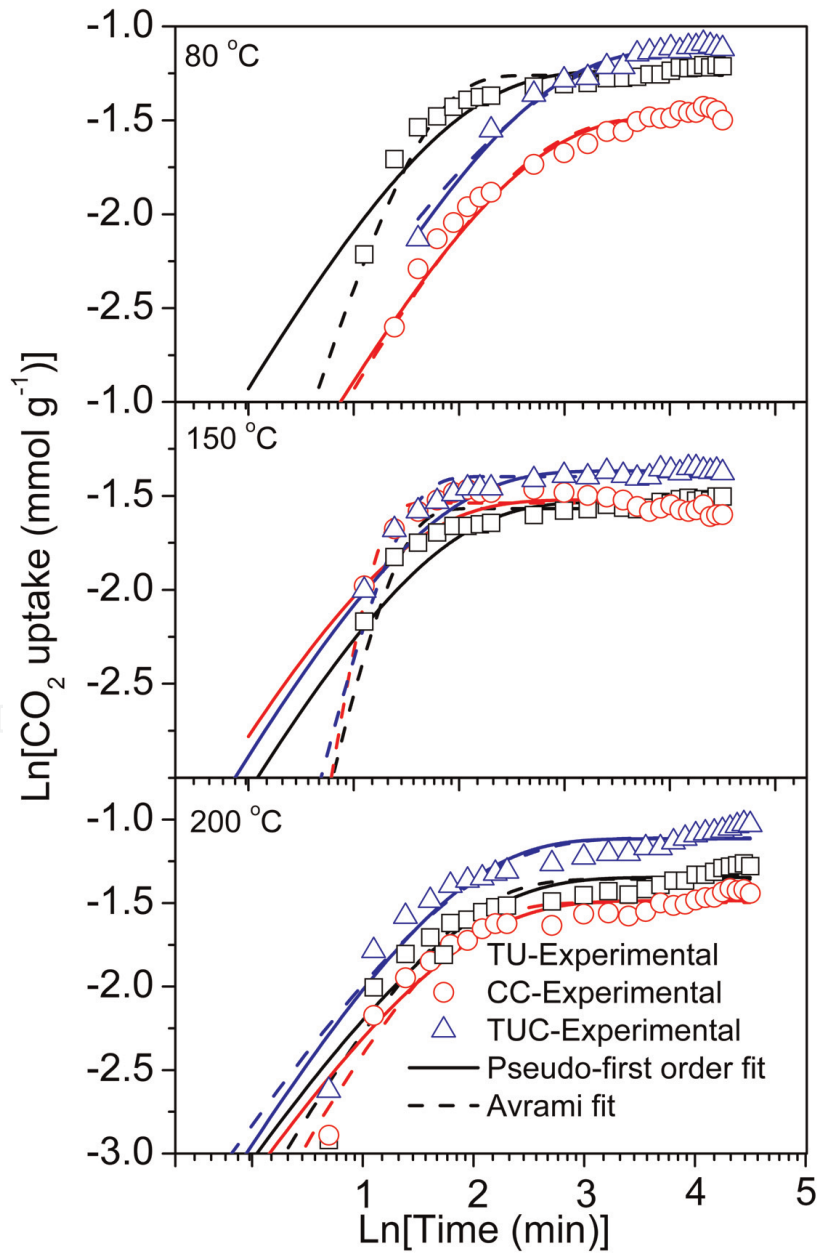


Figure 7. Experimental CO₂ uptake on different LDHs at different temperatures and corresponding fit to kinetic models: (□) TU-LDHs, (○) CC-LDHs, (△) TUC-LDHs, (—) Pseudo-first order fit and (---) Avrami fit.

showed obvious two-stage adsorption process under different adsorption conditions. That means, adsorption process of CO₂ sorption by LDHs consists of a fast reaction stage and a much slower second stage controlled by CO₂ diffusion. Clearly, both of the models predict CO₂ adsorption process well. But, Avrami kinetic model offers a better description of the adsorption of CO₂, since the R² value was higher and X² and Δq yielded low values in comparison of pseudo-first order model. Therefore, Avrami kinetic model is more suitable to predict the CO₂ adsorption process of LDHs in our experiment. **Table 3** shows the values of kinetic constants and the characteristic parameters from the kinetic model, along with the X², Δq, R² as calculated using Eqs. (1)–(3). This is because pseudo-first order kinetic model is suitable for explaining the low surface coverage adsorption, and hence describes the early stages of adsorption [30, 31]. In the process of CO₂ adsorption by LDHs, it is not a simple physical adsorption process. LDHs consists of positively charged Mg-Al-OH brucite type network in an octahedral network. After calcination, the LDHs gradually loses its interlayer water and form a mixed oxide with sufficient basic sites which are favourable for CO₂ sorption. It is a complex reaction in combination of physical and chemical process during CO₂ uptake [19, 32]. Avrami kinetic model is logical to attribute the fitting of CO₂ uptake process in our experiment.

The pseudo-first order model and Avrami model kinetic parameters k_f and k_A are the time scales for measuring the process to reach equilibrium. The higher k_f and k_A , the quicker speed for the process to reach equilibrium. It can be observed from **Table 3** that k_f and k_A of CC-LDHs and TUC-LDHs increase with temperature overall. When the temperature increases, the molecule's speed (kinetic energy) also increases. So, the CO₂ molecules will migrate faster inside the pores, which in turn will result in an increase in the rate of diffusion. Hence, it is reflected in the form of CO₂ uptake curves with much steeper ones (shown in **Figure 7**). For TU-LDHs, k_f and k_A do not change much as the temperature increases. This might be caused by the fact that the pores of TU-LDHs are easy to saturate or block during the CO₂ adsorption even at high temperature due to its small pore size and volume. This phenomenon usually occurs in the microporous material such as porous MgO [33], zeolites [34] and active carbons [35]. The order of CO₂ adsorption capacity to reach equilibrium (k_A) at 80°C seen in Avrami model is: TU-LDHs > TUC-LDHs > CC-LDHs. The order of CO₂ adsorption capacity to reach equilibrium at 150°C seen in Avrami model is: CC-LDHs > TU-LDHs = TUC-LDHs. When the CO₂ adsorption temperature is 200°C, the time of reaching equilibrium by three materials is almost the same. This indicates that TU-LDHs and TUC-LDHs show the potential application of reaching equilibrium to absorb the CO₂ gas at low temperature (<100°C). The Avrami exponent n_A reflects the extent of driving force on adsorption apparatus. The data of n_A in the range of 1–4 suggest that CO₂ adsorption occurs more than one-reaction pathway from adsorption sites [36].

Here, the schematic CO₂ adsorption mechanism on LDHs is shown in **Figure 8**. During the CO₂ adsorption process in porous material, it is known that CO₂ molecule diffuses through the gas film to pore structure among the agglomerate particles and the crystalline grains; or the CO₂ molecule interacts with the adsorbent (surface reaction). Generally, the surface reaction process is quite rapid, and the resistance associated with the surface adsorption can be assumed to be negligible [33]. The whole process of CO₂ adsorption can be simplified that CO₂ permeates in a tube with tubular structure. As mentioned above, TUC-LDHs has the largest BET surface area as well as pore size and volume. The effective absorbed area is larger and it is easy to absorb the CO₂ in the tubular tube with less resistance. This trend is obvious when the adsorption is operated at a high temperature. For the TU-LDHs, although it shows a second largest surface area, its pore size and volume are limited. The pores of LDHs are easy to block when the CO₂ concentration in the tubular tube

Parameters for Simulation												
Material	Temperature (°C)	Pseudo-first order model					Avrami model					
		K_f (s ⁻¹)	q_e (mmol g ⁻¹)	X^2	Δq (%)	R^2	K_f (s ⁻¹)	q_e (mmol g ⁻¹)	n_a	X^2	Δq (%)	R^2
TU-LDHs	80	0.20	0.29	0.021	7.05	0.9131	0.22	0.28	1.82	0.019	5.78	0.9544
	150	0.24	0.22	0.015	5.74	0.9149	0.27	0.21	2.64	0.019	6.68	0.9463
	200	0.20	0.26	0.024	6.93	0.9420	0.21	0.26	1.22	0.042	11.06	0.9434
CC-LDHs	80	0.10	0.23	0.017	11.18	0.9717	0.11	0.23	1.06	0.017	10.33	0.9708
	150	0.33	0.22	0.034	8.02	0.7791	0.32	0.21	3.9	0.013	5.14	0.9640
	200	0.21	0.23	0.16	21.42	0.9337	0.22	0.22	1.28	0.023	8.32	0.9399
TUC-LDHs	80	0.11	0.33	0.015	8.37	0.9774	0.12	0.32	1.1	0.016	7.35	0.9775
	150	0.25	0.25	0.013	5.04	0.9222	0.27	0.25	2.41	0.015	5.63	0.9727
	200	0.20	0.33	0.024	6.93	0.9447	0.20	0.33	1.09	0.043	11.06	0.9430

Table 3.
Values of the kinetic model parameters for CO₂ adsorption on LDHs.

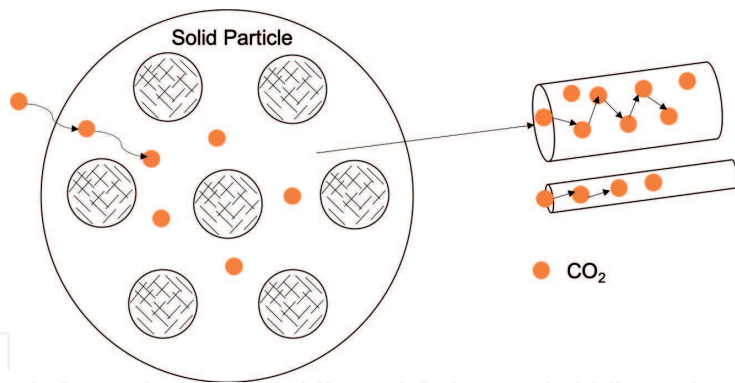


Figure 8.
Schematic CO₂ adsorption mechanism on LDHs.

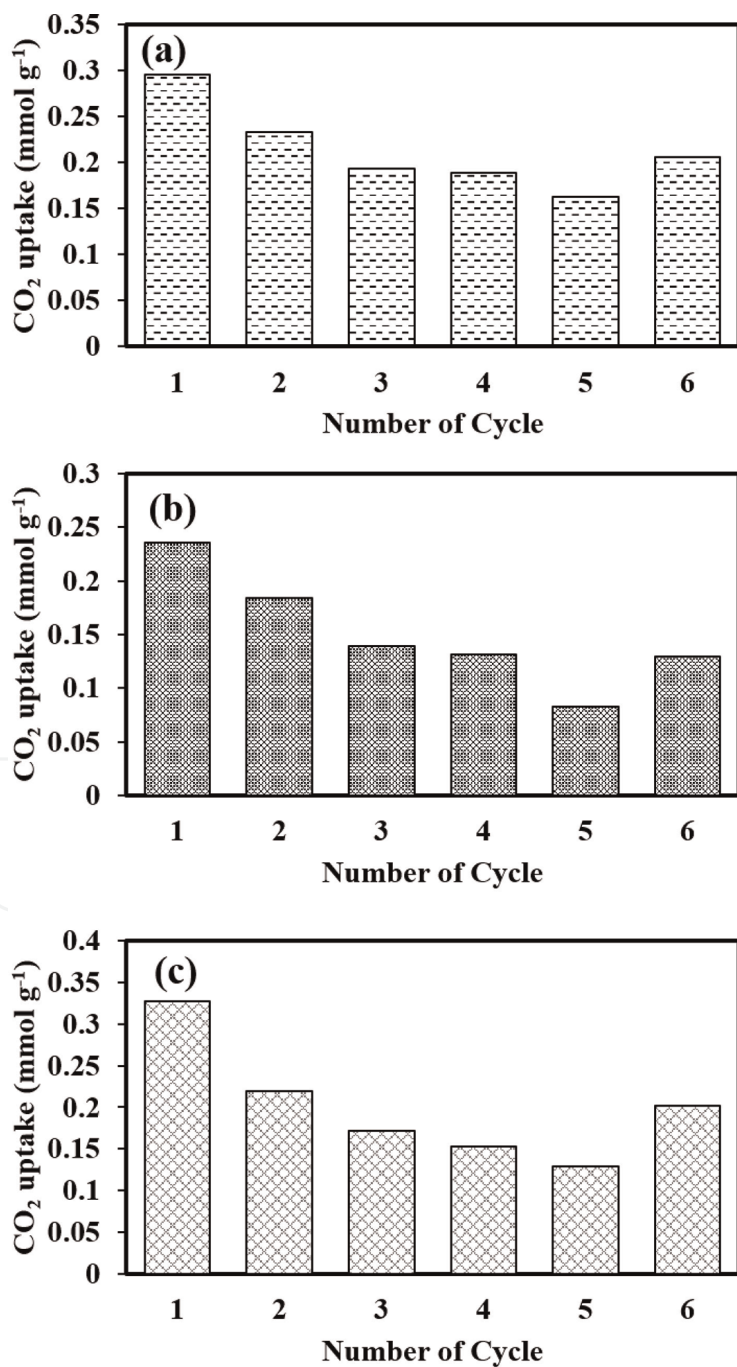


Figure 9.
CO₂ uptake using temperature during six cycles at 80°C (a) TU-LDHs, (b) CC-LDHs and (c) TUC-LDHs.

increases; finally, the CO₂ diffusion rate will slow down. As for CC-LDHs, it has the lowest effective surface area, which finally influences its CO₂ adsorption ability.

3.5 CO₂ adsorption/desorption cycling test

For practical applications, the stability of adsorbents during the adsorption-desorption process should be considered. Hence, it is badly needed to test its cycle operation. **Figure 9** shows six successive runs of adsorption-desorption isotherms of LDHs at 80°C. TUC-LDHs shows an initial cyclic adsorption capacity (0.33 mmol g⁻¹). However, it decreased to CO₂ adsorption capacity of 0.21 mmol g⁻¹ at second cycle, which is 67% of the original capacity. At six cycles of absorption, the adsorption capacity is still 0.2 mmol g⁻¹ with 60.6% of the original capacity although CO₂ adsorption is fluctuated during the middle process. The decrease of adsorption capacity over several cycles has also been reported by several research groups. The main reason for the decrease of CO₂ adsorption is possible that some chemical sorption sites are blocked during the subsequent adsorption/desorption cycles. TU-LDHs and CC-LDHs show an initial CO₂ adsorption capacity of 0.30 and 0.24 mmol g⁻¹, in which the retentions could achieve as high as 69.8 and 54.7%, respectively. These results indicate that the TU process played a role not only in increasing CO₂ sorption capacity, but also in improving the cyclic performance. The experimental results show that stability of hydrotalcites synthesized by both TUC and TU method are higher than the conventional prepared LDHs, which seems promising adsorbents for CO₂ adsorption.

4. Conclusions

The present studies have demonstrated that the MgAl LDHs as a CO₂ adsorbent can be synthesized successfully through an ultrasonic assisted ‘T-mixer’ (TU-LDHs), hybrid two-step preparation method (TUC-LDHs) and conventional co-preparation (CC-LDHs) method. The conclusions reached as the results of the current study are as follows:

1. It was found that the prepared TUC-LDHs had a clear layered structure and the average size was approximately 100 nm with the largest surface area, which makes it a promising adsorbent material for CO₂ capture in practical application.
2. Increasing the adsorption temperature is benefit to improve the CO₂ adsorption capacity of LDHs. The highest capture capacity was got when the CO₂ adsorption took place at 200°C by TUC-LDHs.
3. The CO₂ adsorption stability of TU-LDHs and TUC-LDHs is higher than the CC-LDHs after six adsorption/desorption cycles.

Acknowledgements

This work was financially supported by National Natural Science Foundation of China (NSFC) (Grant No. 21576141) and Zhejiang Provincial Natural Science Foundation (Grant No. LY15B060001). This work was carried out at the International Doctoral Innovation Centre (IDIC). Xiani Huang would also like to

acknowledge the support through the Ph.D. scholarship of the International Doctoral Innovation Centre (IDIC) of University of Nottingham Ningbo China.

Abbreviations

TU-LDHs	MgAl LDHs prepared by ultrasonication-intensified in ‘T-mixer’
CC-LDHs	MgAl LDHs prepared by conventional co-precipitation
TUC-LDHs	MgAl LDHs prepared by ultrasonic-intensified in ‘T-mixer’ pretreatment followed by conventional co-precipitation

Author details

Xiani Huang¹, Xiaogang Yang^{1*}, Guang Li¹, Collins I. Ezech¹, Chenggong Sun² and Collins Snape²

¹ Department of Mechanical, Materials and Manufacturing Engineering, University of Nottingham Ningbo China, Ningbo, P.R. China

² Department of Chemical and Environmental Engineering, University of Nottingham, University Park, Nottingham, UK

*Address all correspondence to: xiaogang.yang@nottingham.edu.cn

IntechOpen

© 2019 The Author(s). Licensee IntechOpen. This chapter is distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/3.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited. 

References

- [1] Yu C-H, Huang C-H, Tan C-S. Mint: A review of CO₂ capture by absorption and adsorption. *Aerosol and Air Quality Research*. 2012;**12**:745-769. DOI: 10.4209/aaqr.2012.05.0132
- [2] Stevens L, Williams K, Han WY, Drage T, Snape C, Wood J, et al. Mint: Preparation and CO₂ adsorption of diamine modified montmorillonite via exfoliation grafting route. *Chemical Engineering Journal*. 2013;**215–216**: 699-708. DOI: 10.1016/j.cej.2012.11.058
- [3] Manohara GV. Mint: Exfoliation of layered double hydroxides (LDHs): A new route to mineralize atmospheric CO₂. *RSC Advances*. 2014;**4**: 46126-46132. DOI: 10.1039/C4RA08865D
- [4] Kou X, Guo H, Ayele EG, Li S, Zhao Y, Wang S, et al. Mint: Adsorption of CO₂ on MgAl-CO₃ LDHs-derived sorbents with 3D nanoflower-like structure. *Energy and Fuels*. 2018;**32**: 5313-5320. DOI: 10.1021/acs.energyfuels.8b00024
- [5] Wang J, Stevens LA, Drage TC, Wood J. Mint: Preparation and CO₂ adsorption of amine modified Mg–Al LDH via exfoliation route. *Chemical Engineering Science*. 2012;**68**:424-431. DOI: 10.1016/j.ces.2011.09.052
- [6] Yong Z, Rodrigues AE. Mint: Adsorption of carbon dioxide onto hydrotalcite-like compounds (HTLcs) at high temperatures. *Industrial and Engineering Chemistry Research*. 2001;**40**:204-209. DOI: 10.1021/ie000238w
- [7] Aschenbrenner O, McGuire P, Alsamaq S, Wang J, Supasitmongkol S, Al-Duri B, et al. Mint: Adsorption of carbon dioxide on hydrotalcite-like compounds of different compositions. *Chemical Engineering Research and Design*. 2011;**89**:1711-1721. DOI: 10.1016/j.cherd.2010.09.019
- [8] Wang Q, Tay HH, Ng DJW, Chen L, Liu Y, Chang J, et al. Mint: The effect of trivalent cations on the performance of Mg-M-CO₃ layered double hydroxides for high-temperature CO₂ capture. *ChemSusChem*. 2010;**3**:965-973. DOI: 10.1002/cssc.201000099
- [9] Hutson ND, Attwood BC. Mint: High temperature adsorption of CO₂ on various hydrotalcite-like compounds. *Adsorption*. 2008;**14**:781-789. DOI: 10.1007/s10450-007-9085-6
- [10] Hou XJ, Li H, He P, Sun Z, Li S. Mint: Structural and electronic analysis of Li/Al layered double hydroxides and their adsorption for CO₂. *Applied Surface Science*. 2017;**416**:411-423. DOI: 10.1016/j.apsusc.2017.04.187
- [11] Kim S, Jeon SG, Lee KB. Mint: High-temperature CO₂ sorption on hydrotalcite having a high Mg/Al molar ratio. *ACS Applied Materials and Interfaces*. 2016;**8**:5763-5767. DOI: 10.1021/acsami.5b12598
- [12] Gao Y, Zhang Z, Wu J, Yi X, Zheng A, Umar A, et al. Mint: Comprehensive investigation of CO₂ adsorption on Mg-Al-CO₃ LDH-derived mixed metal oxides. *Journal of Materials Chemistry A*. 2013;**1**:12782-12790. DOI: 10.1039/c3ta13039h
- [13] Silva JM, Trujillano R, Rives V, Soria MA, Madeira LM. Mint: High temperature CO₂ sorption over modified hydrotalcites. *Chemical Engineering Journal*. 2017;**325**:25-34. DOI: 10.1016/j.cej.2017.05.032
- [14] Oliveira ELG, Grande CA, Rodrigues AE. Mint: CO₂ sorption on hydrotalcite and alkali-modified (K and Cs) hydrotalcites at high temperatures. *Separation and Purification Technology*. 2008;**62**:137-147. DOI: 10.1016/j.seppur.2008.01.011

- [15] Zhu X, Chen C, Wang Q, Shi Y, O'Hare D, Cai N. Mint: Roles for K₂CO₃ doping on elevated temperature CO₂ adsorption of potassium promoted layered double oxides. *Chemical Engineering Journal*. 2019;**366**:181-191. DOI: 10.1016/j.cej.2019.01.192
- [16] Kim S, Lee KB. Mint: Impregnation of hydrotalcite with NaNO₃ for enhanced high-temperature CO₂ sorption uptake. *Chemical Engineering Journal*. 2019;**356**:964-972. DOI: 10.1016/j.cej.2018.08.207
- [17] Hanif A, Dasgupta S, Divekar S, Arya A, Garg MO, Nanoti A. Mint: A study on high temperature CO₂ capture by improved hydrotalcite sorbents. *Chemical Engineering Journal*. 2014;**236**:91-99. DOI: 10.1016/j.cej.2013.09.076
- [18] Ram Reddy MK, Xu ZP, Lu GQM, Diniz da Costa JC. Mint: Influence of water on high-temperature CO₂ capture using layered double hydroxide derivatives. *Industrial and Engineering Chemistry Research*. 2008;**47**: 2630-2635. DOI: 10.1021/ie0716060
- [19] Ram Reddy MK, Xu ZP, (Max) Lu GQ, Diniz da Costa JC. Mint: Layered double hydroxides for CO₂ capture: Structure evolution and regeneration. *Industrial & Engineering Chemistry Research*. 2006;**45**:7504-7509. DOI: 10.1021/ie060757k
- [20] Wang Q, Gao Y, Luo J, Zhong Z, Borgna A, Guo Z, et al. Mint: Synthesis of nano-sized spherical Mg₃Al-CO₃ layered double hydroxide as a high-temperature CO₂ adsorbent. *RSC Advances*. 2013;**3**:3414-3420. DOI: 10.1039/c2ra22607c
- [21] Ramírez-Moreno MJ, Romero-Ibarra IC, Hernández-Pérez MA, Pfeiffer H. Mint: CO₂ adsorption at elevated pressure and temperature on Mg-Al layered double hydroxide. *Industrial and Engineering Chemistry Research*. 2014;**53**:8087-8094. DOI: 10.1021/ie5010515
- [22] Martunus OMR, Fernando WJN. Mint: Elevated temperature carbon dioxide capture via reinforced metal hydrotalcite. *Microporous and Mesoporous Materials*. 2011;**138**: 110-117. DOI: 10.1016/j.micromeso.2010.09.023
- [23] Dong B, Huang X, Yang X, Li G, Xia L, Chen G. Mint: Rapid preparation of high electrochemical performance LiFePO₄/C composite cathode material with an ultrasonic-intensified micro-impinging jetting reactor. *Ultrasonics Sonochemistry*. 2017;**39**:816-826. DOI: 10.1016/j.ultsonch.2017.06.010
- [24] Dong B, Li G, Yang X, Chen L, Chen GZ. Mint: Controllable synthesis of (NH₄)Fe₂(PO₄)₂(OH)₂H₂O using two-step route: Ultrasonic-intensified impinging stream pre-treatment followed by hydrothermal treatment. *Ultrasonics Sonochemistry*. 2018;**42**: 452-463. DOI: 10.1016/j.ultsonch.2017.12.008
- [25] Mallakpour S, Dinari M, Behranvand V. Mint: Ultrasonic-assisted synthesis and characterization of layered double hydroxides intercalated with bioactive N,N'-(pyromellitoyl)-bis- α -amino acids. *RSC Advances*. 2013;**3**:23303-23308. DOI: 10.1039/c3ra43645d
- [26] Sing KSW, Everett DH, Haul RAW, Moscou L, Pierotti RA, Rouquerol J, et al. Mint: Reporting physisorption data for gas solid systems with special reference to the determination of surface area and porosity. *Pure and Applied Chemistry*. 1985;**57**:603-619. DOI: 10.1351/pac198557040603
- [27] Carrado KA, Csencsits R, Thiyagarajan P, Seifert S, Macha SM, Harwood J. Mint: Crystallization and textural porosity of synthetic clay minerals. *Journal of Materials*

Chemistry. 2002;**12**:3228-3237. DOI: 10.1039/b204180b

[28] Gunjakar JL, Kim IY, Lee JM, Lee N-S, Hwang S-J. Mint: Self-assembly of layered double hydroxide 2D nanoplates with graphene nanosheets: An effective way to improve the photocatalytic activity of 2D nanostructured materials for visible light-induced O₂ generation. *Energy and Environmental Science*. 2013;**6**:1008-1017. DOI: 10.1039/C3EE23989F

[29] Wang J, Huang L, Zheng Q, Qiao Y, Wang Q. Mint: Layered double hydroxides/oxidized carbon nanotube nanocomposites for CO₂ capture. *Journal of Industrial and Engineering Chemistry*. 2016;**36**:255-262. DOI: 10.1016/j.jiec.2016.02.010

[30] Serna-Guerrero R, Sayari A. Mint: Modeling adsorption of CO₂ on amine-functionalized mesoporous silica. 2: kinetics and breakthrough curves. *Chemical Engineering Journal*. 2010; **161**:182-190. DOI: 10.1016/j.cej.2010.04.042

[31] Loganathan S, Tikmani M, Edubilli S, Mishra A, Ghoshal AK. Mint: CO₂ adsorption kinetics on mesoporous silica under wide range of pressure and temperature. *Chemical Engineering Journal*. 2014;**256**:1-8. DOI: 10.1016/j.cej.2014.06.091

[32] Wang J, Mei X, Huang L, Zheng Q, Qiao Y, Zang K, et al. Mint: Synthesis of layered double hydroxides/graphene oxide nanocomposite as a novel high-temperature CO₂ adsorbent. *Journal of Energy Chemistry*. 2015;**24**:127-137. DOI: 10.1016/s2095-4956(15)60293-5

[33] Song G, Zhu X, Chen R, Liao Q, Ding Y-D, Chen L. Mint: An investigation of CO₂ adsorption kinetics on porous magnesium oxide. *Chemical Engineering Journal*. 2016;**283**:175-183. DOI: 10.1016/j.cej.2015.07.055

[34] Li P, Tezel H. Mint: Equilibrium and kinetic analysis of CO₂-N₂ adsorption separation by concentration pulse chromatography. *Journal of Colloid and Interface Science*. 2007;**313**:12-17. DOI: 10.1016/j.jcis.2007.04.015

[35] Saha D, Deng S. Mint: Adsorption equilibrium and kinetics of CO₂, CH₄, N₂O, and NH₃ on ordered mesoporous carbon. *Journal of Colloid and Interface Science*. 2010;**345**:402-409. DOI: 10.1016/j.jcis.2010.01.076

[36] Liu Q, Shi J, Zheng S, Tao M, He Y, Shi Y. Mint: Kinetics studies of CO₂ adsorption/desorption on amine-functionalized multiwalled carbon nanotubes. *Industrial and Engineering Chemistry Research*. 2014;**53**: 11677-11683. DOI: 10.1021/ie502009n