

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

6,900

Open access books available

186,000

International authors and editors

200M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.
For more information visit www.intechopen.com



Nanosphere Lithography for Nitride Semiconductors

Wai Yuen Fu and Hoi Wai Choi
The University of Hong Kong
Hong Kong

1. Introduction

Nanolithography has been widely studied in recent years, considering its wide-ranging applications in electronics and photonics. In the ideal case, lithography using short-wavelength electromagnetic wave through a pre-defined mask is probably the most desirable solution. However, as technology progresses further, traditional photolithography is becoming exceedingly complex and incurring higher cost associated with light source as the wavelength of light goes shorter. Therefore, other nanolithography methods become strong competitors excelling with lower equipment cost and simpler fabrication procedures. In particular, nanosphere lithography as a self-assembly bottom-up approach for producing periodic array of spherical particles is simple and inexpensive as compared to other lithographic methods.

Originally developed by Deckman et al. for defining a large area lithographic mask (Deckman & Dunsmuir, 1982), nanosphere lithography was further optimized by Hultenn et al. for applications involving surface-enhanced Raman spectroscopy (Haynes & Van Duyne, 2003; Hultenn & Vanduyne, 1995). Nanospheres that are used in lithography are commercially available in solution form, and through a simple coating procedure with optimized conditions, ordered hexagonal array of nanospheres can be naturally assembled as the nano-particles achieve equilibrium in an initially disordered system, i.e., a solution of nanospheres. Although only hexagonal array can be formed by this lithographic technique, the hexagonal pattern is useful for a range of applications, for instance, in nanophotonics where ordered hexagonal patterns can be used for the fabrication of photonic crystal (Han et al., 2005; Su et al., 2008) and also in plasmonics (Jensen et al., 2000; Malinsky et al., 2001; Stewart et al., 2006). With rivals like nanoimprint lithography (Byeon et al., 2007; Kim et al., 2007) and electron beam (e-beam) lithography (Berrier et al., 2004; David et al., 2006; Noda et al., 2007), the low cost and high through-put (albeit being less precise) nature of nanosphere lithography is especially suited for photonic applications.

Gallium nitride (GaN) semiconductors and devices thus serve well as a platform for nanosphere lithography. In recent years, GaN has emerged as the most successful semiconductor material in optoelectronics, delivering a range of commercialized products which has since revolutionized our lives, including violet laser diodes for ultra-high capacity optical storage and white light LEDs for solid-state lighting (Humphreys, 2008; Schubert & Kim, 2005). While GaN technology is becoming mature, there is still plenty of

Source: Lithography, Book edited by: Michael Wang,
ISBN 978-953-307-064-3, pp. 656, February 2010, INTECH, Croatia, downloaded from SCIYO.COM

room for further development. For instance, one major issue with GaN devices is the limited efficiency of light extraction. To tackle this problem, texturing of the surface in a regular manner has been adopted at the micrometer and nanometer scales (David et al., 2008; Han et al., 2006; Ng et al., 2008; Noda & Fujita, 2009).

Therefore in this chapter, we will demonstrate the potential applications of nanosphere lithography including photonic crystals and surface plasmons. Several topics will be outlined in this chapter, including the various techniques of coating nanosphere arrays, together with a detailed analysis of their structural, morphological and optical characteristics. The possibilities of applying nanosphere lithography into practical GaN devices and beyond will be discussed.

2. Process of self-assembled nanosphere lithography

There have been intense efforts targeted at the formation of nanosphere into regular patterns. Although lots of variants of the process have since been developed, including the vertical deposition method (Gil et al., 2007; Jiang et al., 1999; Ye et al., 2001; Zhou & Zhao, 2004), spin coating (Mihi et al., 2006; Ogi et al., 2007) and even merely dipping (Choi et al., 2009; Im et al., 2003), all these fundamentally rely on manipulation of the forces applied amongst nanospheres. Thus, most of these methods require precise control of ambient conditions such as temperature and pressure, together with the viscosity and evaporation rate of the fluid. These conditions could be varied in order to control the number of layers and degree of order of the assembled pattern, as well as the extent of coverage across the sample. It was found that the vertical deposition method yields a better quality of ordered nanosphere array (Wong et al., 2003) compared with others, therefore in this chapter we will concentrate on its discussion.

2.1 Vertical deposition

Known for its good orderliness and simplicity, the vertical deposition method has been adopted in many research studies employing nanosphere lithography (Chiappini et al., 2007; Kuai et al., 2004). A common and general setup for vertical deposition consist of an apparatus for maintaining a constant ambient temperature such as a dry-bath, or a basic oven, that is capable of providing a stable stream of air or gas, and a vial for holding the nanosphere in solution form with the sample to be coated lying upon the sidewall of the vial. A schematic diagram of a typical setup is illustrated in Figure 1. The solution typically consist of nanospheres suspended, and a water-alcohol mixture that controls the evaporation rate (Shimmin et al., 2006). Surfactants are sometimes used together to reduce the viscosity. As the nanosphere solution dries up, the nanosphere will be self-assembled into hexagonal close-packed pattern, adhering to the sample. Unfortunately, cracks often exist in the resultant nanosphere coating, regardless of the degree of order. The reason for the persistent formation of cracks is identified to be caused by the movement of “water line” as the water level changes during evaporation of solution. Also, since the concentration increases as the solution dries up, the thickness of the nanosphere coating, or the number of nanosphere layers, will usually be thicker towards the lower end of the sample than that at the upper end.

The problem of uneven layer distribution along the sample can be resolved by a modified vertical deposition method, namely the flow-controlled vertical deposition method. Instead of waiting for the solution to be evaporated, this modified method proactively scans the

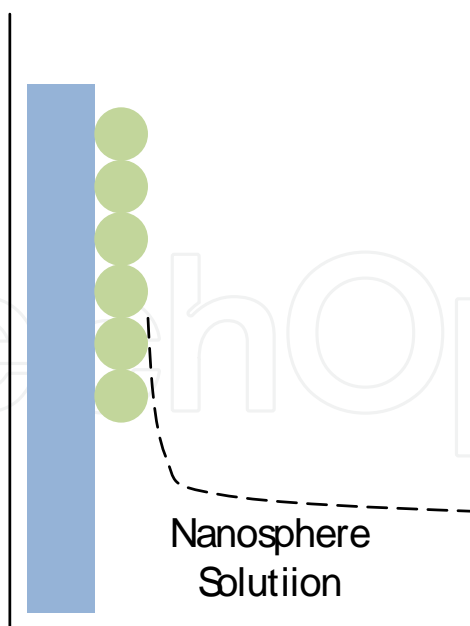


Fig. 1. Schematic diagram of the setup for vertical deposition.

water level along the entire sample by adjusting the relative position between sample and vial, while keeping the concentration changes to a minimum. This allows a much shorter processing time which also minimize possible sedimentation of nanospheres that will aggravate the unevenness during the deposition process. Thus, this method is ideal for maintaining a more even thickness of coating across the sample. For addressing the cracking problem, there have been attempts to use a chemical method in conjunction with vertical deposition method. L. Wang et al. have reported crack-free colloidal crystal by means of hydrolysis of a silica precursor during vertical deposition (Wang & Zhao, 2007). Silica species formed acts like a glue among nanospheres to avoid crack formation during evaporation. Other crack-free approach includes self-assembly at air/ water/ air interface which will form a free standing nanosphere films, although this is not an approach suitable for lithography.

3. Characterization of nanosphere coating

3.1 Topography of nanosphere coating

After deposition, a hexagonal close-packed nanosphere pattern can be observed under scanning electron microscope (SEM), as shown in Figure 2, if the coating is successful. Unless using very specific approaches to eliminate cracks as suggested in the last section, different kinds of defects, including but not limited to cracks and point defects, will be formed. As mentioned in the previous section, cracks formed through vertical deposition are most likely due to the movement of “water line” across the sample. However, there are also many other causes that could lead to a defect. For example, the vast amount of nanosphere that a solution contains cannot possibly be of identical dimensions. A single apparently larger or smaller nanosphere amongst many in an array is enough to give rise to point defects. Apart from dimensional non-uniformity, irregular nanosphere may also exist, that is, some of the nanosphere may not be perfectly spherical. Point defects will also be resulted from the protruding portions of irregular nanospheres. Due to the limitations in nanosphere synthesis and deposition, defects among nanosphere arrays are inevitable. Nevertheless,

with a low defect density, nanosphere lithography is adequate for many applications unless extremely high accuracy is required.

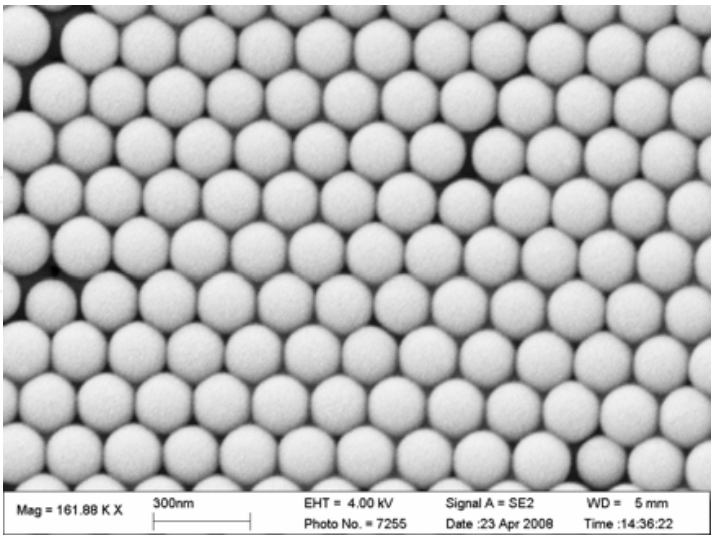


Fig. 2. SEM image of a monolayer of nanospheres, with occasional defects caused by non-uniformity in dimension of nanospheres.

One distinct advantage of nanosphere lithography is that nanospheres that self-assemble into a hexagonal close-packed pattern can produce features of nano- or even sub-nano scales, provided that the required dimensions of nanosphere are available. The voids between nanospheres are at least one order of magnitude smaller than the diameter of nanosphere itself; that is, for a 10 nm-diameter nanosphere, the void can easily be smaller than 1 nm.

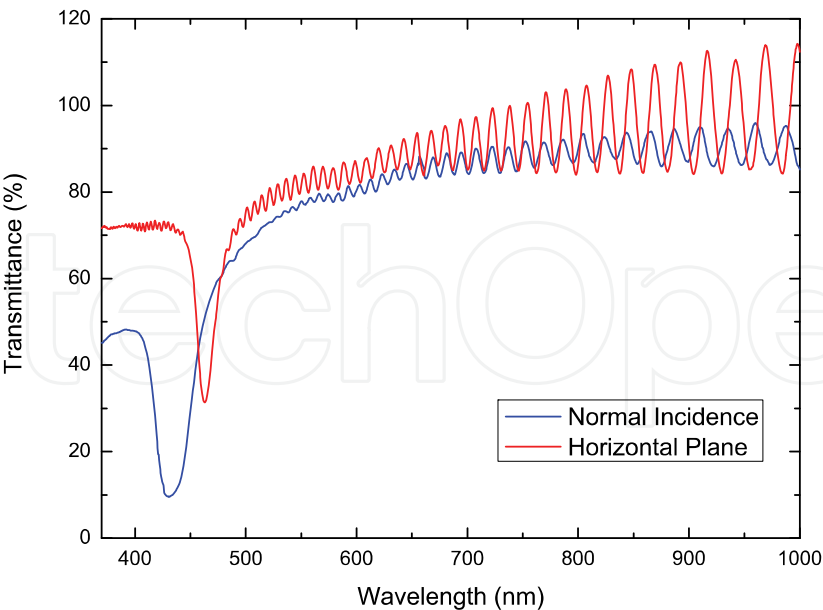


Fig. 3. Transmission spectrum of hexagonal close-packed 192-nm-diameter nanosphere multi-layer array coated on a GaN wafer measured at 2 different angles with reference to an as-grown GaN sample. (with permission for reproduction from Institute of Physics Publishing)

3.2 Optical properties of nanosphere coating

The optical properties of a nanosphere coating are pretty obvious by observing it at different angles under broadband illumination – different colors of light are reflected at different angles, acting like a grating. In fact, the nanosphere coating is a 2-dimensional photonic crystal itself. In the frequency domain there is in fact a gap in the transmission spectrum, an example of which is illustrated in Figure 3. The existence of the gap indicates that certain wavelength of light is being reflected or scattered away. The spectral position of the gap varies according to the material's refractive index, the size of nanosphere, orientation of coating and the number of layers. Typically the gap exists at a position at 2-3 times the diameter of nanosphere spectrally.

4. Nanosphere coating applications

4.1 Nanopillar photonic crystal LED

Besides using the nanospheres themselves directly, a patterned nanosphere layer can act as a good medium for further processing. Amongst different kinds of materials, silica-made nanosphere is especially suitable for etching process, since the good etch resistivity of silica renders the patterned monolayer of nanosphere a naturally good hard mask.

One of the most popular 'secondary' nanostructures derived from nanosphere lithography is the nanopillar array (Cheung et al., 2006; Li et al., 2007; Ng et al., 2008). After coating a monolayer of nanospheres onto a sample, the circular hexagonal close-packed pattern can be easily transferred to the sample by a subsequent dry etch. Figure 4 shows an example of the resultant nanopillar structure. An array of nanopillar is an effective approach to improve light extraction when fabricated on a GaN LED. Due to the high refractive index of GaN, LEDs without any light extraction strategy adopted will suffer from low light extraction efficiency, as a large fraction of emitted light is trapped within the GaN epilayer, propagating as guiding modes and subsequently re-absorbed. A nanopillar array integrated into the surface of an LEDs will have a surface-texturing effect. In one way, the nanopillars increase the total surface area of LED, thus increasing the probability for light to escape, and thereby decreasing photon re-absorption in GaN. At the same time, they reduce the effective refractive index such that total internal reflection is suppressed to a certain extent.

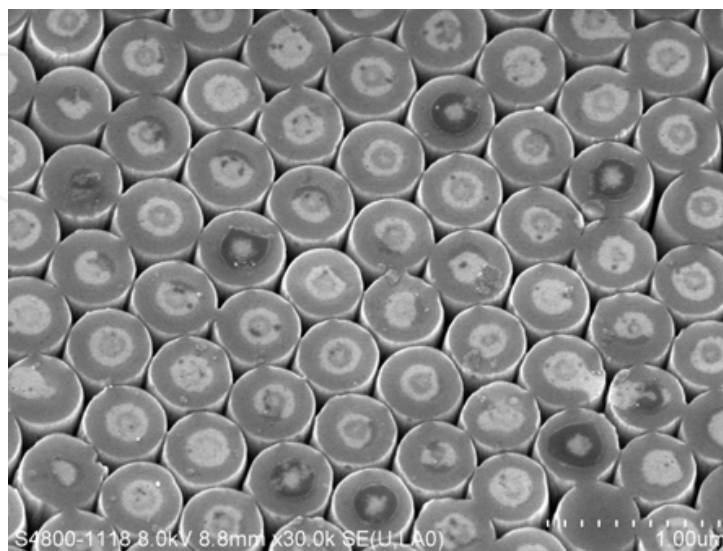


Fig. 4. SEM Image of a nanopillar array with diameter of 500 nm fabricated on GaN wafer.

In the research studies by W. N. Ng et al., a monolayer of silica nanospheres of 500 nm diameter, coated by spin coating method, served as a lithographic mask. Inductively coupled plasma (ICP) etching using a gas chemistry of Cl_2 and BCl_3 at flow rates of 20 sccm and 10 sccm respectively was carried out for a duration of 120 s. The silica nanosphere residual was removed by sonification to expose the nanopillar array beneath. The resulting nanopillar sample contributed to a two-fold enhancement of photoluminescence intensity in the normal direction. In their later studies, the authors successfully demonstrated light extraction enhancement from an electroluminescent LED with an integrated nano-pillar array. Significant improvement to the optical output was achieved compared to an unpatterned LED, as shown in the plot of L - I characteristics in Figure 5.

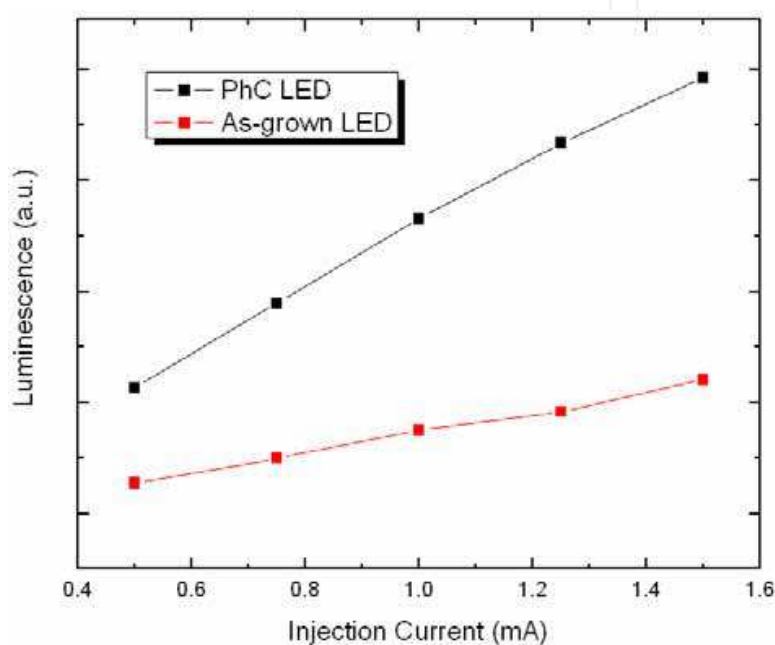


Fig. 5. L - I characteristics of a nanopillar photonic crystal LED as compared with an unpatterned LED. (with permission for reproduction from Institute of Physics Publishing)

To further extend the applications of nanospheres to GaN materials, an isotropic etching model with a monolayer of nanosphere has been reported by W. Y. Fu et al. Hemiellipsoid structures were been fabricated, as illustrated in Figure 6, using nanosphere coating mask with a modified recipe from the study in the previous paragraph, using a gas chemistry comprising 12 sccm of Cl_2 and 9 sccm for CHF_3 . Compared to the etch recipe adopted by W. N. Ng et al., this modified recipe makes use of CHF_3 that is particularly suited for etching of silica; as a result the dimensions of silica nanosphere in the array will slowly shrink as etching progresses. The etch rates of GaN and SiO_2 can be controlled independently, allowing more freedom in the control of desired shape of the resultant arrays. This is useful for the design of different photonic dispersion characteristics that can be exhibited by photonic crystal structures. For example, a photonic bandgap based on an array of hemiellipsoids can be designed for light extraction purposes. From the angular PL emission plot as shown in Figure 7 (Fu et al., 2009), an obvious overall enhancement to the PL intensity is observed. By comparing the integrated PL intensity between an as-grown with the hemiellipsoid array an enhancement factor of over 3 times can be deduced.

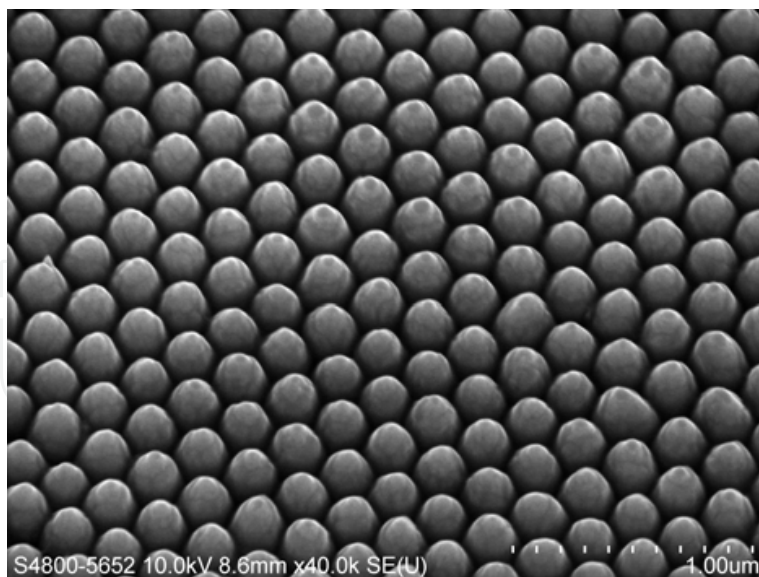


Fig. 6. SEM image of a hemiellipsoid array fabricated by nanosphere lithography. (with permission for reproduction from American Institute of Physics)

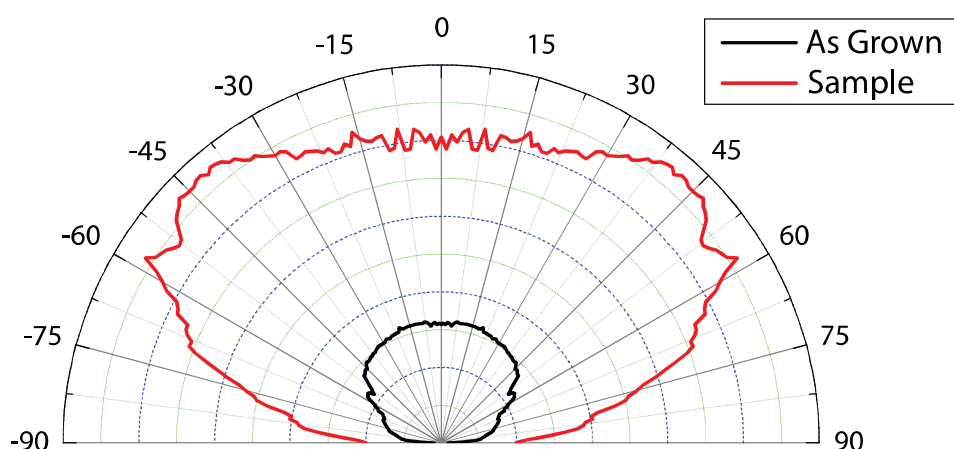


Fig. 7. Angular PL emission pattern from an LED fabricated with a self-assembled hemiellipsoid on top for superior light extraction. (with permission for reproduction from American Institute of Physics)

4.2 Fluorescent nanospheres coated white LED

The white-light LED has become a widely available commercial product with numerous applications including solid state lighting, liquid crystal display (LCD) backlighting and signaling etc. There are two common approaches to achieve white light emission from an LED, either by spectral down conversion using YAG phosphor-coated blue LEDs (Pan et al., 2004; Schubert & Kim, 2005) or the mixing of discrete LEDs with the primary colors red, green and blue (Hui et al., 2009; Humphreys, 2008; Muthu et al., 2002; Steigerwald et al., 2002). Due to the technical difficulties of color mixing with three discrete LEDs without bulky optics, phosphor-coated white LED tends to be more widely adopted despite the large Stokes shift losses. Under this circumstance, fluorescent nanospheres coated white LED has been suggested as an alternative with some advantage over phosphor-coated white LED. A schematic diagram of such design of LED device is shown in Figure 8.

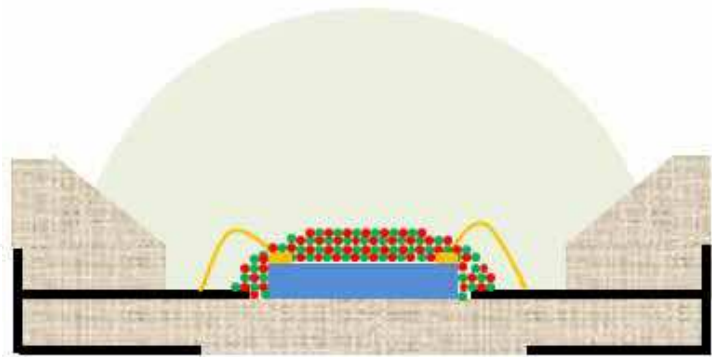


Fig. 8. Schematic diagram of a fluorescent nanosphere coated LED device. (with permission for reproduction from Institute of Physics Publishing)

Nanospheres with fluorescent dyes incorporated internally have been demonstrated to act as an alternative to the conventional approach of coating phosphor on blue LED for white light emission. Commercially available in dimensions ranging from tens of nanometers to micrometers, polystyrene fluorescent-dyed nanospheres have been widely used in the chemical and biological areas (Bhalgat et al., 1998; Matsuya et al., 2003; Seo & Lee, 2004). The swelling and unswelling of the polymeric spheres during preparation ensures that the pores are able to entrap the fluorescent dyes physically, resulting in an enhanced dye photostability, with predicted lifetimes exceeding 36 months. Simply by adjusting the ratio between excited light emission from green- and red- colored nanospheres with respect to the blue light emission intensity from InGaN LED, white light emission can be achieved and the

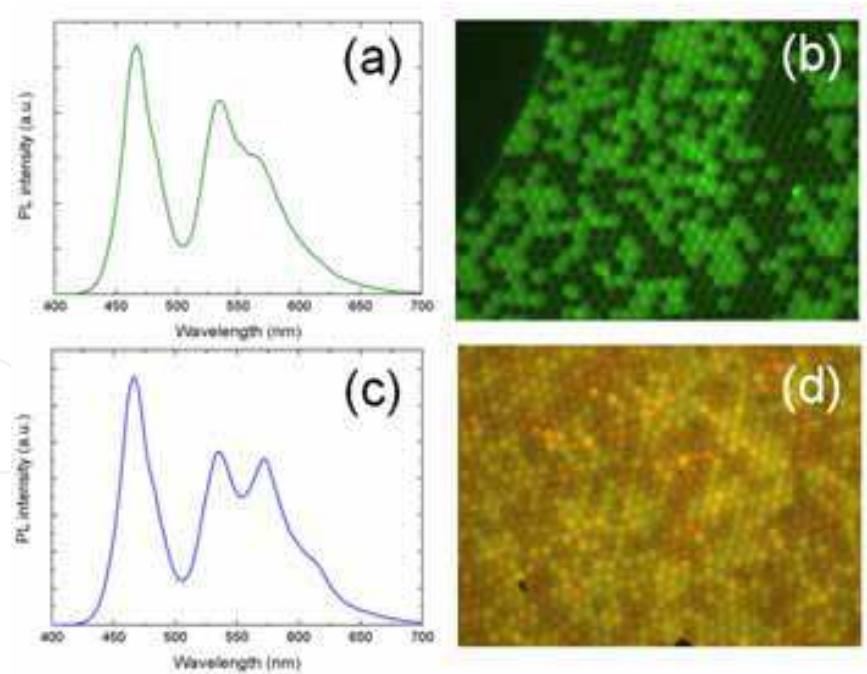


Fig. 9. (a) PL spectrum of the green microspheres, (b) optical image of fluorescence emission from green microspheres (with blue and red light filtered off). (c) PL spectrum of the mixture of green and red microspheres, and (d) optical image of fluorescence emission from green, yellow and red microspheres (with blue light filtered off). (with permission for reproduction from Institute of Physics Publishing)

color temperature can be easily adjusted, although the color conversion is still subjected to Stokes shift loss. However, the hexagonal close-packed patterned and spherical-shaped nature of nanospheres contributes to improved mixing of color both spatially and angularly, with a slightly better advantage on excitation of emission of other colors compared with conventional phosphors.

Figure 9 shows PL spectra and optical images of fluorescent nanosphere on GaN LEDs with blue emission as in the studies by K.N. Hui et al. (Hui et al., 2008). With different colors of fluorescent nanospheres, including green, yellow and red, emission spectrum of LEDs can be tuned to different shades of white light.

4.3 Surface plasmon

Induced by electromagnetic wave, when collective oscillations of free electrons, i.e., plasmons, are confined to surfaces and couples strongly with light, they are known as surface plasmon. This usually occurs at the interface between a metal (of negative dielectric constant) and a dielectric material (of positive dielectric constant). These surface plasmons are conducive to an important phenomenon, the localized surface plasmon resonance, which occurs when metallic nanoparticle is excited by light when in contact with dielectric material. This phenomenon is exhibited by a strong peak in the extinction spectrum. With GaN devices, localized surface plasmon resonance has great potential for improving light extraction efficiency of LEDs since it can significantly enhance the electric field strength near the surface of nanoparticle (Ross & Lee, 2008; Sundaramurthy et al., 2005).

Typically, when light emitted from multi-quantum wells of LED interacts with a metallic layer, a surface plasmon mode will be formed. This surface plasmon mode increases the density of states and spontaneous emission rate (Gianordoli et al., 2000; Hecker et al., 1999; Vuckovic et al., 2000), and thus helps to improve coupling from the multi-quantum wells (Neogi et al., 2002). There have been reports that successfully demonstrated enhancement in InGaN quantum well emission by means of enhancement of Purcell factor with surface plasmons making use of a metal film on top of an LED (Okamoto et al., 2004). However, light coupled to surface plasmon modes is trapped at the metal/ dielectric interface despite the enhancement of internal quantum efficiency. To deal with this problem, localized surface plasmon resonance had been investigated, whereby a periodic metallic array, or plasmonic crystal, is adopted instead of a flat metal film to assist with extracting light from the surface plasmon polaritons (Cesario et al., 2007).

Since the resonance wavelength depends strongly on the size and shape of metallic nanoparticles, and that resonance at visible range often requires a feature size of less than 100 nm, nanosphere lithography is an effective method for the patterning of metallic nanoparticles, particularly because the requirement on orderliness is lower. By controlling the dimensions of the nanospheres, the dimensions of the resultant metallic nanostructures can be adjusted, thereby affecting the spectral position of resonance. With monolayer of nanosphere serving as a mask, deposition of desired metal, typically Ag, Al or Au, can be carried out to form an inverted metallic circular array (Jensen, Malinsky, Haynes & Van Duyne, 2000; Malinsky, Kelly, Schatz & Van Duyne, 2001), providing the metal can penetrate the void regions of the nanosphere array. Figure 10 shows an SEM image illustrating the resultant metallic nanoparticles after removing the nanosphere residual. According to the PL spectra of InGaN/ GaN MQWs coated with an array of metallic nanoparticles using this nanosphere lithography method as reported by G.Y. Mak et al., it

was demonstrated that the metallic nanoparticles are indeed able to improve light extraction without changes of emission characteristics as demonstrated by Figure 11 (Mak et al., 2009).

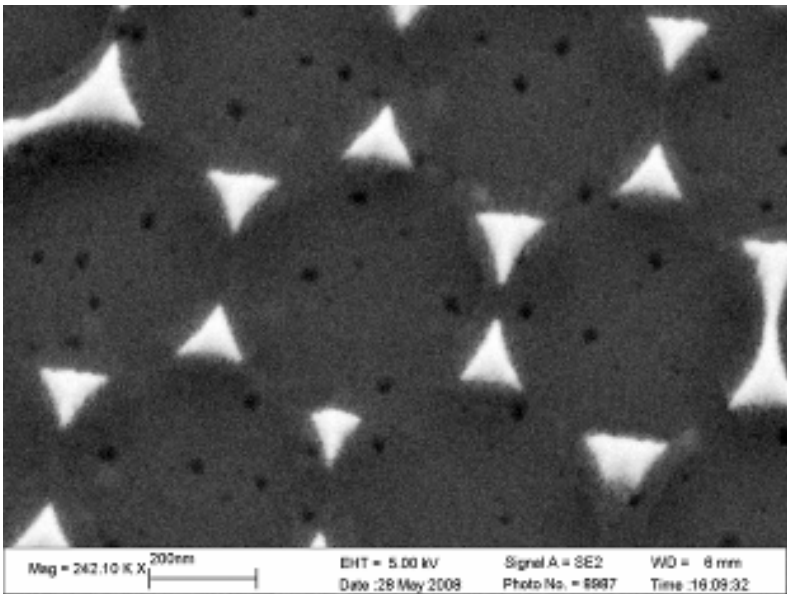


Fig. 10. SEM image showing Au nanoparticles formed by deposition through a nanosphere mask. (with permission for reproduction from WILEY-VCH Verlag GmbH & Co.)

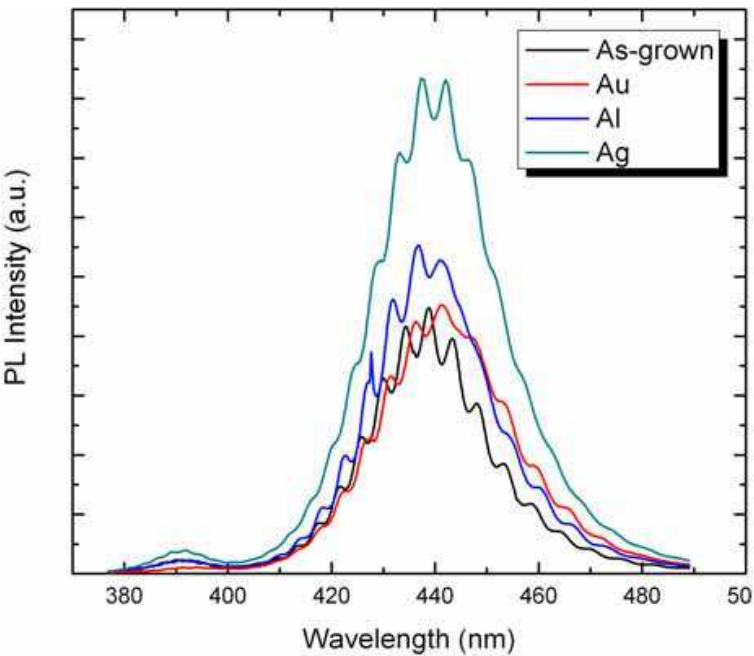


Fig. 11. PL spectra of LED with deposited nanoparticles of Au, Al and Ag. (with permission for reproduction from WILEY-VCH Verlag GmbH & Co.)

5. Summary

An inexpensive and simple approach as compared to other nanolithography methods, nanosphere lithography is able to play an important role in defining periodic-arrayed

lithographic mask for photonic applications. Although more optimization works needs to be done on thickness control, the availability of crack-free deposition method made it feasible for mass production with high yield. A few photonic applications have been addressed in this chapter. Fluorescent nanospheres provide an alternative way to produce white LED for solid state lighting with improved color mixing. Nanopillars derived from a monolayer of hexagonal close-packed nanospheres helps to texturize the surface of an LED in order to improve light extraction efficiency. Last but not least, localized surface plasmon resonance not only can improve light extraction, but also has potential sub-wavelength applications including optical energy transport and near field scanning optical microscopy.

6. References


- Berrier, A.; Mulot, M.; Swillo, M.; Qiu, M.; Thylen, L.; Talneau, A. & Anand, S. (2004). Negative refraction at infrared wavelengths in a two-dimensional photonic crystal. *Physical Review Letters*, 93, 7, 073902, 0031-9007
- Bhalgat, M. K.; Haugland, R. P.; Pollack, J. S.; Swan, S. & Haugland, R. P. (1998). Green- and red-fluorescent nanospheres for the detection of cell surface receptors by flow cytometry. *Journal of Immunological Methods*, 219, 1-2, 57-68, 0022-1759
- Byeon, K. J.; Hwang, S. Y. & Lee, H. (2007). Fabrication of two-dimensional photonic crystal patterns on GaN-based light-emitting diodes using thermally curable monomer-based nanoimprint lithography. *Applied Physics Letters*, 91, 9, 091106, 0003-6951
- Cesario, J.; Gonzalez, M. U.; Cheylan, S.; Barnes, W. L.; Enoch, S. & Quidant, R. (2007). Coupling localized and extended plasmons to improve the light extraction through metal films. *Optics Express*, 15, 17, 10533-10539, 1094-4087
- Cheung, C. L.; Nikolic, R. J.; Reinhardt, C. E. & Wang, T. F. (2006). Fabrication of nanopillars by nanosphere lithography. *Nanotechnology*, 17, 5, 1339-1343, 0957-4484
- Chiappini, A.; Armellini, C.; Chiasera, A.; Ferrari, M.; Jestin, Y.; Mattarelli, M.; Montagna, M.; Moser, E.; Conti, G. N.; Pelli, S.; Righini, G. C.; Gonclves, M. C. & Almeida, R. M. (2007). Design of photonic structures by sol-gel-derived silica nanospheres. *Journal of Non-Crystalline Solids*, 353, 5-7, 674-678,
- Choi, H. K.; Kim, M. H.; Im, S. H. & Park, O. O. (2009). Fabrication of Ordered Nanostructured Arrays Using Poly(dimethylsiloxane) Replica Molds Based on Three-Dimensional Colloidal Crystals. *Advanced Functional Materials*, 19, 10, 1594-1600,
- David, A.; Fujii, T.; Sharma, R.; McGroddy, K.; Nakamura, S.; DenBaars, S. P.; Hu, E. L.; Weisbuch, C. & Benisty, H. (2006). Photonic-crystal GaN light-emitting diodes with tailored guided modes distribution. *Applied Physics Letters*, 88, 6, 061124, 0003-6951
- David, A.; Moran, B.; McGroddy, K.; Matioli, E.; Hu, E. L.; DenBaars, S. P.; Nakamura, S. & Weisbuch, C. (2008). GaN/ InGaN light emitting diodes with embedded photonic crystal obtained by lateral epitaxial overgrowth. *Applied Physics Letters*, 92, 11, 113514,
- Deckman, H. W. & Dunsmuir, J. H. (1982). Natural Lithography. *Applied Physics Letters*, 41, 4, 377-379, 0003-6951
- Fu, W. Y.; Wong, K. K. Y. & Choi, H. W. (2009). Close-packed hemiellipsoid arrays: A photonic band gap structure patterned by nanosphere lithography. *Applied Physics Letters*, 95, 13, 133125, 0003-6951

- Gianordoli, S.; Hainberger, R.; Kock, A.; Finger, N.; Gornik, E.; Hanke, C. & Korte, L. (2000). Optimization of the emission characteristics of light emitting diodes by surface plasmons and surface waveguide modes. *Applied Physics Letters*, 77, 15, 2295-2297, 0003-6951
- Gil, A.; Vaupel, M.; Guitian, F. & Mobius, D. (2007). Stress-free production and effective medium model of colloidal crystals. *Journal of Materials Chemistry*, 17, 23, 2434-2439, 0959-9428
- Han, D.-S.; Kim, J.-Y.; Na, S.-I.; Kim, S.-H.; Lee, K.-D.; Kim, B. & Park, S.-J (2006). Improvement of light extraction efficiency of flip-chip light-emitting diode by texturing the bottom side surface of sapphire substrate. *IEEE Photonics Technology Letters*, 18, 13, 1406-1408, 1041-1135
- Han, S.; Hao, Z. B.; Wang, J & Luo, Y. (2005). Controllable two-dimensional photonic crystal patterns fabricated by nanosphere lithography. *Journal of Vacuum Science & Technology B*, 23, 4, 1585-1588, 1071-1023
- Haynes, C. L. & Van Duyne, R. P. (2003). Plasmon-sampled surface-enhanced Raman excitation spectroscopy. *Journal of Physical Chemistry B*, 107, 30, 7426-7433, 1520-6106
- Hecker, N. E.; Hopfel, R. A.; Sawaki, N.; Maier, T. & Strasser, G. (1999). Surface plasmon-enhanced photoluminescence from a single quantum well. *Applied Physics Letters*, 75, 11, 1577-1579, 0003-6951
- Hui, K. N.; Fu, W. Y.; Ng, W. N.; Leung, C. H.; Lai, P. T.; Wong, K. K. Y. & Choi, H. W. (2008). Polychromatic light-emitting diodes with a fluorescent nanosphere opal coating. *Nanotechnology*, 19, 35, 355203, 0957-4484
- Hui, K. N.; Wang, X. H.; Li, Z. L.; Lai, P. T. & Choi, H. W. (2009). Design of vertically-stacked polychromatic light-emitting diodes. *Optics Express*, 17, 12, 9873-9878, 1094-4087
- Hulteen, J. C. & Vanduyne, R. P. (1995). Nanosphere Lithography - a Materials General Fabrication Process for Periodic Particle Array Surfaces. *Journal of Vacuum Science & Technology A-Vacuum Surfaces and Films*, 13, 3, 1553-1558, 0734-2101
- Humphreys, C. J (2008). Solid-state lighting. *MRS Bulletin*, 33, 4, 459-470, 0883-7694
- Im, S. H.; Kim, M. H. & Park, O. O. (2003). Thickness control of colloidal crystals with a substrate dipped at a tilted angle into a colloidal suspension. *Chemistry of Materials*, 15, 9, 1797-1802,
- Jensen, T. R.; Malinsky, M. D.; Haynes, C. L. & Van Duyne, R. P. (2000). Nanosphere lithography: Tunable localized surface plasmon resonance spectra of silver nanoparticles. *Journal of Physical Chemistry B*, 104, 45, 10549-10556, 1089-5647
- Jiang, P.; Bertone, J. F.; Hwang, K. S. & Colvin, V. L. (1999). Single-crystal colloidal multilayers of controlled thickness. *Chemistry of Materials*, 11, 8, 2132-2140, 0897-4756
- Kim, S. H.; Lee, K. D.; Kim, J. Y.; Kwon, M. K. & Park, S. J (2007). Fabrication of photonic crystal structures on light emitting diodes by nanoimprint lithography. *Nanotechnology*, 18, 5, 055306, 0957-4484
- Kuai, S. L.; Hu, X. F.; Hache, A. & Truong, V. V. (2004). High-quality colloidal photonic crystals obtained by optimizing growth parameters in a vertical deposition technique. *Journal of Crystal Growth*, 267, 1-2, 317-324,
- Li, W.; Xu, L.; Zhao, W. M.; Sun, P.; Huang, X. F. & Chen, K. J (2007). Fabrication of large-scale periodic silicon nanopillar arrays for 2D nanomold using modified nanosphere lithography. *Applied Surface Science*, 253, 22, 9035-9038, 0169-4332

- Mak, G. Y.; Fu, W. Y.; Lam, E. Y. & Choi, H. W. (2009). Metallic nanoparticle array on GaN by microsphere lithography. *physica status solidi (c)*, 6, S2, S654-S657, 1862-6351
- Malinsky, M. D.; Kelly, K. L.; Schatz, G. C. & Van Duyne, R. P. (2001). Nanosphere lithography: Effect of substrate on the localized surface plasmon resonance spectrum of silver nanoparticles. *Journal of Physical Chemistry B*, 105, 12, 2343-2350, 1089-5647
- Matsuya, T.; Tashiro, S.; Hoshino, N.; Shibata, N.; Nagasaki, Y. & Kataoka, K. (2003). A core-shell-type fluorescent nanosphere possessing reactive poly(ethylene glycol) tethered chains on the surface for zeptomole detection of protein in time-resolved fluorometric immunoassay. *Analytical Chemistry*, 75, 22, 6124-6132, 0003-2700
- Mihi, A.; Ocana, M. & Miguez, H. (2006). Oriented colloidal-crystal thin films by spin-coating microspheres dispersed in volatile media. *Advanced Materials*, 18, 17, 2244-2249, 0935-9648
- Muthu, S.; Schuurmans, F. J. P. & Pashley, M. D. (2002). Red, green, and blue LEDs for white light illumination. *IEEE Journal of Selected Topics in Quantum Electronics*, 8, 2, 333-338, 1077-260X
- Neogi, A.; Lee, C. W.; Everitt, H. O.; Kuroda, T.; Tackeuchi, A. & Yablonovitch, E. (2002). Enhancement of spontaneous recombination rate in a quantum well by resonant surface plasmon coupling. *Physical Review B*, 66, 15, 153305, 1098-0121
- Ng, W. N.; Leung, C. H.; Lai, P. T. & Choi, H. W. (2008). Nanostructuring GaN using microsphere lithography. *Journal of Vacuum Science & Technology B*, 26, 1, 76-79, 1071-1023
- (2008). Photonic crystal light-emitting diodes fabricated by microsphere lithography. *Nanotechnology*, 19, 25, 255302, 0957-4484
- Noda, S. & Fujita, M. (2009). Light-emitting diodes: Photonic crystal efficiency boost. *Nature Photonics*, 3, 3, 129-130, 1749-4885
- Noda, S.; Fujita, M. & Asano, T. (2007). Spontaneous-emission control by photonic crystals and nanocavities. *Nature Photonics*, 1, 8, 449-458,
- Ogi, T.; Modesto-Lopez, L. B.; Iskandar, F. & Okuyama, K. (2007). Fabrication of a large area monolayer of silica particles on a sapphire substrate by a spin coating method. *Colloids and Surfaces a-Physicochemical and Engineering Aspects*, 297, 1-3, 71-78, 0927-7757
- Okamoto, K.; Niki, I.; Shvartser, A.; Narukawa, Y.; Mukai, T. & Scherer, A. (2004). Surface-plasmon-enhanced light emitters based on InGa_N quantum wells. *Nature Materials*, 3, 9, 601-605, 1476-1122
- Pan, Y. X.; Wu, M. M. & Su, Q. (2004). Tailored photoluminescence of YAG : Ce phosphor through various methods. *Journal of Physics and Chemistry of Solids*, 65, 5, 845-850, 0022-3697
- Ross, B. M. & Lee, L. P. (2008). Plasmon tuning and local field enhancement maximization of the nanocrescent. *Nanotechnology*, 19, 27, 275201, 0957-4484
- Schubert, E. F. & Kim, J. K. (2005). Solid-state light sources getting smart. *Science*, 308, 5726, 1274-1278, 0036-8075
- Seo, J. & Lee, L. P. (2004). Disposable integrated microfluidics with self-aligned planar microlenses. *Sensors and Actuators B-Chemical*, 99, 2-3, 615-622, 0925-4005
- Shimmin, R. G.; DiMauro, A. J. & Braun, P. V. (2006). Slow vertical deposition of colloidal crystals: A Langmuir-Blodgett process? *Langmuir*, 22, 15, 6507-6513, 0743-7463

- Steigerwald, D. A.; Bhat, J. C.; Collins, D.; Fletcher, R. M.; Holcomb, M. O.; Ludowise, M. J.; Martin, P. S. & Rudaz, S. L. (2002). Illumination with solid state lighting technology. *IEEE Journal of Selected Topics in Quantum Electronics*, 8, 2, 310-320, 1077-260X
- Stewart, M. E.; Mack, N. H.; Malyarchuk, V.; Soares, J. A. N. T.; Lee, T. W.; Gray, S. K.; Nuzzo, R. G. & Rogers, J. A. (2006). Quantitative multispectral biosensing and 1D imaging using quasi-3D plasmonic crystals. *Proceedings of the National Academy of Sciences of the United States of America*, 103, 46, 17143-17148, 0027-8424
- Su, Y. K.; Chen, J. J.; Lin, C. L.; Chen, S. M.; Li, W. L. & Kao, C. C. (2008). GaN-Based Light-Emitting Diodes Grown on Photonic Crystal-Patterned Sapphire Substrates by Nanosphere Lithography. *Japanese Journal of Applied Physics*, 47, 8, 6706-6708, 0021-4922
- Sundaramurthy, A.; Crozier, K. B.; Kino, G. S.; Fromm, D. P.; Schuck, P. J. & Moerner, W. E. (2005). Field enhancement and gap-dependent resonance in a system of two opposing tip-to-tip Au nanotriangles. *Physical Review B*, 72, 16, 165409, 1098-0121
- Vuckovic, J.; Loncar, M. & Scherer, A. (2000). Surface plasmon enhanced light-emitting diode. *IEEE Journal of Quantum Electronics*, 36, 10, 1131-1144, 0018-9197
- Wang, L. & Zhao, X. S. (2007). Fabrication of Crack-Free Colloidal Crystals Using a Modified Vertical Deposition Method. *Journal of Physical Chemistry C*, 111, 24, 8538-8542, 1932-7447
- Wong, S.; Kitaev, V. & Ozin, G. A. (2003). Colloidal crystal films: Advances in universality and perfection. *Journal of the American Chemical Society*, 125, 50, 15589-15598, 0002-7863
- Ye, Y. H.; LeBlanc, F.; Hache, A. & Truong, V. V. (2001). Self-assembling three-dimensional colloidal photonic crystal structure with high crystalline quality. *Applied Physics Letters*, 78, 1, 52-54, 0003-6951
- Zhou, Z. C. & Zhao, X. S. (2004). Flow-controlled vertical deposition method for the fabrication of photonic crystals. *Langmuir*, 20, 4, 1524-1526, 0743-7463

IntechOpen



Lithography

Edited by Michael Wang

ISBN 978-953-307-064-3

Hard cover, 656 pages

Publisher InTech

Published online 01, February, 2010

Published in print edition February, 2010

Lithography, the fundamental fabrication process of semiconductor devices, plays a critical role in micro- and nano-fabrications and the revolution in high density integrated circuits. This book is the result of inspirations and contributions from many researchers worldwide. Although the inclusion of the book chapters may not be a complete representation of all lithographic arts, it does represent a good collection of contributions in this field. We hope readers will enjoy reading the book as much as we have enjoyed bringing it together. We would like to thank all contributors and authors of this book.

How to reference

In order to correctly reference this scholarly work, feel free to copy and paste the following:

Wai Yuen Fu and Hoi Wai Choi (2010). Nanosphere Lithography for Nitride Semiconductors, Lithography, Michael Wang (Ed.), ISBN: 978-953-307-064-3, InTech, Available from:
<http://www.intechopen.com/books/lithography/nanosphere-lithography-for-nitride-semiconductors>

INTECH
open science | open minds

InTech Europe

University Campus STeP Ri
Slavka Krautzeka 83/A
51000 Rijeka, Croatia
Phone: +385 (51) 770 447
Fax: +385 (51) 686 166
www.intechopen.com

InTech China

Unit 405, Office Block, Hotel Equatorial Shanghai
No.65, Yan An Road (West), Shanghai, 200040, China
中国上海市延安西路65号上海国际贵都大饭店办公楼405单元
Phone: +86-21-62489820
Fax: +86-21-62489821

© 2010 The Author(s). Licensee IntechOpen. This chapter is distributed under the terms of the [Creative Commons Attribution-NonCommercial-ShareAlike-3.0 License](https://creativecommons.org/licenses/by-nc-sa/3.0/), which permits use, distribution and reproduction for non-commercial purposes, provided the original is properly cited and derivative works building on this content are distributed under the same license.

IntechOpen

IntechOpen