

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

6,900

Open access books available

186,000

International authors and editors

200M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.
For more information visit www.intechopen.com



Field-Effect Transistors for Gas Sensing

Toshihiro Yoshizumi and Yuji Miyahara

Additional information is available at the end of the chapter

<http://dx.doi.org/10.5772/intechopen.68481>

Abstract

This chapter reviews gas-sensitive field-effect transistors (FETs) for gas sensing. Although various types of gas sensors have been reported, this review focuses on FET-based sensors such as catalytic-gate FETs, solid electrolyte-based FETs, suspended-gate FETs, and nanomaterial-based FETs. For recognition of analytes in the gas phase, the combination of cross-reactive gas sensor arrays with pattern recognition methods is promising. Cross-reactive sensor arrays consist of gas sensors that have broad and differential sensitivity. Signals from the cross-reactive sensor array are processed using pattern recognition methods. Reports of FET-based sensor arrays combined with pattern recognition methods are briefly reviewed.

Keywords: gas-sensitive field-effect transistor, gas sensor, cross-reactive sensor array, pattern recognition method

1. Introduction

The importance and demand for sensing gases, vapors, and volatile organic compounds (VOCs) have been increasing in fields such as diagnostics [1–4], environmental monitoring for industrial, agricultural, home safety, and so on [4, 5]. Various types of gas sensors and sensor arrays have been researched and developed [6–8], including field-effect transistor (FET)-based sensors. Following the report of pioneering work on catalytic-gate FETs, research on FET-based gas sensors has been extended to various types of gas-sensitive FETs. In this chapter, catalytic-gate FETs, suspended-gate FETs (SGFETs), and solid electrolyte-based FETs are introduced. Gas-sensitive FETs based on nanomaterials such as carbon nanotubes (CNTs), nanowires (NWs), graphene, and transition metal chalcogenides have also been investigated because the high surface-to-volume ratios of nanomaterials are attractive for improving sensor properties [5, 9]. These nanomaterial-based FETs are also reviewed.

For recognition of gaseous and volatile analytes from sensing results, two main methods have been used [3]. The conventional recognition method uses selective sensors with specific receptors designed for selective interaction with target analytes [3, 6]. Another recognition method uses a combination of cross-reactive sensor arrays and pattern recognition methods [3, 6–8, 10]. These cross-reactive sensor arrays consist of gas sensors that are responsive to a broad range of analytes and have differential sensitivities. To date, various gas sensors have been applied in sensor arrays [6, 8], including gas-sensitive FETs. In this chapter, research on the combination of FET-based sensor arrays and pattern recognition methods is briefly reviewed.

2. Gas-sensitive FETs and field-effect devices combined with catalytic metal gates

Catalytic-gate FETs are one of types of gas-sensitive FETs. In 1975, Lundström et al. first reported a Pd-gate FET sensitive to hydrogen [11, 12]. Pioneering research on catalytic-gate FETs opened up the field of FET-based gas sensors and other gas-sensitive field-effect devices such as capacitor-based [13–17] and Schottky diode-based sensors [18, 19]. Catalytic-gate field-effect devices feature a nanoscale layer of catalytic metals, such as palladium and platinum, as a gate electrode on insulating layers in a metal-insulator-semiconductor (MIS) structure [20]. **Figure 1** shows reported schematic illustrations of this structure and the threshold voltage shift of a Pd-gate FET that is sensitive to hydrogen [21]. In initial reports of catalytic-gate FETs, Pd as a catalytic-gate electrode was deposited onto the insulating layer of the MIS structure of the FET [11, 12, 21]. **Figure 2** shows changes observed in the threshold voltage [11] on hydrogen introduction to Pd-gate FETs. The gas-sensitive mechanisms of catalytic-gate FETs and catalytic-gate field-effect devices have been described in earlier reviews [20, 21].

Porous metal gates in catalytic-gate field-effect devices have allowed for important progress in NH_3 sensing [20, 22]. **Figure 3** shows reported TEM observations of 3- and 7-nm-thick Pt layers evaporated onto SiO_2 . These thin Pt layers consist of discontinuous metals [22]. The choice of catalytic materials, the structure of the catalytic layer, and the operating temperature affect the sensitivity and selectivity of catalytic-gate field-effect devices [14, 15, 20]. Furthermore, the type of insulating materials used in the MIS structure also influences the responsive properties of gas-sensitive field-effect devices [16].

For operation at high temperatures, silicon carbide (SiC)-based FETs have been investigated. SiC is a wide-bandgap semiconductor, and can be used as a substrate for the MIS structure instead of the conventional Si substrate [17]. SiC can be used at high temperatures and harsh environments because of its chemical inertness [23–25]. SiC-based FETs have been applied to the sensing of CO [23], NH_3 [23, 24], NO_2 [24], and SO_2 [25]. As with conventional catalytic-gate FETs using an Si substrate, the catalytic-gate material used in SiC-based FETs influences the sensitivity and selectivity of the sensor [25].

Catalytic-gate devices consisting of high-electron mobility transistors (HEMTs) have also been studied for operation at high temperature. For example, GaN/AlGaN heterostructures that exhibit two-dimensional electron gas (2DEG) induced by spontaneous and piezoelectric polarization at the interface of the heterostructure have been applied to a catalytic-gate HEMT

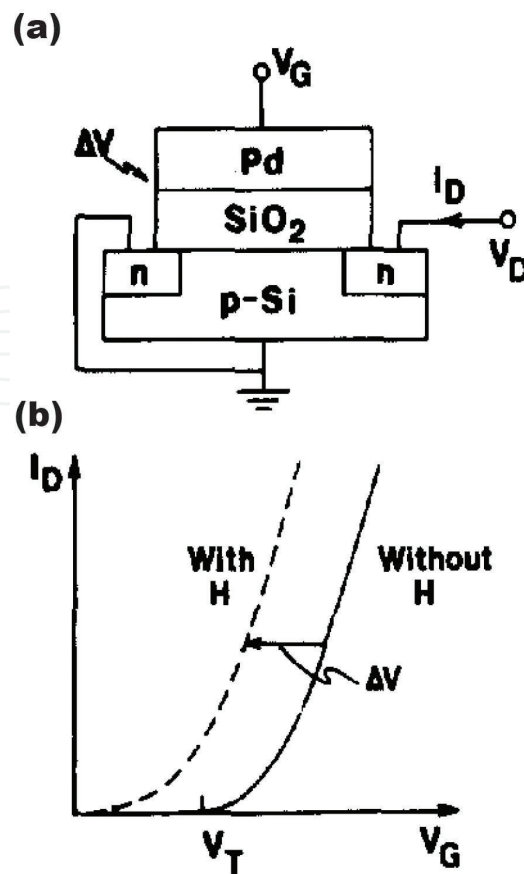


Figure 1. Schematic illustrations of the (a) structure and (b) threshold voltage shift of a Pd-gate FET sensitive to hydrogen. Reprinted with permission from Ref. [21]. Copyright 1993 Elsevier.

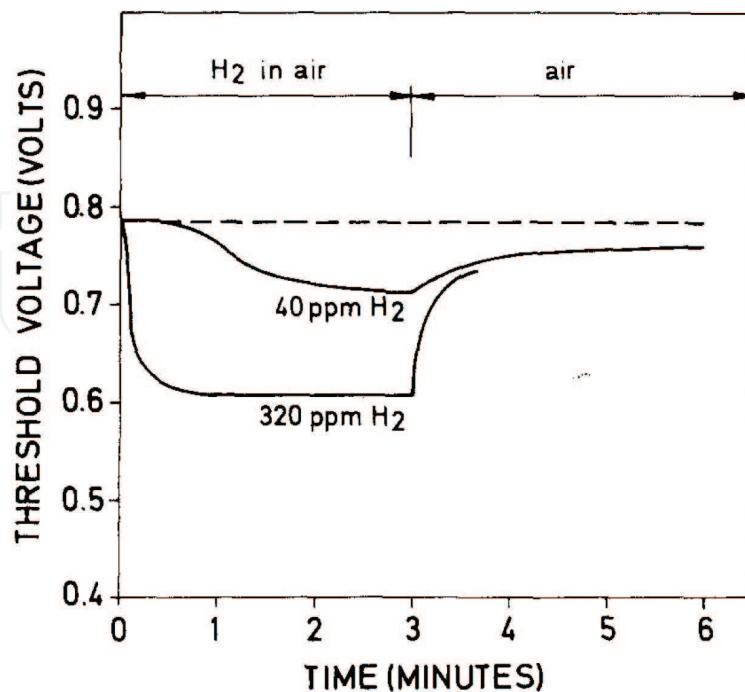


Figure 2. Changes in the threshold voltage toward H₂ at different concentrations at 150°C. Reprinted with permission from Ref. [11]. Copyright 1975 American Institute of Physics.

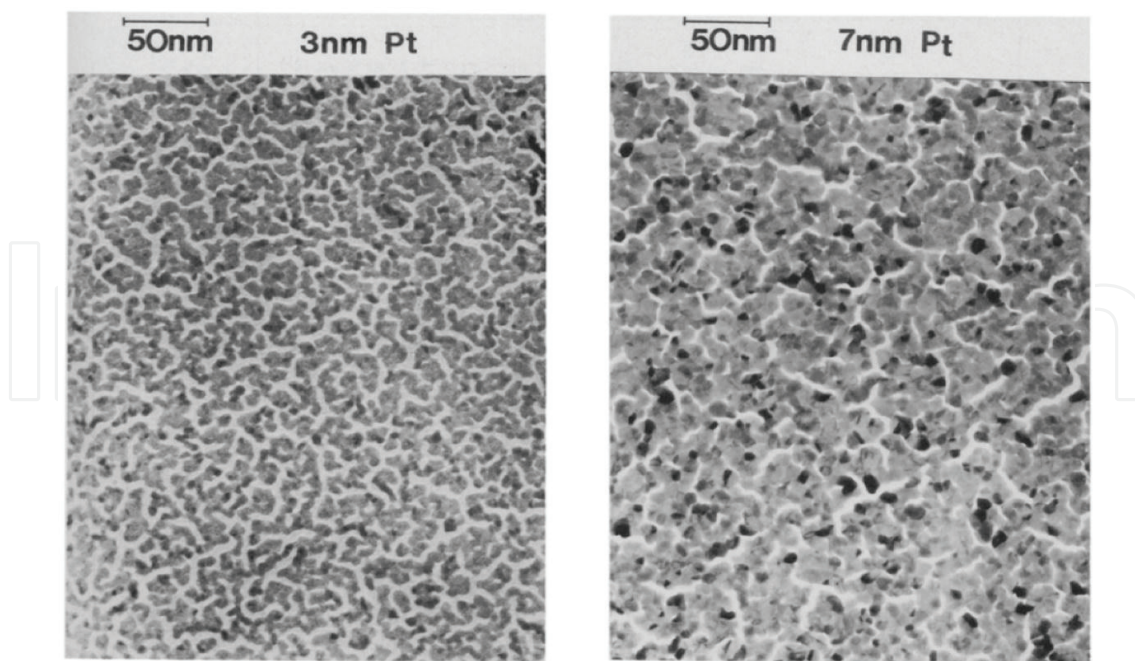


Figure 3. Transmission electron micrographs of 3- and 7-nm thick porous Pt metal layers on SiO_2 . Reprinted with permission from Ref. [22]. Copyright 1987 Elsevier.

as a gas sensor [26]. In this report, the GaN/AlGaN-based HEMT combined with a Pt gate electrode was operated at about 400°C for sensing of H_2 , CO, C_2H_2 , and NO_2 .

3. Solid electrolyte-based FETs

Solid electrolytes can also be applied to FET-based sensors. For example, an FET-based oxygen sensor using yttria-stabilized zirconia (YSZ) as a solid electrolyte (**Figure 4**) has been reported [27]. In this sensor, a YSZ film was formed on an insulating layer consisting of Si_3N_4 and SiO_2 . Furthermore, a nanoscale layer of Pt was deposited on the YSZ film as a gate electrode. **Figure 5** shows responses of this sensor to oxygen and nitrogen (1 atm) [27]. At room temperature, a repeated stepwise response curve and a subsequent drift were observed. The response of the sensor showed a linear relationship against the partial pressure of oxygen in a logarithmic range between 0.01 and 1 atm. The sensitivity of the sensor to oxygen increased as the thickness of the Pt layer decreased.

To investigate the YSZ-based FET structure for use as an oxygen sensor, the crystalline structure and electrical properties were studied for a YSZ film deposited on a layer of Si_3N_4 by RF sputtering [28]. In the capacitance-voltage curve, hysteresis was observed, and was considered to be caused by the movement of oxygen ions and/or electrons in the YSZ film. This resulted in an unstable response at room temperature as mentioned above. Therefore, to increase the stability and quicken the response of the oxygen sensor at room temperature, the solid electrolyte-based FET would need to incorporate an electrolyte with a high diffusion coefficient for oxygen ions [28].

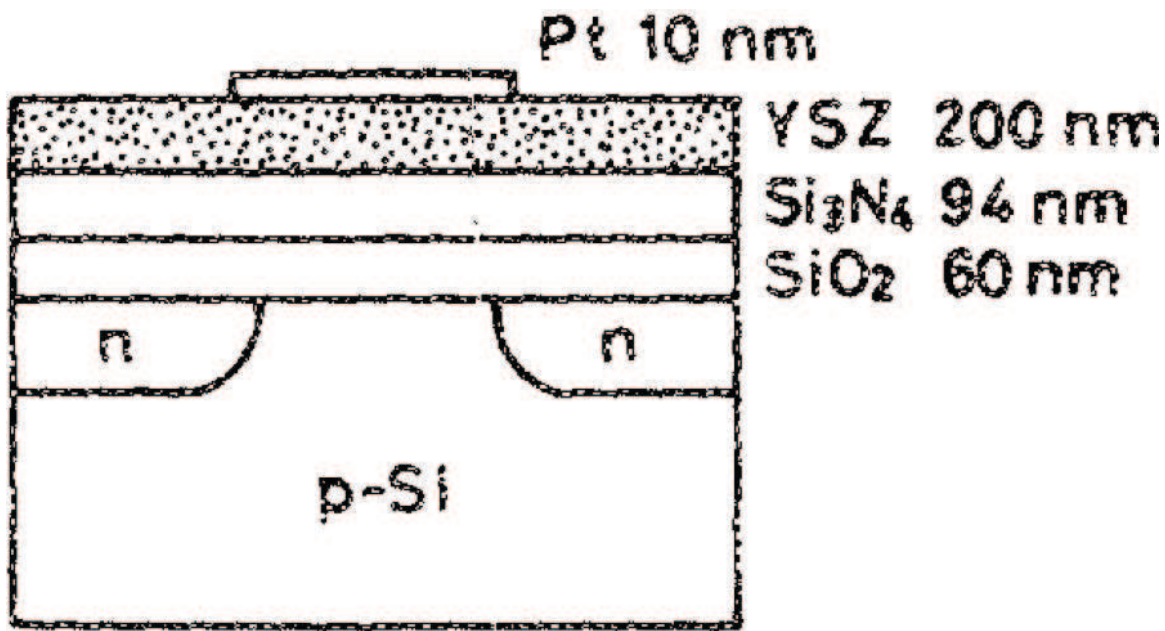


Figure 4. Schematic illustration of a YSZ-based FET. The YSZ-based FET is n-channel type and depletion-mode device. A nanoscale Pt layer is formed on a layer of YSZ. Reprinted with permission from Ref. [27]. Copyright 1988 American Institute of Physics.

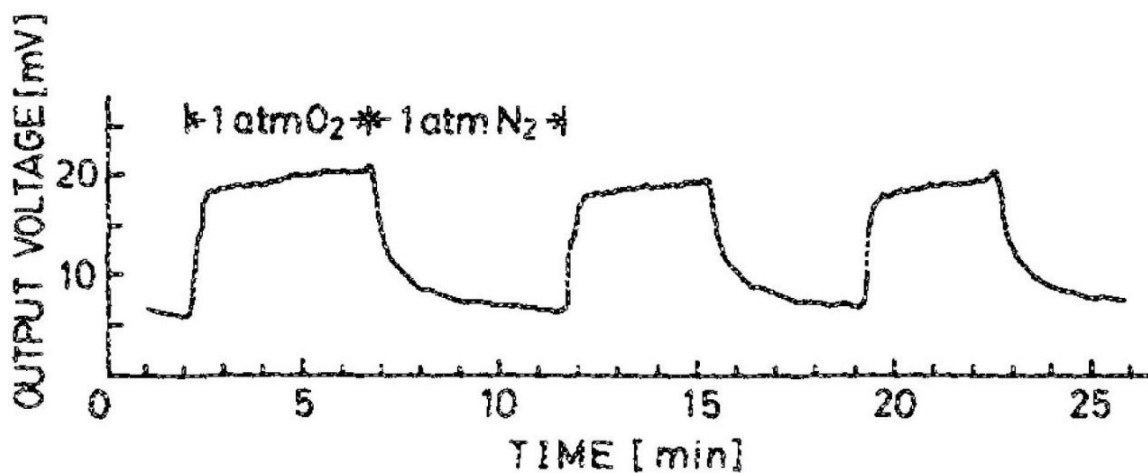


Figure 5. Responses at 20°C of a YSZ-based FET against O₂ and N₂. Reprinted with permission from Ref. [27]. Copyright 1988 American Institute of Physics.

4. Suspended-gate FETs

In 1983, Janata et al. reported an SGFET sensitive to dipolar molecules such as methanol and methylene chloride [29]. In the SGFET shown in **Figure 6**, fluid samples can penetrate into the gap between the insulating layer and the suspended metal mesh. Electrochemical surface modification using polypyrroles has been used to improve the selectivity of the SGFET [30]. This report described the preparation of SGFETs with differential selectivity by chemical modification with a polymer coating.

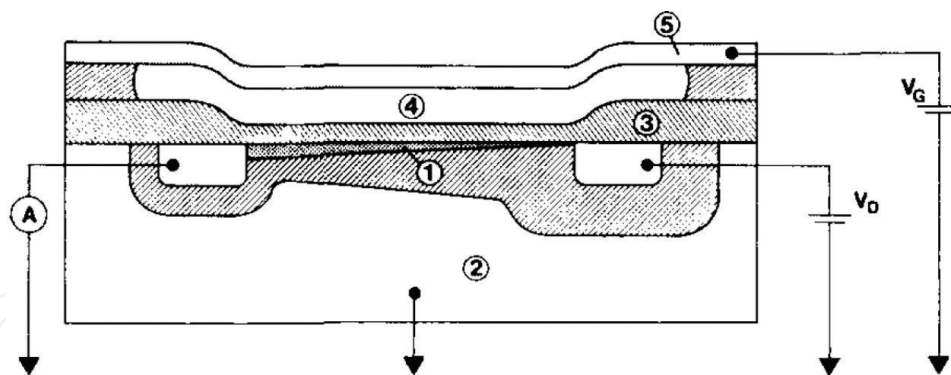


Figure 6. Schematic illustration of a suspended gate FET. Reprinted with permission from Ref. [29]. Copyright 1983 American Institute of Physics.

Improvement of fabrication processes is an important topic in SGFET research. Hybrid SGFETs prepared using an improved process and with diverse materials in the sensing layer have been reported [31]. In the fabrication process of hybrid SGFETs, the gate and body chip are prepared separately and then combined. This manufacturing technique has advantages over conventional methods because it allows for incorporation of a diverse range of sensitive materials in the structure. The flip-chip method has also been applied to the preparation of an SGFET for sensing ammonia [32]. In this report, a polyacrylic acid layer was formed on the gate structure by a spraying process.

The air gap in the gate structure of an SGFET causes undesirable effects on the sensing stability because of a lack of passivation, small W/L ratio, and a low gate capacity [33]. To overcome these drawbacks, research on SGFETs has been expanded to capacitively controlled FETs (CCFETs) [33] and floating-gate GasFETs (FGFETs) [34]. CCFETs contain an FET structure and a gas-sensitive capacitor with an air gap. FGFETs are a modification of CCFETs that use a floating gate for improved signal stability [34]. An FGFET with a hybrid-mounted gas-sensitive top electrode has been reported (Figure 7a) [34]. In this structure, the gas-sensitive capacitor and read-out transistor were integrated in one chip. Figure 7b shows the equivalent circuit diagram of the FGFET. The gate and the plate are electrically floating because they are isolated by the SiO_2 layer. This FGFET was used for sensing H_2 (500 ppm).

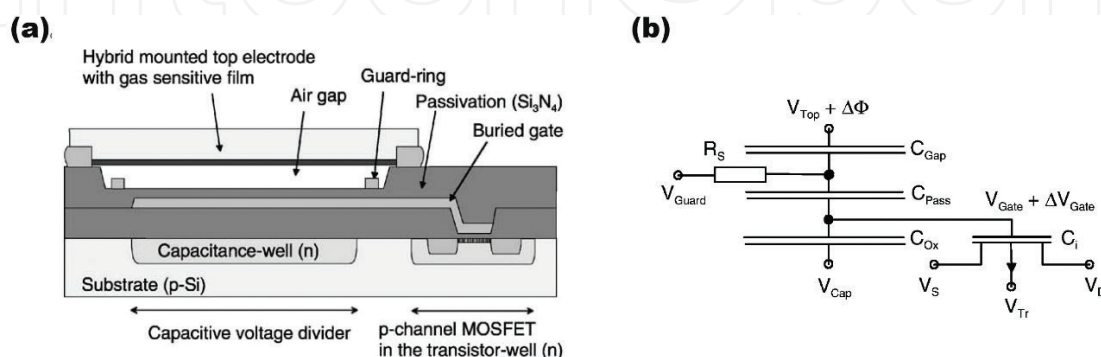


Figure 7. (a) Schematic illustration and (b) equivalent circuit diagram of a reported FGFET. Reprinted with permission from Ref. [34]. Copyright 2003 Elsevier.

Different FET-based sensors can be combined to extend the sensitivity range. For example, an SGFET responsive to high concentrations of H_2 and a catalytic-gate FET with good sensitivity for low concentrations of H_2 have been combined in one chip to increase the sensitivity range [35].

5. Nanomaterial-based FETs

FET-based gas sensors have been expanded to sensors containing nanomaterials. Nanomaterial-based FETs have large surface-to-volume ratios, which contribute to high sensitivity and fast response and recovery times [3]. Nanomaterials allow for high-packing densities because of their intrinsic small dimensions [5]. This section briefly reviews FET-based gas sensors using nanomaterials such as CNTs, NWs, graphene, and transition metal chalcogenides.

5.1. CNT-based FETs

The fabrication of CNT-based FETs was first reported in 1998 [36, 37]. A typical CNT-based FET consists of a CNT, source and drain electrodes, insulating layer, and a substrate as the back gate [38]. Both individual CNTs and random networks of CNTs can be used to prepare CNT-based FETs. Chemical-gating effects of an individual single-walled CNT-based FET caused by exposure to gaseous NH_3 or NO_2 were reported in 2000 [39]. To date, CNT-based FETs have been applied to sensing H_2 [40], CH_4 [40], CO [40], CO_2 [41], NO_2 [40], NH_3 [40], H_2S [40], alcohols [42], and breath samples [43].

To improve the sensitivity and selectivity of CNT-based FETs, they have been modified with nanoscale catalytic materials such as Pd [40, 44], Pt [40, 44], Rh [40], Au [40, 44], and Ag [44]. Furthermore, modifications with polymers [41], peptides [44], olfactory receptor proteins [45], and DNA [46, 47] have been reported.

5.2. NW-based FETs

5.2.1. Gas-sensitive FETs using Si NWs

As a gas-sensitive FET using one-dimensional nanomaterials, an application of an Si NW-based FET for sensing NH_3 was reported in 2006 [48]. After that, an FET-based sensor consisting of a highly ordered Si NW array on a bendable plastic substrate was prepared and applied to sensing NO_2 at parts per billion levels [49]. Furthermore, Si NW-based sensors have been applied to sensing H_2 [50].

Despite the potential of Si NW-based FETs for gas sensing, the sensitivity of bare Si NW-based FETs toward nonpolar volatile analytes is limited [51]. To overcome this, the native SiO_2 layer on the surface of the Si NWs has been chemically modified with silane monolayers [51]. Silane monolayer-modified Si NW-based FETs have been used for sensing nonpolar VOCs [51] and exhaled breath samples [52]. Modification with nanoparticles [50] has also been used to improve the responses of Si nanomaterial-based FETs to target analytes. In addition, an Si nanoribbon-based FET functionalized with an organic compound that is reactive toward nerve agents at sub-ppm levels has been reported [53].

5.2.2. Gas-sensitive FETs using metal oxide NWs or compound semiconductor NWs

Metal oxide NWs such as In_2O_3 [54, 55], SnO_2 [56–58], and $\alpha\text{-Fe}_2\text{O}_3$ [59] have also been applied to FET-based gas sensors. For example, an In_2O_3 NW-based FET has been used for sensing NO_2 and NH_3 [54].

Surface modification of NWs with nanoparticles has been used to improve the sensitivity and selectivity of gas-sensitive metal oxide NW-based FETs. To date, Pd [56, 58], Pt [55], Ag [55], Au [55], ZnO [57], and NiO [57] nanoparticles have been used to improve the properties of metal oxide NW-based FETs for gas sensing. For example, Moskovis et al. reported modification of SnO_2 NW-based FETs with Pd nanoparticles, and the application of this device to sensing H_2 [58]. In this work, an unusual sensitivity to H_2 in the charge depletion region of the device was reported [58]. This device was used for sensing a H_2 concentration range from 10 to 2500 ppm [58].

Compound semiconductor NWs have also been applied in FET-based sensors [60, 61]. Gao and coworkers applied NWs of InAs, which is a III–V semiconductor, to fabrication of a gas-sensitive FET [60]. This FET-based sensor was responsive to several gases and alcoholic vapors [60].

5.3. 2D nanomaterial-based FETs

Because of their high surface-to-volume ratios in molecular-level interactions, two-dimensional nanomaterials are attractive for use in FET-based sensors [5, 62]. Applications of 2D nanomaterials such as graphene and transition metal chalcogenides to FET-type gas sensors have been studied.

Since the potential of graphene-based sensors for gas sensing was first reported [63], other studies have investigated gas sensing using graphene-based FETs [62, 64]. A reported graphene-based FET is shown in **Figure 8** [64]. **Figure 8a** shows an atomic force microscopy (AFM) image of the FET based on graphene. Schematic diagram of the back-gate-type FET is shown in **Figure 8b** [64]. In the structure, the FET consists of a graphene sample connected

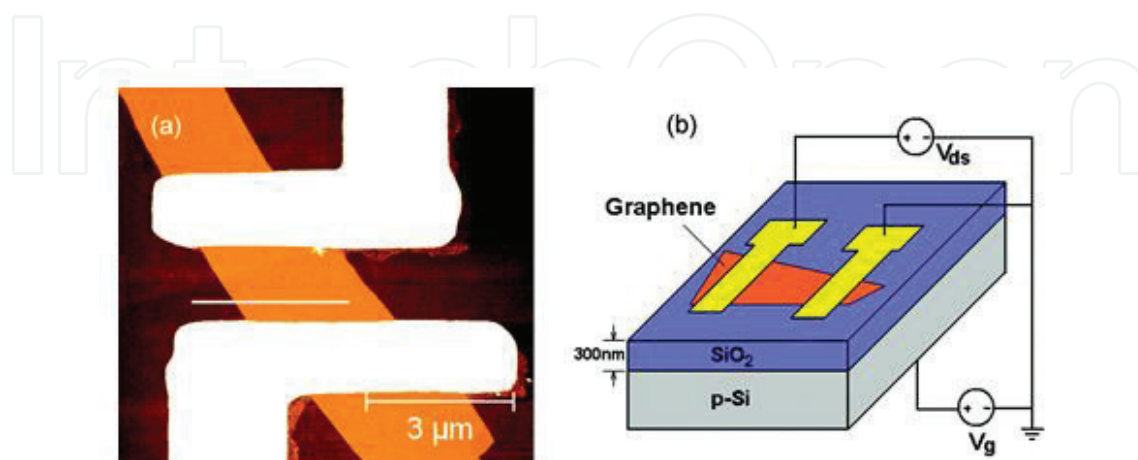


Figure 8. (a) AFM image and (b) schematic illustration of a graphene-based FET. Reprinted with permission from Ref. [64]. Copyright 2009 American Chemical Society.

with source and drain electrodes of Au/Cr, an SiO₂-insulating layer, and a p-Si substrate as the back gate. In this report, the sensor was used for sensing NH₃ vapors [64].

As 2D nanomaterials, the transition metal chalcogenides MoS₂ [65], MoTe₂ [66], and WS₂ [67] have also been applied in FET-based gas sensors. **Figure 9a** shows a schematic illustration of a back-gate FET based on MoS₂ [5]. **Figure 9b** shows an optical image of MoS₂-based FETs. In this FET, MoS₂ sheets were grown on an SiO₂/Si substrate, with Ti/Au as the source and drain electrodes. This sensor was responsive to 20 ppb NO₂ and 1 ppm NH₃ [5].

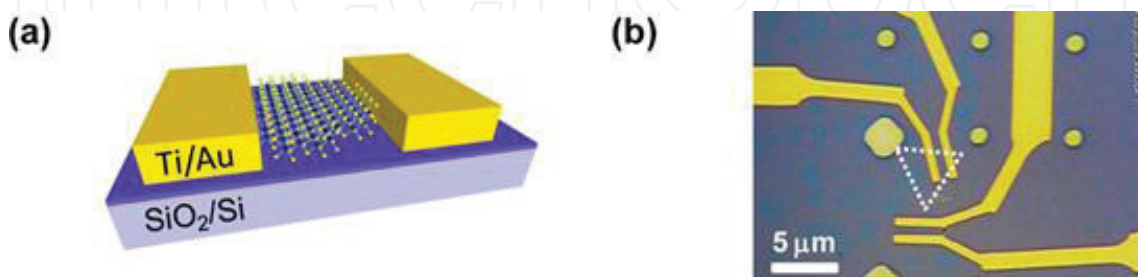


Figure 9. (a) Schematic illustration and (b) optical image of a back-gate MoS₂ nanowire-based FET. Reprinted with permission from Ref. [5]. Copyright 2014 American Chemical Society.

6. Combination of gas sensors and pattern recognition methods

According to an earlier review [6], receptors in mammalian olfactory systems do not show highly selective responses against specific analytes. Pattern recognition methods are thought to be a dominant mode used in processing signals from the broad responses of the mammalian olfactory system [6].

Cross-reactive chemical sensor arrays combined with pattern recognition methods to mimic mammalian olfactory systems have been studied as an alternative sensor system to traditional sensing devices that use a “lock-and-key” design [6]. In intelligent sensor arrays using pattern recognition methods, complex patterns generated by nonspecific cross-reactive sensors are analyzed for classification and identification of analytes [3, 6–8]. Cross-reactive sensor arrays are constructed using sensors that are responsive to a broad range of analytes and have differential sensitivity [3, 6]. Conventional semiconductor processes can be applied to miniaturize FET-based sensors for the fabrication of cross-reactive sensor arrays.

Before data analysis, complex signals obtained from sensor arrays can be preprocessed and normalized for the application of appropriate computational methods [7, 8, 10]. After preprocessing and feature extraction, the selected method is performed. Currently, there is no general rule for the selection of computational methods. Therefore, computational methods must be appropriately selected on the nature of the data and the particular situation [7].

Various types of gas sensor arrays have been used with pattern recognition methods [6–8], including FET-based gas sensor arrays. For example, Lundström et al. reported combination

of catalytic-gate FET-based gas sensor arrays with pattern recognition methods [68, 69]. The signals from the FET-based sensor arrays were processed using conventional partial least-squares regression and an artificial neural network to predict the concentrations of individual gases [69]. Molecularly modified Si NW-based FET sensors have also been combined with an artificial neural network to recognize VOCs and estimate their concentrations [70].

7. Overview and outlook

For the introduction of gas-sensitive FETs, a broad overview of catalytic-gate FETs, solid electrolyte-based FETs, suspended-gate FETs, and nanomaterial-based FETs is given in this chapter. Arrays of these sensors can be combined with computational pattern recognition methods. As introduced, the combination of cross-reactive gas sensor arrays with pattern recognition methods is a promising method for the recognition of analytes in the gas phase. Cross-reactive sensor arrays should contain sensors that are responsive to a broad range of analytes and have differential sensitivity. Conventional semiconductor processes can be used for miniaturization of FET-based sensors. FET-based sensors may have advantages over other sensors used in device miniaturization of cross-reactive sensor arrays.

Acknowledgements

This work was supported by ImPACT Program of Council for Science, Technology and Innovation.

Author details

Toshihiro Yoshizumi* and Yuji Miyahara

*Address all correspondence to: yoshizumi.bsr@tmd.ac.jp

Institute of Biomaterials and Bioengineering, Tokyo Medical and Dental University, Tokyo, Japan

References

- [1] Turner PFA, Magan N. Electronic noses and disease diagnostics. *Nature Reviews*. 2004;**2**: 161-166
- [2] Konvalina G, Haick H. Sensors for breath testing: From nanomaterials to comprehensive disease detection. *Accounts of Chemical Research*. 2014;**47**:66-76

- [3] Vishinkin R, Haick H. Nanoscale sensor technologies for disease detection via volatolomics. *Small*. 2015;**11**:6142-6164
- [4] Potyrailo AR. Multivariable sensors for ubiquitous monitoring of gases in the era of Internet of things and industrial Internet. *Chemical Reviews*. 2016;**116**:11877-11923
- [5] Liu B, Chen L, Liu G, Abbas NA, Fathi M, Zhou C. High-performance chemical sensing using Schottky-contacted chemical vapor deposition grown monolayer MoS₂ transistors. *ACS Nano*. 2014;**8**:5304-5314
- [6] Albert JK, Lewis SN, Schauer LC, Sotzing AG, Stitzel ES, Vaid PT, Walt RD. Cross-reactive chemical sensor arrays. *Chemical Reviews*. 2000;**100**:2595-2626
- [7] Jurs CP, Bakken AG, McClelland EH. Computational methods for the analysis of chemical sensor array data from volatile analytes. *Chemical Reviews*. 2000;**100**:2649-2678
- [8] Hierlemann A, Gutierrez-Osuna R. Higher-order chemical sensing. *Chemical Reviews*. 2008;**108**:563-613
- [9] Chen X, Wong KYC, Yuan AC, Zhang G. Nanowire-based gas sensors. *Sensors and Actuators B*. 2013;**177**:178-195
- [10] Göpel W. Chemical imaging: I. Concepts and visions for electronic and bioelectronic noses. *Sensors and Actuators B*. 1998;**52**:125-142
- [11] Lundström I, Shivaraman S, Svensson C, Lundkvist L. A hydrogen-sensitive MOS field-effect transistor. *Applied Physics Letters*. 1975;**26**:55-57
- [12] Lundström IK, Shivaraman SM, Svensson MC. A hydrogen-sensitive Pd-gate MOS transistor. *Journal of Applied Physics*. 1975;**46**:3876-3881
- [13] Winqvist F, Spetz A, Armgarth M, Nylander C, Lundström I. Modified palladium metal-oxide-semiconductor structures with increased ammonia gas sensitivity. *Applied Physics Letters*. 1983;**43**:839-841
- [14] Lundström I, Spetz A, Winqvist F, Ackelid U, Sundgren H. Catalytic metals and field-effect devices—a useful combination. *Sensors and Actuators B*. 1990;**1**:15-20
- [15] Löfdahl M, Eriksson M, Johansson M, Lundström I. Difference in hydrogen sensitivity between Pt and Pd field-effect devices. *Journal of Applied Physics*. 2002;**91**:4275-4280
- [16] Eriksson M, Salomonsson A, Lundström I, Briand D, Åbom EA. The influence of the insulator surface properties on the hydrogen response of field-effect gas sensors. *Journal of Applied Physics*. 2005;**98**:0349031-0349036
- [17] Trinchì A, Kandasamy S, Wlodarski W. High temperature field effect hydrogen and hydrocarbon gas sensors based on SiC MOS devices. *Sensors and Actuators B*. 2008;**133**:705-716
- [18] Steele CM, MacIver AB. Palladium/cadmium-sulfide Schottky diodes for hydrogen detection. *Applied Physics Letters*. 1976;**28**:687-688

- [19] Ito K. Hydrogen-sensitive Schottky barrier diodes. *Surface Science*. 1979;**86**:345-352
- [20] Lundström I, Sundgren H, Winqvist F, Eriksson M, Krantz-Rülcker C, Lloyd-Spetz A. Twenty-five years of field effect gas sensor research in Linköping. *Sensors and Actuators B*. 2007;**121**:247-262
- [21] Lundström I, Svensson C, Spetz A, Sundgren H, Winqvist F. From hydrogen sensors to olfactory images – twenty years with catalytic field-effect devices. *Sensors and Actuators B*. 1993;**13**:16-23
- [22] Spetz A, Armgarth M, Lundström I. Optimization of ammonia-sensitive metal-oxide-semiconductor structures with platinum gates. *Sensors and Actuators*. 1987;**11**:349-365
- [23] Andersson M, Pearce R, Spetz LA. New generation SiC based field effect transistor gas sensors. *Sensors and Actuators B*. 2013;**179**:95-106
- [24] Bur C, Bastuck M, Spetz LA, Andersson M, Schütze A. Selectivity enhancement of SiC-FET gas sensors by combining temperature and gate bias cycled operation using multivariate statistics. *Sensors and Actuators B*. 2014;**193**:931-940
- [25] Darmastuti Z, Bur C, Möller P, Rahlin R, Lindqvist N, Andersson M. SiC-FET based SO₂ sensor for power plant emission applications. *Sensors and Actuators B*. 2014;**194**:511-520
- [26] Schalwig J, Müller G, Eickhoff M, Ambacher O, Stutzmann M. Gas sensitive GaN/AlGaN-heterostructures. *Sensors and Actuators B*. 2002;**87**:425-430
- [27] Miyahara Y, Tsukada K, Miyagi H. Field-effect transistor using a solid electrolyte as a new oxygen sensor. *Journal of Applied Physics*. 1988;**63**:2431-2434
- [28] Miyahara Y. Characterization of sputtered yttria-stabilized zirconia thin film and its application to a metal-insulator-semiconductor structure. *Journal of Applied Physics*. 1992;**71**:2309-2314
- [29] Blackburn FG, Levy M, Janata J. Field-effect transistor sensitive to dipolar molecules. *Applied Physics letters*. 1983;**43**:700-701
- [30] Josowicz M, Janata J. Suspended gate field effect transistor modified with polypyrrole as alcohol sensor. *Analytical Chemistry*. 1986;**58**:514-517
- [31] Flietner B, Doll T, Lechner J, Leu M, Eisele I. Fabrication of a hybrid field-effect structure for gas detection with diverse sensitive materials. *Sensors and Actuators B*. 1994;**19**:632-636
- [32] Oprea A, Simon E, Fleischer M, Frerichs PH, Wilbertz C, Lehmann M, Weimar U. Flip-chip suspended gate field effect transistors for ammonia detection. *Sensors and Actuators B*. 2005;**111-112**:582-586
- [33] Gergintschew Z, Kornetzky P, Schipanski D. The capacitively controlled field effect transistor (CCFET) as a new low power gas sensor. *Sensors and Actuators B*. 1996;**36**:285-289
- [34] Burgmair M, Frerichs PH, Zimmer M, Lehmann M, Eisele I. Field effect transducers for work function gas measurements: Device improvements and comparison of performance. *Sensors and Actuators B*. 2003;**95**:183-188

- [35] Wilbertz C, Frerichs PH, Freund I, Lehmann M. Suspended-gate- and Lundstrom-FET integrated on a CMOS-chip. *Sensors and Actuators A*. 2005;**123-124**:2-6
- [36] Tans JS, Verschueren RMA, Dekker C. Room-temperature transistor based on a single carbon nanotube. *Nature*. 1998;**393**:49-52
- [37] Martel R, Schmidt T, Shea RH, Hertel T, Avouris P. Single- and multi-wall carbon nanotube field-effect transistors. *Applied Physics Letters*. 1998;**73**:2447-2449
- [38] Wilbertz C, Frerichs PH, Freund I. Carbon nanotube gas and vapor sensors. *Angewandte Chemie*. 2008;**47**:6550-6570
- [39] Kong J, Franklin RN, Zhou C, Chaplin GM, Peng S, Cho K, Dai H. Nanotube molecular wires as chemical sensors. *Science*. 2000;**287**:622-625
- [40] Star A, Joshi V, Skarupo S, David T, Gabriel CPJ. Gas sensor array based on metal-decorated carbon nanotubes. *The Journal of Physical Chemistry B*. 2006;**110**:21014-21020
- [41] Star A, Han RT, Joshi V, Gabriel CPJ, Grüner G. Nanoelectronic carbon dioxide sensors. *Advanced Materials*. 2004;**16**:2049-2052
- [42] Someya T, Small J, Kim P, Nuckolls C, Yardley TJ. Alcohol vapor sensors based on single-walled carbon nanotube field effect transistors. *Nano Letters*. 2003;**3**:877-881
- [43] Peng G, Tisch U, Haick H. Detection of nonpolar molecules by means of carrier scattering in random network of carbon nanotubes: Toward diagnosis of diseases via breath samples. *Nano Letters*. 2009;**3**:347-351
- [44] Kuang Z, Kim NS, Crookes-Goodson JW, Farmer LB, Naik RR. Biomimetic chemosensor: Designing peptide recognition elements for surface functionalization of carbon nanotube field effect transistors. *ACS Nano*. 2010;**4**:452-458
- [45] Goldsmith RB, Mitala JJ, Josue J, Castro A, Lerner BM, Bayburt HT, Khamis MS, Jones AR, Brand GJ, Sligar GS, Luetje WC, Gelperin A, Rhodes AP, Discher MB, Johnson CAT. Biomimetic chemical sensors using nanoelectronic readout of olfactory receptor proteins. *ACS Nano*. 2011;**5**:5408-5416
- [46] Staii C, Johnson TA. DNA-decorated carbon nanotubes for chemical sensing. *Nano Letters*. 2005;**5**:1774-1778
- [47] Kuang Z, Kim NS, Crookes-Goodson JW, Farmer LB, Naik RR. Differentiation of complex vapor mixtures using versatile DNA-carbon nanotube chemical sensor arrays. *ACS Nano*. 2013;**7**:2800-2807
- [48] Talin AA, Hunter LL, Léonard F, Rokad B. Large area, dense silicon nanowire array chemical sensors. *Applied Physics Letters*. 2006;**89**:1531021-1531023
- [49] Mcalpine CM, Ahmad H, Wang D, Heath RJ. Highly ordered nanowire arrays on plastic substrates for ultrasensitive flexible chemical sensors. *Nature Materials*. 2007;**6**:379-384
- [50] Chen HZ, Jie SJ, Luo BL, Wang H, Lee SC, Lee TS. Applications of silicon nanowires functionalized with palladium nanoparticles in hydrogen sensors. *Nanotechnology*. 2007;**18**:345502

- [51] Paska Y, Stelzner T, Christiansen S, Haick H. Enhanced sensing of nonpolar volatile organic compounds by silicon nanowire field effect transistors. *ACS Nano*. 2011;**5**: 5620-5626
- [52] Shehada N, Brönstrup G, Funka K, Christiansen S, Leja M, Haick H. Ultrasensitive silicon nanowire for real-world gas sensing: Noninvasive diagnosis of cancer from breath volatolome. *Nano Letters*. 2015;**15**:1288-1295
- [53] Clavaguera S, Carella A, Caillier L, Celle C, Pécaut J, Lenfant S, Vuillaume D, Simonato PJ. Sub-ppm detection of nerve agents using chemically functionalized silicon nanoribbon field-effect transistors. *Angewandte Chemie*. 2010;**49**:4063-4066
- [54] Li C, Zhang D, Liu X, Han S, Tang T, Han J, Zhou C. In_2O_3 nanowires as chemical sensors. *Applied Physics Letters*. 2003;**82**:1613.
- [55] Zou X, Wang J, Liu X, Wang C, Jiang Y, Wang Y, Xiao X, Ho CJ, Li J, Jiang C, Fang Y, Liu W, Liao L. Rational design of sub-parts per million specific gas sensors array based on metal nanoparticles decorated nanowire enhancement-mode transistors. *Nano Letters*. 2013;**13**:3287-3292
- [56] Kolmakov A, Klenov OD, Stemmer S, Moskovits M. Enhanced gas sensing by individual SnO_2 nanowires and nanobelts functionalized with Pd catalyst particles. *Nano Letters*. 2005;**5**:667-673
- [57] Kuang Q, Lao SC, Li Z, Liu ZY, Xie XZ, Zheng SL, Wang LZ. Enhancing the photon- and gas-sensing properties of a single SnO_2 nanowire based nanodevice by nanoparticle surface functionalization. *The Journal of Physical Chemistry C*. 2008;**112**:11539-11544
- [58] Mubeen S, Moskovits M. Gate-tunable surface processes on a single-nanowire field-effect transistor. *Advanced Materials*. 2011;**23**:2306-2312
- [59] Liao L, Zheng Z, Yan B, Zhang XJ, Gong H, Li CJ, Liu C, Shen XZ, Yu T. Morphology controllable synthesis of $\alpha\text{-Fe}_2\text{O}_3$ 1D nanostructures: Growth mechanism and nanodevice based on single nanowire. *The Journal of Physical Chemistry C*. 2008;**112**:10784-10788
- [60] Du J, Liang D, Tang H, Gao PAX. InAs nanowire transistors as gas sensor and the response mechanism. *Nano Letters*. 2009;**9**:4348-4351
- [61] Zhang X, Fu M, Li X, Shi T, Ning Z, Wang X, Yang T, Chen Q. Study on the response of InAs nanowire transistors to H_2O and NO_2 . *Sensors and Actuators B*. 2015;**209**:456-461
- [62] Kulkarni SG, Reddy K, Zhong Z, Fan X. Graphene nanoelectronic heterodyne sensor for rapid and sensitive vapour detection. *Nature Communications*. 2014;**5**:4376
- [63] Schedin F, Geim KA, Morozov VS, Hill WE, Blake P, Katsnelson IM, Novoselov SK. Detection of individual gas molecules adsorbed on graphene. *Nature Materials*. 2007;**6**:652-655
- [64] Dan Y, Lu Y, Kybert JN, Luo Z, Johnson TCA. Intrinsic response of graphene vapor sensors. *Nano Letters*. 2009;**9**:1472-1475

- [65] Li H, Yin Z, He Q, Li H, Huang X, Lu G, Fam WHD, Tok LYA, Zhang Q, Zhang H. Fabrication of single- and multilayer MoS₂ film-based field-effect transistors for sensing NO at room temperature. *Small*. 2012;**8**:63-67
- [66] Lin FY, Xu Y, Lin YC, Suen WY, Yamamoto M, Nakaharai S, Ueno K, Tsukagoshi K. Origin of noise in layered MoTe₂ transistors and its possible use for environmental sensors. *Advanced Materials*. 2015;**27**:6612-6619
- [67] Huo N, Yang S, Wei Z, Li SS, Xia BJ, Li J. Photoresponsive and gas sensing field-effect transistors based on multilayer WS₂ nanoflakes. *Scientific Reports*. 2014;**4**:5209
- [68] Sundgren H, Lundström I, Winqvist F, Lukkari I, Carlsson R, Wold S. Evaluation of a multiple gas mixture with a simple MOSFET gas sensor array and pattern recognition. *Sensors and Actuators B*. 1990;**2**:115-123
- [69] Sundgren H, Winqvist F, Lukkar I, Lundström I. Artificial neural networks and gas sensor arrays: Quantification of individual components in a gas mixture. *Measurement Science and Technology*. 1991;**2**:464-469
- [70] Wang B, Cancilla CJ, Torrecilla SC, Haick H. Artificial sensing intelligence with silicon nanowires for ultraselective detection in the gas phase. *Nano Letters*. 2014;**14**:933-938

